



Standard Specification for Pressure Vessel Plates, Alloy Steel, Chromium-Molybdenum-Vanadium¹

This standard is issued under the fixed designation A 832/A 832M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

^{e1} NOTE—An editorial change was made in June 2001.

1. Scope

1.1 This specification² covers chromium-molybdenum-vanadium alloy steel plates intended primarily for the fabrication of welded pressure vessels.

1.2 The plates furnished under this specification are required to be normalized-and-tempered. Specification A 542/A 542M includes coverage of the material in the quenched-and-tempered condition.

1.3 The maximum thickness of plates furnished to this specification is limited only by the capacity of the composition to meet the specified property requirements. However, the maximum thickness of plates normally furnished under this specification is 6 in. [150 mm].

1.4 The material is intended to be suitable for fusion welding. Welding technique is of fundamental importance and it is presupposed that welding procedures will be in accordance with approved methods.

1.5 This specification is expressed in both inch-pound units and in SI units. However, unless the order specifies the applicable “M” specification designation (SI units), the material shall be furnished to inch-pound units.

1.6 The values stated in either inch-pound units or SI units are to be regarded separately as standard. Within the text, the SI units are shown in brackets. The values stated in each system must be used independently of the other. Combining values from the two systems may result in nonconformance with the specification.

2. Referenced Documents

2.1 ASTM Standards:

A 20/A20M Specification for General Requirements for Steel Plates for Pressure Vessels³

A 370 Test Methods and Definitions for Mechanical Testing of Steel Products⁴

A 435/A435M Specification for Straight-Beam Ultrasonic Examination of Steel Plates³

A 542/A542M Specification for Pressure Vessel Plates, Alloy Steel, Quenched-and-Tempered, Chromium-Molybdenum and Chromium-Molybdenum-Vanadium³

A 577/A577M Specification for Ultrasonic Angle-Beam Examination of Steel Plates³

A 578/A578M Specification for Straight-Beam Ultrasonic Examination of Plain and Clad Steel Plates for Special Applications³

3. General Requirements and Ordering Information

3.1 Material supplied to this material specification shall conform to Specification A 20/A 20M. These requirements outline the testing and retesting methods and procedures, permissible variations in dimensions, quality and repair of defects, marking, loading, etc.

3.2 Specification A 20/A 20M establishes the rules for ordering information that should be complied with when purchasing material to this specification.

3.3 In addition to the basic requirements of this specification, certain supplementary requirements are available when additional control, testing, or examination is required to meet end use requirements. These include the following:

3.3.1 Vacuum treatment,

3.3.2 Additional or special tension testing,

3.3.3 Impact testing, and

3.3.4 Nondestructive examination.

3.4 The purchaser is referred to the listed supplementary requirements in this specification and to the detailed requirements in Specification A 20/A 20M. If the requirements of this

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel, and Related Alloys and is the direct responsibility of Subcommittee A01.11 on Steel Plates for Boilers and Pressure Vessels.

Current edition approved March 10, 1999. Published June 1999. Originally published as A 832/A 832M – 84. Last previous edition A 832/A832M – 97.

² For ASME Boiler and Pressure Vessel Code applications, see related Specification SA-832/SA-832M in Section II of that Code.

³ *Annual Book of ASTM Standards*, Vol 01.04.

⁴ *Annual Book of ASTM Standards*, Vol 01.01.

specification are in conflict with the requirements of Specification A 20/A 20M, the requirements of this specification shall prevail.

4. Manufacture

4.1 *Steelmaking Process*—The steel shall be made by one of the processes permitted in Specification A 20/A 20M.

4.2 *Steelmaking Practice*—The steel shall be killed and shall conform to the fine grain size requirement of Specification A 20/A 20M.

5. Heat Treatment

5.1 All plates shall be normalized and tempered except as allowed by 5.2. The minimum normalizing temperature for Grade 22V shall be 1650°F [900°C]. The minimum normalizing temperature for Grade 23V shall be 1850°F [1010°C]. The minimum tempering temperature shall be 1250°F [675°C].

5.2 Plates ordered without the heat treatment required by 5.1 shall be furnished in either the stress-relieved or the annealed condition. Heat treatment of plates so ordered, to conform to 5.1 and to Table 1, shall be the responsibility of the purchaser.

6. Chemical Composition

6.1 The steel shall conform to the requirements as to chemical composition shown in Table 2.

7. Mechanical Properties

7.1 Tension Test Requirements:

7.1.1 The material as represented by the tension test specimens shall conform to the requirements of Table 1.

7.2 Notch Toughness Requirements:

7.2.1 A transverse Charpy V-notch test from each plate as heat-treated shall have a minimum energy absorption value of 40 ft·lbf [54 J] average of three specimens and 35 ft·lbf [48 J] for one specimen only in the set.

TABLE 1 Tensile Requirements

Tensile strength, ksi, [MPa]	85–110 [585–760]
Yield strength, min, ksi, [MPa]	60 [415]
Elongation in 2 in. [50 mm], min, % ^A	18
Reduction of area, min, %	45 ^B 40 ^C

^ASee Specification A 20/A 20M for elongation adjustments.

^BMeasured on round specimen.

^CMeasured on flat specimen.

TABLE 2 Chemical Requirements

Element	Composition, %		
	Grade 21V	Grade 22V	Grade 23V
Carbon			
Heat analysis	0.10–0.15	0.11–0.15	0.10–0.15
Product analysis	0.08–0.18	0.09–0.18	0.08–0.18
Manganese			
Heat analysis	0.30–0.60	0.30–0.60	0.30–0.60
Product analysis	0.25–0.66	0.25–0.66	0.25–0.66
Phosphorus, max	0.025 ^A	...	0.025
Heat analysis	...	0.015	
Product analysis	...	0.020	
Sulfur, max	0.025 ^A	...	0.010
Heat analysis	...	0.010	
Product analysis	...	0.015	
Silicon, max			
Heat analysis	0.10	0.10	0.10
Product analysis	0.13	0.13	0.13
Chromium			
Heat analysis	2.75–3.25	2.00–2.50	2.75–3.25
Product analysis	2.63–3.37	1.88–2.62	2.63–3.37
Molybdenum			
Heat analysis	0.90–1.10	0.90–1.10	0.90–1.10
Product analysis	0.85–1.15	0.85–1.15	0.85–1.15
Vanadium			
Heat analysis	0.20–0.30	0.25–0.35	0.20–0.30
Product analysis	0.18–0.33	0.23–0.37	0.18–0.33
Titanium			
Heat analysis	0.015–0.035	0.030, max	
Product analysis	0.005–0.045	0.035, max	
Boron			
Heat analysis	0.001–0.003	0.0020, max	
Product analysis	NA ^B	NA ^B	
Copper, max			
Heat analysis	...	0.20	
Product analysis	...	0.23	
Nickel, max			
Heat analysis	...	0.25	
Product analysis	...	0.28	
Columbium, max			
Heat analysis	...	0.07	0.015–0.070
Product analysis	...	0.08	0.010–0.075
Calcium, max ^C			
Heat analysis	...	0.015	0.0005–0.0150
Product analysis	...	0.020	NA ^B

^AApplies to both heat analysis and product analysis.

^BNA = Not Applicable.

^CRare earth metals (REM) may be added in place of calcium, subject to agreement between the product and the purchaser. In that case, the total amount of REM shall be determined and reported.

7.2.2 The notch toughness test temperature shall be 0°F [–18°C].

8. Keywords

8.1 alloy steel plates; pressure containing parts; pressure vessel steels; steel plates; steel plates for pressure vessel applications

SUPPLEMENTARY REQUIREMENTS

Supplementary requirements shall not apply unless specified in the order.

A list of standardized supplementary requirements for use at the option of the purchaser is included in Specification A 20/A 20M. Some of those considered suitable for use with this specification are listed below by title.

- S1. Vacuum Treatment,
- S2. Product Analysis,
- S3. Simulated Post-Weld Heat Treatment of Mechanical Test Coupons,
- S4. Additional Tension Test,
- S6. Drop-Weight Test,
- S7. High-Temperature Tension Test,
- S8. Ultrasonic Examination in accordance with Specification A 435/A 435M,

- S9. Magnetic Particle Examination,
- S11. Ultrasonic Examination in accordance with Specification A 577/A 577M,
- S12. Ultrasonic Examination in accordance with Specification A 578/A 578M,
- S14. Bend Test,
- S19. Restricted Chemical Requirements.

ADDITIONAL SUPPLEMENTARY REQUIREMENTS
HIGH TEMPERATURE HYDROGEN SERVICE

In addition, the following supplementary requirements are suitable for this application.

S62. Temper Embrittlement Factor

S62.1 The composition of the steel, based on heat analysis, shall be restricted in accordance with the following equations:

$$J = (\text{Si} + \text{Mn}) \times (\text{P} + \text{Sn}) \times 10^4 \leq 150 \quad (\text{Si, Mn, P and Sn in wt \%})$$

$$\text{Cu} \leq 0.20 \%$$

$$\text{Ni} \leq 0.30 \%$$

S62.1.1 Lower values of J, Cu and Ni can be specified by agreement between purchaser and the supplier.

S62.1.2 When so specified by the purchaser, the maximum value of J shall not exceed 100.

S62.1.3 The values of J shall be reported.

S62.1.4 If the plates are repaired by welding, the composition of the weld deposit shall be restricted in accordance with the following equations:

$$X = (10\text{P} + 5\text{Sb} + 4\text{Sn} + \text{As})/100 \leq 15 \quad (\text{P, Sb, Sn and As in ppm})$$

$$\text{Cu} \leq 0.20 \%$$

$$\text{Ni} \leq 0.30 \%$$

S62.1.5 The values of X shall be reported.

S63. Impact Properties After Step Cooling

S63.1 The Charpy V-notch impact properties shall be determined as follows:

S63.1.1 A sufficient amount of Charpy V-notch test specimens shall be taken from the same location from a plate from each heat of steel to construct two transition temperature curves.

S63.1.2 The test specimens for one transition temperature curve shall be given the minimum post-weld heat treatment (PWHT) cycle specified by the purchaser.

S63.2 The test specimens for the other transition temperature curve shall be given the PWHT cycle specified in S63.1.2 plus the following step cooling heat treatment:

Hold at 1100°F (593°C) for 1 h, then cool at 10°F (5.6°C)/h to 1000°F (538°C).

Hold at 1000°F (538°C) for 15 h, then cool at 10°F (5.6°C)/h to 975°F (524°C).

Hold at 975°F (524°C) for 24 h, then cool at 10°F (5.6°C)/h to 925°F (496°C).

Hold at 925°F (496°C) for 60 h, then cool at 5°F (2.8°C)/h to 875°F (468°C).

Hold at 875°F (468°C) for 100 h, then cool at 50°F (27.8°C)/h to 600°F (315°C).

Cool in still air.

S63.3 Test the Charpy V-notch test specimens in accordance with Test Methods and Definitions A 370 to determine the 40-ft-lbs (55 J) transition temperature from each transition temperature curve using a set of three test specimens at each test temperature. The test temperatures shall include tests on the upper and lower shelves and a minimum of four intermediate temperatures.

S63.4 The following requirements shall be met:

$$\sqrt{v\text{Tr}40} + 2.5 \Delta v\text{Tr}40 \leq 50^\circ\text{F}$$

$$\sqrt{v\text{Tr}55} + 2.5 \Delta v\text{Tr}55 \leq 10^\circ\text{C}$$

where:

$\sqrt{v\text{Tr}40}$ ($\sqrt{v\text{Tr}55}$) = the 40-ft-lbs (55 J) transition temperature of the material subjected to the minimum PWHT specified by the purchaser.

ΔvTr_{40} (ΔvTr_{55}) = the shift of the 40-ft-lbs (55 J) transition temperature the of the step cooled material. (The 40-ft-lbs (55 J) transition temperature the of the step cooled material minus that of the material subjected to the minimum PWHT only).

S63.5 The 40-ft-lbs (55 J) transition temperatures for the two material conditions shall be reported. Fig. S1.1

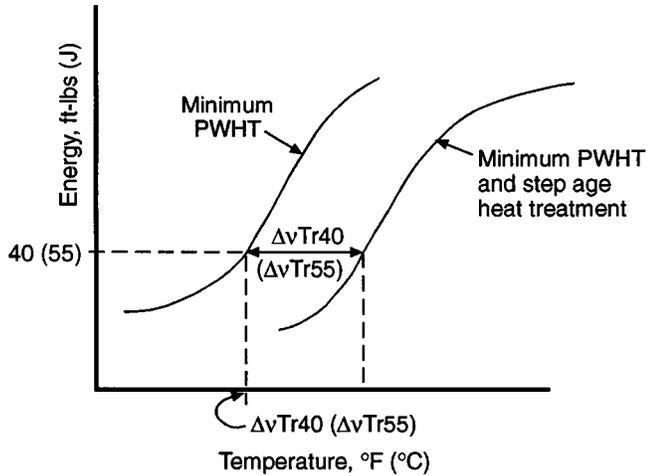


FIG. S1.1 Transition Temperature Curves Before and After Step Cool Heat Treatment

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).