



## Standard Specification for Copolymers of Vinylidene Fluoride (VDF) with Other Fluorinated Monomers<sup>1</sup>

This standard is issued under the fixed designation D 5575; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

### 1. Scope\*

1.1 This specification covers both developing property designations and specifications for thermoplastic compositions consisting of vinylidene fluoride (VDF) polymers modified with other fluoromonomers and property-enhancing additives. The other fluoromonomers include one or more of the following: hexafluoropropylene (HFP), tetrafluoroethylene (TFE), and chlorotrifluoroethylene (CTFE). The additives are those that improve its flame resistance, processing, or physical properties. However, these additives are not normally considered to be reinforcing. This specification covers thermoplastic compositions supplied in pellet or powder forms.

1.2 A designation or specification applies only to the virgin polymers prepared from vinylidene fluoride (>50 weight %) with one or more of the following comonomers: hexafluoropropylene, tetrafluoroethylene, and chlorotrifluoroethylene. These polymers may contain additives to enhance certain properties.

1.3 This system constitutes a line callout as a means of designating and specifying properties of VDF-based copolymers. At least four of the designated properties are used to define a polymer's specification. Specification criteria from international documents can be used if their criteria match designation properties currently used by this specification.<sup>2</sup> This specification is not intended for the selection of materials.

1.4 The manufacturer of the virgin resin shall establish the designation of a resin based on the property value criteria in this specification.

1.5 The minimum specification properties are established by this specification. Additional specification properties, based on

the designation properties cited, can be established by the resin supplier and customer.

1.6 The values stated in SI units are to be regarded as standard and the practices of IEEE/ASTM SI-10 incorporated herein, except where common usage or test method specify common units acceptable within IEEE/ASTM SI-10.

1.7 The property tests are intended to provide information for specifications of modified VDF-copolymer compositions. It is not the purpose of this specification to provide engineering data for design purposes.

NOTE 1—Although the values listed in Table 1, Table 2, Table 3, Table 4, Table 5 are necessary to include the range of properties available in existing materials, they should not be interpreted as implying that every possible combination of the properties exists or can be obtained. It is possible for a user or designer, using Tables 1-5, to call out property relationships that are physically impossible to occur in a copolymer made using current technology.

NOTE 2—Many of these polymers exhibit polymorphism.<sup>3</sup> The type and extent of crystalline structure can vary with the thermomechanical history of the sample. Specimens prepared by different techniques could have properties that may vary.

1.8 Test methods used in this specification may involve the incidental production of hazardous materials. Modified VDF polymer fluoroplastics melt between 90 and 182°C (194 and 359°F) and are thermally stable up to about 350°C (662°F), or somewhat higher, depending on the composition. **Warning**—Evolution of corrosive, colorless, and toxic hydrogen fluoride can occur under certain conditions.

1.9 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* See Warning in 1.8 and Section 10 for specific hazards statements.

NOTE 3—Most of the technical content of this specification is included as part of ISO 12086/1, 2. These standards have been approved for publication and are in the final editing process. Many designations from the ISO standards will be similar to those from this ASTM specification.

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials.

Current edition approved November 1, 2003. Published December 2003. Originally approved in 1994. Last previous edition approved in 1999 as D 5575 - 99.

This standard is needed to cover commercial products outside the scope of Specification D 3222.

<sup>2</sup> Fluoropolymer property specification data from international standards can include properties intentionally excluded from this specification (for example, composition). The only property criteria from other documents that can be used are those having similar properties allowed under the designation system.

<sup>3</sup> Lovinger, A. J., "Poly(vinylidene fluoride)," *Developments in Crystalline Polymers*, Vol 1, Chapter 5, D.C. Bassett, Ed., Applied Science, London, 1982.

\*A Summary of Changes section appears at the end of this standard.

**2. Referenced Documents**

2.1 *ASTM Standards:*<sup>4</sup>

NOTE 4—For ASTM and ISO documents, the equivalent or a comparable method is listed after each citation in parentheses.

- D 150 Test Methods for A-C Loss Characteristics and Permittivity (Dielectric Constant) of Solid Electrical Insulating Materials (IEC 250)
- D 257 Test Methods for D-C Resistance or Conductance of Insulating Materials (IEC 93)
- D 618 Practice for Conditioning Plastics for Testing (ISO 291)
- D 638 Test Method for Tensile Properties of Plastics (ISO 527/1,2,3)
- D 792 Test Methods for Specific Gravity (Relative Density) and Density of Plastics by Displacement (ISO 1183)
- D 883 Terminology Relating to Plastics (ISO 472, ISO 1043/1, -2)
- D 1238 Test Method for Flow Rates of Thermoplastics by Extrusion Plastometer (ISO 1133)
- D 1600 Terminology for Abbreviated Terms Relating to Plastics
- D 1999 Guide for the Selection of Specimens and Test Parameters for International Commerce
- D 2863 Test Method for Measuring the Minimum Oxygen Concentration to Support Candle-like Combustion of Plastics (Oxygen Index) (ISO 4583)
- D 3222 Specification for Unmodified Poly(Vinylidene Fluoride) (PVDF) Molding, Extrusion, and Coating Materials
- D 3418 Test Method for Transition Temperatures of Polymers by Thermal Analysis
- D 3835 Test Method for Determination of Properties of Polymeric Materials by Means of a Capillary Rheometer
- D 3892 Practice for Packaging/Packing of Plastics
- D 4591 Test Method for Determining Temperatures and Heats of Transitions of Fluoropolymers by Differential Scanning Calorimetry
- D 4703 Practice for Compression Molding Thermoplastic Materials into Test Specimens, Plaques, or Sheets
- D 5740 Guide for Writing Material Standards in the D 4000 Format

<sup>4</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

**TABLE 1 Codes for the Information on Fluoropolymers Used in Data Block 1**

Code	Meaning
A	modified
B	block copolymer
H	homopolymer
K	copolymer
L	graft polymer
R	random copolymer
Z	other

**TABLE 2 Code-Letters Used in Data Block 2 (Intended Application or Method of Processing, Essential Properties, Additives, or Other Information)**

Code	Position 1	Code	Positions 2 to 8
A	adhesives	C	colored
B	blow molding	D	powder
B1	extrusion blow molding	D2	free-flowing
B2	injection blow molding	D3	not free-flowing
C	calendaring	E	expandable
E	extrusion	F	special burning characteristics
G	general use	F1	nonflammable
H	coating	F2	flame retarded
H1	powder coating	F4	reduced smoke emission
H2	dip coating	G	granules
K	cable and wire coating	G1	pellets
L	monofilament extrusion	L	light and weather stabilized
M	molding (injection/transfer)	M	nucleated
Q	compression molding	N	natural (no color added)
R	rotational molding	N1	suitable for food contact
V	thermoforming	N2	high purity
X	no indication	P	impact modified
Y	textile yarns, spinning	R	mold release agent
Z	other	S	lubricated
		T	transparent
		T1	translucent
		T2	opaque
		W1	improved chemical resistance
		Y	increased electrical conductivity
		Z	antistatic

**TABLE 3 Designatory and Specification Properties for Data Block 3**

Position Number <sup>A</sup>	Property
1	<sup>B</sup> melt temperature
2	<sup>B</sup> melt flow rate/melt viscosity
3	<sup>B</sup> tensile strength and modulus
4	tensile elongation
5	<sup>B</sup> density
6	electrical
7	flammability by oxygen index (OI)
8	specimen preparation method and type

<sup>A</sup> Property test information for Positions 1 to 7 are given in Section 8.

<sup>B</sup> Positions 1, 2, 3, and 5 are mandated as the minimum specification properties.

IEEE/ASTM S1–10 Standard for Use of the International System of Units (SI)

2.2 *IEC and ISO Standards:*<sup>5</sup>

- IEC 93 Recommended Methods of Test for Volume and Surface Resistivities of Electrical Insulating Materials
- IEC 250 Recommended Methods for the Determination of the Permittivity and Dielectric Dissipation Factor of Electrical Insulating Materials at Power, Audio and Radio Frequencies Including Metre Wavelengths
- ISO 291 Plastics—Standard Atmospheres for Conditioning and Testing (Practice D 618)
- ISO 293 Plastics—Compression Molding Test Specimens of Thermoplastic Materials (Practice 4703)
- ISO 472 Plastics—Vocabulary (Terminology D 883)
- ISO 527/1,2,3 Plastics—Determination of Tensile Properties (Test Method D 638)

<sup>5</sup> Available from American National Standards Institute (ANSI), 25 W. 43rd St., 4th Floor, New York, NY 10036.

**TABLE 4 Date Block 3**

Position 1		Position 2				Position 3		Position 4				
Code	Tm, °C	Melt Viscosity/Melt-Flow Rate				Tensile Strength		Tensile Elongation				
		Code	Melt-Flow Rate, g/10 min	Load, kg	Melt Viscosity, Pa/s <sup>A</sup>	Temperature, °C	Code	Yield Strength, MPa	Modulus, MPa	Code	Yield, %	Break, %
a	<20	a	<0.1		<250		a	<15	<500	a	<5	<50
b	20 to <30	b	0.1 to< 0.2	0.325	>250		b	15 to <20	500 to< 800	b	5 to <10	50 to <100
c	30 to <40	c	0.2 to <0.5	1.20	>500		c	20 to <25	800 to< 1200	c	10 to <15	100 to <150
d	40 to< 50	d	0.5 to <1.0	2.16	>100		d	25 to< 30	1200 to <1600	d	15 to <20	150 to <200
e	50 to <60	e	1.0 to <2.0	3.80	>1500		e	30 to< 35	1600 to <2000	e	20 to <25	200 to <250
f	60 to <70	f	2.0 to <5.0	5.00	>2000	230	f	35 to< 40	2000 to< 3000	f	25 to <30	250 to <300
g	70 to <80	g	5.0 to <10	10.00	>2500	125	g	40 to< 45	3000 to< 4000	g	>30	300 to <350
h	80 to< 90	h	10 to < 20	12.50	>3000		h	45 to< 50	4000 to <6000	h		350 to <400
i	90 to < 100	i	20 to <50	21.60	>3500		i	50 to< 55	>6000	i		400 to <500
j	100 to< 110	j	Ls50	31.60			j	55 to< 60		j		500 to <600
k	110 to< 120	k					k	60 to <65		k		600 to< 800
l	120 to< 130	l					l	Ls65		l		>800
m	130 to <140	m					m			m		
n	140 to <150	n					n			n		
o	150 to <160	o					o			o		
p	160 to <170	p					p			p		
q	170 to <180	q					q			q		
r	180 to <190	r					r			r		
s	190 to <200	s					s			s		
t	200 to <210	t					t			t		
u		u					u			u		
v		v					v			v		
w		w					w			w		
x		x					x			x		
y		y					y			y		
z	not specified	z	not specified				z	not specified		z	not specified	

<sup>A</sup>1 Pa/s = 10 P.

Position 5		Position 6			Position 7		Position 8		
Code	Specific Gravity, g/cm <sup>3</sup>	Code	Electrical a-c Dielectric Constant	Loss	d-c Electric Volume	Code	Limiting Oxygen Index	Code	Specimen Type
a	<1.6	a			>10E3	a	<40	a	D 638 Type I
b	1.6 to <1.7	b			10E3 to 10E12	b	40 to <50	b	D 638 Type II
c	1.7 to< 1.8	c			>10E12	c	50 to <60	c	D 638 Type III
d	1.8 to <1.9	d				d	60 to< 70	d	D 638 Type IV
e	1.9 to< 2.0	e				e	70 to <80	e	ISO 527 Type 1A
f	2.0 to <2.1	f				f	80 to <90	f	ISO 527 Type 1B
g	2.1 to< 2.2	g		<0.0012		g	>90	g	ISO 527 Type 6A
h	2.2 to< 2.3	h	<3.0	<0.0014		h		h	ISO 527 Type 7A
i	2.3 to <2.4	i	3.0 to< 3.1	<0.0016		i		i	ISO 12086/1 Fig. 1
j	2.4 to <2.5	j	3.1 to <3.2	<0.0018		j		j	D 638M Type MI
k		k	3.2 to <3.5	<0.0020		k		k	D 638M Type MII
l		l	3.5 to <4.0	<0.0022		l		l	D 638M Type MIII
m		m	4.0 to< 4.5	<0.0024		m		m	D 1999 Type 1A
n		n	4.5 to <5.0	<0.0026		n		n	D 1999 Type 1B
o		o	5.0 to< 5.5	<0.0028		o		o	D 1999 Type II
p		p	5.5 to <6.0	<0.0030		p		p	D 1708
q		q	6.0 to <6.5	<0.0035		q		q	
r		r	6.5 to <7.0	<0.0040		r		r	
s		s	7.0 to <8.0	<0.0060		s		s	
t		t	8.0 to <9.0	<0.0080		t		t	
u		u	9.0 to <10	<0.0100		u		u	
v		v	10 to <11	<0.0300		v		v	
w		w	11 to <12	<0.1000		w		w	
x		x	12 to <14	>0.1000		x		x	
y		y	>14			y		y	
z	not specified	z	not specified		not specified	z	not specified	z	

ISO 1043/1 Plastics—Symbols—Part 1: Symbols for Basic Polymers and Their Special Characteristics (Terminology D 883)  
 ISO 1043/2 Plastics—Symbols—Part 2: Fillers and Rein-

forcing Materials (Terminology D 883)  
 ISO 1133 Plastics—Determination of the Melt Mass-Flow Rate (MFR) and the Melt Volume-Flow Rate (MVR) of Thermoplastics (Test Method D 1238)

**TABLE 5 Codes for Filler and Physical Form of Materials for Use in Data Block 4**

Code	Material	Code	Form/Structure
B	boron	B	beads, spheres, balls
C	carbon	C	chips, cuttings
CG	graphite	D	powder
E	clay	F	fiber
G	glass	G	ground
K	calcium carbonate	H	whisker
M	mineral, metal	K	knitted fabric
Ma	aluminum oxide	L	layer
Mb	bronze	M	mat (thick)
MC	calcium fluoride	N	nonwoven (fabric)
Md	molybdenum disulfide	P	paper
Me	stainless steel	S	roving
P	mica	T	scale, flake
Q	silica	V	cord
R	aramid	W	veneer
S	synthetic, organic	X	not specified
T	talcum	Y	yarn
X	not specified	Z	others
Z	none		

ISO 1183 Plastics—Methods for Determining Density and Relative Density of Non-Cellular Plastics (Test Methods D 792)

ISO 4583 Plastics—Determination of Flammability By Oxygen Index

ISO 12086/1 Fluoropolymer Dispersion and Molding and Extrusion Materials—Part 1: Designation and Specification

ISO 12086/2 Fluoropolymer Dispersion and Molding and Extrusion Materials—Part 2: Preparation of Test Specimens and Determination of Properties

### 3. Terminology

#### 3.1 Definitions:

3.1.1 *copolymer*—a polymer derived from more than one species of monomer. **ISO 472**

3.1.2 *fluoroplastic*—a plastic based on polymers made with monomers containing one or more atoms of fluorine, or copolymers of such monomers with other monomers, the fluoro-monomer(s) being in the greatest amount by mass. **ISO 12086**

3.1.3 *monomer*—a low-molecular-weight substance consisting of molecules capable of reacting with like or unlike molecules to form a polymer. **D 883**

3.1.4 *thermoplastic*—a plastic that repeatedly can be softened by heating and hardened by cooling through a temperature range characteristic of the plastic, and that in the softened state can be shaped by flow into articles by molding or extrusion. **D 883**

#### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *amorphous*—noncrystalline or devoid of regular structure.

3.2.2 *contamination*—the presence of nonpolymer particulate and debris in the polymer, excluding any property-enhancing additives.

3.2.3 *fluoropolymer*—synonymous with fluoroplastic.

3.2.4 *melt-processible*—capable of being processed by, for example, injection molding, screw extrusion, and other operations typically used with thermoplastics.

3.2.5 *polymorphism*—the ability of a material to form two or more different but stable crystalline forms.

3.2.6 *thermomechanical history*—the mechanical and thermal exposure that a material experiences before testing.

#### 3.3 Abbreviations: Abbreviations:

3.3.1 *CTFE*—chlorotrifluoroethylene (1-chloro-1,2,2-trifluoroethylene). **D 1600**

3.3.2 *DMAC*—dimethylacetamide.

3.3.3 *DSC*—differential scanning calorimetry.

3.3.4 *HFP*—hexafluoropropylene (1,1,2,3,3,3-hexafluoropropylene).

3.3.5 *MFR*—melt-flow rate.

3.3.6 *MV*—melt viscosity.

3.3.7 *PVDF*—poly(vinylidene fluoride). **D 1600**

3.3.8 *TFE*—tetrafluoroethylene (1,1,2,2-tetrafluoroethylene). **D 1600**

3.3.9 *VDF*—vinylidene fluoride (1,1-difluoroethylene).

3.3.10 *VDF/CTFE*—vinylidene fluoride/chlorotrifluoroethylene copolymer.


3.3.11 *VDF/HFP*—vinylidene fluoride/hexafluoropropene copolymer.

3.3.12 *VDF/TFE*—vinylidene fluoride/tetrafluoroethylene copolymer.

3.3.13 *VDF/TFE/HFP*—vinylidene fluoride/tetrafluoroethylene/hexafluoropropene copolymer.

### 4. Classification and Designation

4.1 The classification and designation system of the polymers is based on the following standardized pattern taken from ISO 12086/1:

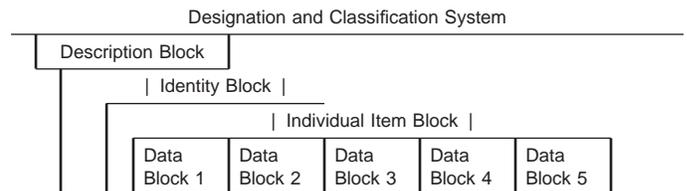

4.1.1 The designation system consists of the following:

4.1.1.1 An optional description block, reading “Thermoplastics,”

4.1.1.2 An identity block comprising the ASTM standard number, and

4.1.1.3 An individual item block.

(1) The individual item block is subdivided into five data blocks that include the information in 4.2-4.6. Data Block 5 is used when a designation is converted to a specification. See Section 7 for more details.

(2) The blocks shall be separated from each other by commas. If a data block is not used, this shall be indicated by doubling the separation sign, that is, by two commas (,).

4.2 *Data Block 1*—This data block identifies the fluoropolymer by its abbreviation from the list in 3.3 (additional terms are listed in ISO 12086/1, 2, or Terminology D 1600). The abbreviation is followed by a hyphen and a one-letter code giving more information about the polymer, using the codes from Table 1.

4.3 *Data Block 2*:

4.3.1 This block can indicate up to eight items of information coded by letters as specified in Table 2. Position 1 gives information about intended application or method of processing. Positions 2 through 8 provide up to seven items that can use codes from Table 2 to indicate the polymer's form as well as specific special characteristics.

4.3.2 If only one letter is given (for example, E), it must apply to Position 1. Whenever there is an indication of properties, etc., in Positions 2 to 8, a code in Position 1 is required. The code "X" indicates that no other letter code is appropriate. An alphabetical order is recommended if more than one code letter is used in Positions 2 to 8.

NOTE 5—Selecting the application or processing method for Position 1 of Data Block 2 should be done carefully. Many polymers are capable of more than one application or method of processing (for example, extrusion (E) and molding (M) resins should be coded "general use" (G)). Coding for special methods of processing should be reserved for polymers only designed for the application.

#### 4.4 Data Block 3:

4.4.1 Data Block 3 is used as the designation or general description of the fluoropolymer's properties. The property values are presented by code letters in seven of eight positions within Data Block 3. Each position represents a specific property listed in Table 3. Table 4 lists the code letters corresponding to the various property values. The values are determined by the methods cited in Section 8. At least four of the seven properties are specification properties. Position 8 cites specimen preparation methods when the designation is converted to a specification.

4.4.1.1 Each position may contain one or more code letters, depending on the property cited. The positions are separated by a hyphen (-). Use of an asterisk (\*) or question mark (?) before the code letters denotes that property as a specification property.

4.4.1.2 The resin manufacturer shall assign the codes in Data Block 3, based on test results from Table 4. If test values lie on, or on either side of, a cell limit because of manufacturing tolerances, the resin manufacturer shall state which cell will designate.

NOTE 6—Other properties could be used as designation and specification properties for these polymers. Most are similar to the ones used and would only duplicate measuring the same property. Other properties either do not have standard test methods or are outside of the property focus of the document scope (for example, comonomer ratios).

4.4.2 *Melting Endotherm Peak Temperature (Position 1)*—Melting endotherm peak temperature shall be determined in accordance with the principles of Test Methods D 3418 and D 4591. Semicrystalline polymers shall use melting endotherm peak temperature as a designatory property. Cell codes and ranges are given in Table 4.

4.4.3 *Melt-Flow Rate or Melt Viscosity (Position 2)*—Melt viscosity (MV) shall be determined using Test Method D 3835. Melt-flow rate (MFR) shall be determined in accordance with Test Method D 1238 or ISO 1133, using test conditions selected from Table 4. The melt viscosity or the melt-flow rate is indicated in Data Block 3 by the cell code and ranges in accordance with Table 4, followed by the codes for temperature

and load for MFR and shear rate for MV also included in Table 4. Order for Position 2 is as follows:

Position 2 Order

1st = MFR  
2nd = MFR load  
3rd = MV  
4th = Temperature

4.4.4 *Tensile Strength Properties (Positions 3 and 4)*—Tensile-strength properties shall be determined in accordance with the principles of Test Method D 638 or ISO 527 modified by details given in 8.9 or ISO 12086/2. Table 4 provides the codes to use for each range of tensile strength and modulus, and percentage elongation at yield and break. Order for Positions 3 and 4 are as follows:

Position 3 Order

1st = tensile yield  
2nd = tensile break  
3rd = tensile modulus

Position 4 Order

1st = tensile-yield elongation  
2nd = tensile-break elongation

4.4.5 *Density (Relative Density, Specific Gravity) (Position 5)*—Density shall be determined in accordance with the principles of Test Methods D 150 or ISO 12086/2. The cell codes are listed in Table 4.

4.4.6 *Electrical Properties (Position 6)*—Electrical properties for d-c and a-c currents shall be determined by Test Methods D 150, D 257, or their ISO equivalents. The cell codes are listed in Table 4. Order for Position 6 is as follows:

Position 6 Order

Position 1 = resistivity  
Position 2 = frequency (listed as the exponent of the power of ten)  
Position 3 = dielectric constant  
Position 4 = dissipation factor

Positions 5 to 7, 8 to 10, 11 to 13, ... (repeat of 2 to 4 for each frequency cited)

4.4.7 *Flammability Properties (Position 7)*—Flammability properties shall be determined by oxygen index (OI) values using Test Method D 2863 or ISO 4583. The cell codes are listed in Table 4.

4.4.8 *Specimen Preparation and Type (Position 8)*—This position is used only when a designation is converted to a specification to describe the molded specimen type and its preparation. Section 9 provides information on preparing compression-molded specimens. Cell codes are listed in Table 2 and Table 4. Order for Position 8 is as follows:

Position 8 Order

1st = molding method (from Table 2, Position 1)  
2nd = tensile bar type and method (Table 4)

NOTE 7—Using specimen preparation method and type cited in Position 8 should allow the supplier and customer to monitor polymer properties while minimizing the effects of specimen preparation.

4.5 *Data Block 4*—Data Block 4 is used to site the type (Position 1) and form (Position 2) of fillers or other materials added to the fluoropolymer. Letter codes listed in Table 5 are used to indicate the type and form used (supplemental codes can be found in ISO 1043/2). The nominal content, by weight percent, is noted by arabic numerals after Position 2 to the nearest 1%. Additive contents below 2% need not be specified. For designation clarity, a hyphen (-) may be used to

separate material type codes. When a material is present in more than one form, a plus sign (+) may be used to separate the form codes.

#### 4.6 Data Block 5:

4.6.1 Data Block 5 is used to denote changes in the values of a property when the designation is converted to specification. The type of changes would be the following:

4.6.1.1 To cite the alternate property value range when a (?) is used in Data Block 3. Where more than one (?) is cited, the value ranges shall be listed in order of their occurrence.

NOTE 8—It is recommended that any ranges smaller than designated by Table 4 codes be greater than the precision and bias for the test method that measures the property.

4.6.1.2 To cite a current ASTM or other standard specification for the polymer (see 4.7 for restrictions).

4.6.1.3 A combination of 4.6.1.1 and 4.6.1.2.

#### 4.7 Designation and Specification Restrictions:

4.7.1 Data Block 5 of the specification call-out cannot cite properties beyond the scope of this specification. In other words, specification criteria or properties from other specifications that conflict with this specification's scope are not allowed.

NOTE 9—Some specifications cite properties that are either not detectable or use test methods not available to most customers. Therefore, specification property values or results shall be able to be determined by a user without *a priori* knowledge of the polymer's manufacturer, polymerization process, or any other unique finishing process.

4.7.2 A commercial grade of polymer should not have multiple designations for Data Block 2. The application choice should be broad enough for a variety of the applications to which it can be applied.

4.7.3 An alternate specification property range in Data Block 5 shall not be greater than the original designation-code range from Table 4 and either the preceding or following code. In other words, if a property code is normally "D," the new range could encompass values or ranges from Code "C and D" or "D and E." The new values cannot encompass a range cited by Codes "C to E" or greater.

4.7.4 At no time shall a designation for a commercial grade have more than one designation for Data Blocks 1, 2, 3, and 4. If the code values need to be modified from those cited in Table 4, the changes shall be done by use of a (?) and listed in Data Block 5.

## 5. General Requirements

5.1 The material should be ordered by the manufacturer's trade name and corresponding copolymer line callout and the necessary suffix properties to define the material.

5.2 The material shall be of uniform composition and free of foreign matter to a contamination level agreed upon between the purchaser and the seller.

5.3 Adequate statistical sampling shall be considered an acceptable alternative.

## 6. Example of a Designation

6.1 The following example is for VDF/HFP fluoropolymer material for general-purpose molding with a designation of:

## 7. Specifications for Fluoropolymers

### 7.1 Designation Conversion to Specification:

7.1.1 A designation is converted into a specification by preceding 4 or more property codes in Data Block 3 with an asterisk and adding the specimen preparation codes in Data Block 3, Position 8, from Table 2 and Table 4.

7.1.1.1 Four property codes, cited by Data Block 3 positions, that must be included in a specification are as follows:

Data Block 3 Position	Property
1	melt temperature
2	melt-flow rate or melt viscosity, or both
3	tensile strength and modulus
5	density

### 7.1.2 Specification Using Designation Ranges:

#### 7.1.2.1 Example (see Appendix X2):

A VDF/CTFE copolymer, a general-use grade, sold as granules, and having the following (specification properties are in boldface type):

- (1) **A melting point of 165°C,**
- (2) **An MV of 1500 Pa/s when tested at 230°C at 100 s<sup>-1</sup>,**
- (3) **A tensile strength yield of 28 MPa; break strength not cited; modulus of 800 MPa,**
- (4) Elongation yield of 9 %; break of 450 %,
- (5) **Density between 1.78,**
- (6) Electricals of:  
Volume resistivity greater than 2.3 E<sup>14</sup>Ω,  
Dielectric constant at 1 kHz at 10.1; at 10 kHz at 9.3; 1 MHz at 7.3,  
Dissipation factor at 1 kHz at 0.021; at 10 kHz at 0.031; at 1 MHz at 0.15,
- (7) OI at 53, and
- (8) Tested using compression-molded specimens using ISO 527 Type-6A tensile bars.

Designation and specification where each designatory property is desired as part of the specification with the specification limits equal to the cell limits is as follows:

**ASTM D5XXX, VDF/CTFE-K,  
GG,\*P-\*ZZE-\*DZC-BI-\*C-C3VU4UVSXY-C-\*QG, Z,,**

### 7.1.3 Specification Using Alternate Property Ranges:

7.1.3.1 When the values given in the cell tables are not satisfactory for specification purposes, indicate this situation by inserting a question mark in Data Block 3 at the beginning of the destination cell code and the specification range given in Data Block 5.

#### 7.1.3.2 Example (see Appendix X3):

A modified VDF/HFP copolymer that is processed by extrusion, with reduced-burning characteristics and smoke emissions. The resin is marketed as pellets, contains a lubricant, and is opaque. The additive level is less than 2 %. Its properties are as follows (specification properties are in boldface type):

- (1) **A melting point of 143°C,**
- (2) **An MV between 1300 and 1700 Pa/s when tested at 230°C at 100 s<sup>-1</sup>,**
- (3) **A tensile strength yield of 24 MPa; break not cited; modulus of 1000 MPa,**
- (4) Elongation yield of 12 %; break of 350 %,
- (5) **Density of 1.79,**
- (6) Electricals not cited.
- (7) OI greater than 80,
- (8) **Tensile specimens are compression-molded and Test Method D 638, Type I, and**
- (9) The melt-viscosity range encompasses two ranges.

Designation and specification is as follows:

**ASTM D5XXX, VDF/HFP-A, EFF4G1ST2, \*N-\*ZZ?E-\*CZC-CH-  
\*C-ZZ-\*C-QA, Z, ?1300-1700,**

## 8. Property Determination Methods

8.1 The following subsections of Section 8 cite test methods used to determine polymer-property values of code levels from

**Thermoplastics, ASTM D 5XXX, VDF/HFP-R, GDO2MM2, M-MIG-CDB-DH-C-C3YY4UV6SW-B-, Z,,  
Detailed Explanation of the Designation**

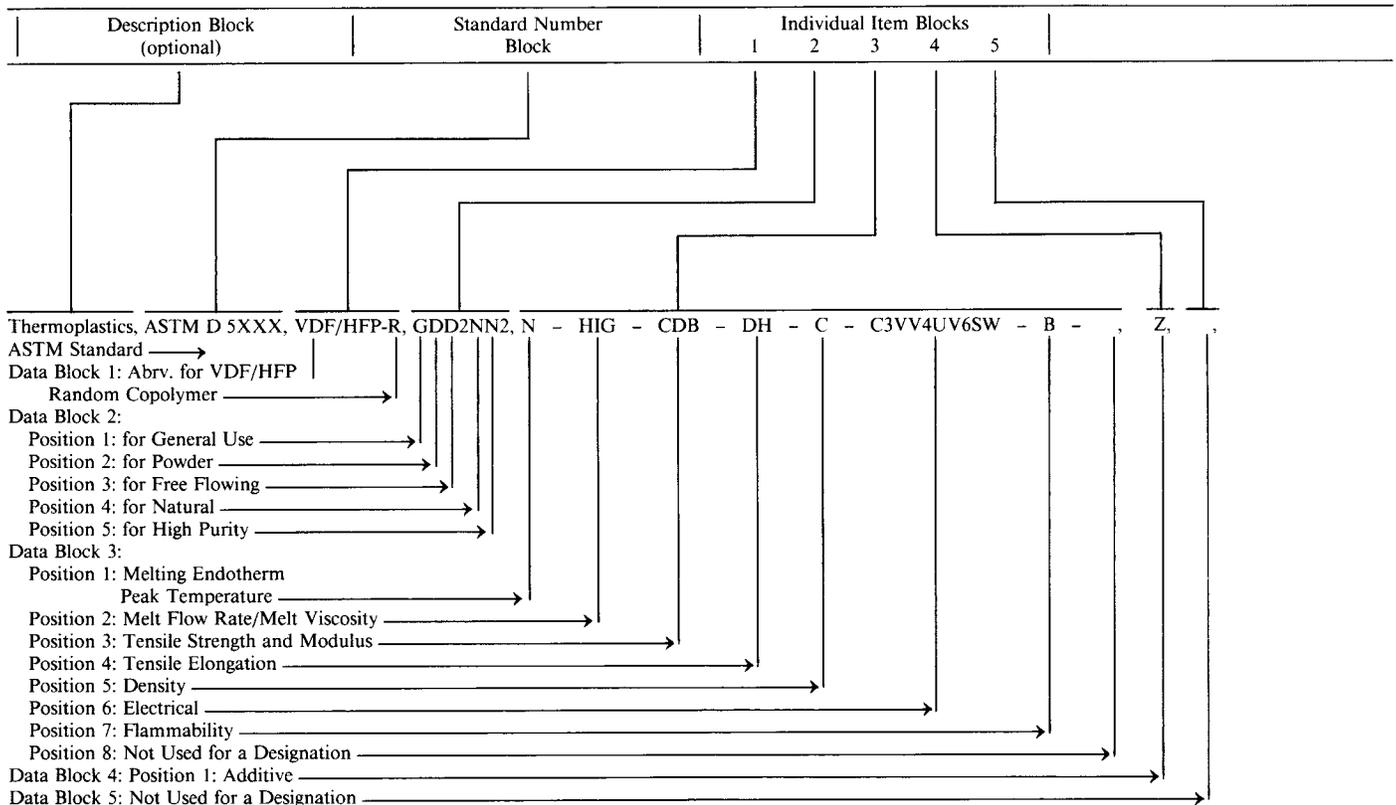


Table 4 for Data Block 3 of a designation or specification line call-out. When a test value normally varies between two code levels, the manufacturer shall designate the code levels. Several properties are tested using molded specimens. Section 9 presents a procedure to prepare compression-molded specimens. Specimens may be injection molded. Due to stress effects on many properties, compression molding of specimens is preferred.

**8.2 Melt Temperature**—The copolymers peak melting points are determined using Test Methods D 4591 or D 3418 using DSC. The sample size is  $10 \pm 1$  mg. The sample is heated, cooled, and reheated over a temperature range from  $-20$  to  $220^\circ\text{C}$  at a rate of  $10^\circ\text{C}/\text{min}$ . The sample is held at the upper temperature for 5 min before cooling. The second heating endotherm peak value shall be used. Occasionally multiple peaks are observed. The temperature of the tallest peak shall be reported as the melting point.

**8.3 Melt-Flow Rate and Melt Viscosity:**

**8.3.1 Melt-Flow Rate**—The melt-flow rate (MFR) shall be determined using Test Method D 1238 or ISO 1133 at  $230^\circ\text{C}$  for all resins whose melt point is above  $100^\circ\text{C}$ . Lower melt-point resins shall use a test temperature of  $125^\circ\text{C}$ .

**8.3.2 Melt Viscosity**—The melt-viscosity value at  $100 \text{ s}^{-1}$  at  $230^\circ\text{C}$  shall be determined from a shear-rate viscosity curve of four or more points ranging from less than  $50 \text{ s}^{-1}$  to greater than  $500 \text{ s}^{-1}$  shear rate. For polymers with melt points greater than  $110^\circ\text{C}$ , a test temperature of  $125^\circ\text{C}$  shall be used. The rheometer die shall have an entrance angle of  $60^\circ$  (cone angle of  $120^\circ$ ) and a capillary L/D ratio of 15. The sample may be

pellets or pieces cut from molded or extruded forms. Strips about 6 mm wide by 76 mm long may be handled conveniently.

**8.4 Tensile Properties:**

**8.4.1 Tensile properties**, except modulus, shall be tested in accordance with Test Method D 638 or ISO 527 at a strain rate of  $25 \text{ mm}/\text{mm}/\text{min}$  ( $1 \text{ in.}/\text{in.}/\text{min}$ ). The strain rate is the ratio of the cross-head speed divided by the specimen-gage length. Tensile modulus shall use a strain rate of 2 % of the previous strain rate ( $0.5 \text{ mm}/\text{mm}/\text{min}$  or  $0.013 \text{ in.}/\text{in.}/\text{min}$ ). The property values of the resin shall be determined as the average of results from at least five specimens.

NOTE 10—When test equipment cannot test at a 2 % strain rate for the smaller test bars, a higher strain rate (less than 5 %) may be used.

**8.4.2 Elongation** is determined as the percent change in specimen length during the test, based on the original gage length. This value can be determined by either cross-head separation or by use of an extensometer.

**8.4.3** The type of bar may vary within the types cited in Table 4. Preferably compression-molded specimens should be used (see Section 9), but injection-molded specimens or specimens cut from extruded sheet may be used. Dies or mold cavity-dimensions to cut or mold specimens shall match the required specimen dimensions and tolerances.

NOTE 11—The different test bar shapes have three basic types with minor variations. Unfortunately, these differences can affect the test values. For this reason Position 8 in Data Block 3 is used when a designation is changed to a specification. Examples of the three basic shapes are as follows:

Large: D 638 Type I or ISO 527 Type 1A (50-mm gage)  
 Medium: ISO 527 Type 6A or Test Method D 638 Type IV (25-mm gage)  
 Small: ISO 12086/2 Figure 1 (22-mm gage)

NOTE 12—Due to the molded-in stress and orientation, injection-molded or samples cut from extruded sheet may break outside of the gage region and show low (and possibly variable) elongation compared to compression-molded specimens. Samples may show extreme strain hardening with some specimen types. This effect can result in variable break properties.

8.5 *Specific Gravity*—The specific gravity shall be determined by Test Methods D 792 using two test specimens cut from a compression-molded sample. With this test, care must be exercised to eliminate all air bubbles that may be attached to the specimens upon immersion. Dipping the specimens in a very dilute solution (less than 0.1 weight %) of a surfactant will minimize the problem.

#### 8.6 *Electrical Properties:*

##### 8.6.1 *Specimen Type:*

8.6.1.1 The electrical tests are determined on three specimens, each 100 mm in diameter and 0.12 to 0.25 mm (0.005 to 0.010 in.) in accordance with IEC 250, Test Methods D 150, and Test Method D 257.

8.6.2 *Volume Resistivity*—The d-c volume resistivity shall be measured using Test Method D 257 or IEC 93. Cell codes and ranges are listed in Table 4.

8.6.3 *Dielectric Constant and Dissipation Factor*—The a-c dielectric constant and dissipation factor shall be determined by Test Methods D 150. The testing shall be done at the following frequencies: 1 kHz, 10 kHz, 0.1 MHz, and 1 MHz. Codes for dielectric constant and dissipation factor are listed in Table 4. The code used for each frequency shall be the first integer of the base 10 log of the frequency (for example, 1 kHz = 3; 1 MHz = 6).

8.7 *Limiting Oxygen Index (LOI)*—Limiting oxygen index is determined by Test Method D 2863. The flame-enhanced formulations may extinguish before the 3-min burn time that defines the LOI value at oxygen levels above 95 %. In this case, the LOI value is the highest oxygen level used.

NOTE 13—If a column with a restricted opening is used, the top of the specimen should be positioned at least 40 mm below the opening.

## 9. Preparation of Compression-Molded Specimens

### 9.1 *Molding Conditions:*

9.1.1 Compression-molded sheets can be prepared by Practice D 4703 using a “picture frame” mold. The resin form can be pellets, molded preforms, or powder. The temperature should be 230°C for all resins with a melt point greater than 110°C. For resins with a lower melt point, use 125°C. Where possible, cooling should be done under pressure either by slow cooling (Method A or B) or quench cooling (Method C). It is recommended that an inert mold-release sheet (less than 0.007 in.) of aluminum, polyimide, or PTFE be used.

9.1.2 The ram forces may be used based on the size of the specimen area. The force adjustment should exert an approximate pressure of 0.25 kN/cm<sup>2</sup> (360 lb/in.<sup>2</sup>) of specimen area.

NOTE 14—Powder samples tend to entrap air and cause bubbles in the specimen when compression molded. Such specimens are not suitable for

any test in this specification. Use molded preforms or densified powder to eliminate bubble formation.

9.2 *Specimen Preparation*—Test specimens can be molded directly by a shaped mold or cut from a molded sheet. The dimensions of shaped molds can vary due to mold-shrinkage effects. Cutting specimens from a molded sheet is preferred.

NOTE 15—The specimen edge may affect performance in mechanical tests. Die-cutting is the preferred method of preparing specimens. The cutting edges should be sharp and free from any nicks or other defects that could cause a dimensional defect in the specimen.

## 10. Handling

10.1 As with any synthetic resin, it is advisable to wear a dust mask when handling large quantities of powder grades to prevent ingestion.

10.2 The Material Safety Data Sheets of the fluoropolymer grade should be reviewed to determine if there is any special-handling information.

## 11. Inspection and Certification

11.1 Inspection and certification of the material supplied under this classification system or specification shall be for conformance to the requirements specified herein.

11.2 Lot-acceptance inspection shall be the basis on which acceptance or rejection of the lot is made. The lot-acceptance inspection shall consist of

11.2.1 Those tests that ensure process control during manufacture as well as those necessary to ensure certifiability in accordance with 11.5.

11.2.2 The four minimum lot-acceptance tests are melt temperature, melt flow rate/melt viscosity, tensile strength and modulus, and density as listed in Table 3.

11.3 A lot is defined as one production run or a uniform blend of two or more production runs.

11.4 Periodic check inspection shall consist of the tests specified for all requirements of the material under this specification. Inspection frequency shall be adequate to ensure that the material is certifiable in accordance with 11.5.

11.5 Certification shall be that the material was manufactured by a process in statistical control, tested, and inspected in accordance with this specification and that average values meet the requirements at a confidence level of 95 %.

11.6 A report of the test results shall be furnished when requested. The report shall consist of the results of the lot-acceptance inspection for the shipment and the results of the most recent periodic-check inspection.

## 12. Packaging, Packing, and Marking

12.1 Unless otherwise agreed upon between the purchaser and the seller, the packing, packaging, and marking provisions of Practice D 3892 shall apply to this specification.

## 13. Precision and Bias

13.1 The precision and bias statements of the ASTM test methods referenced herein apply to the specific tests required in this specification.

## 14. Keywords

14.1 fluoropolymers; line callout; plastics; poly(vinylidene fluoride) copolymers

**APPENDIXES**

**(Nonmandatory Information)**

**X1. FORM TO DEVELOP DESIGNATION AND SPECIFICATION CODE**

Test/Parameter	Actual Lot Data	Specification Y N	Data Block	Data Table	Code Used	Other Comments
Polymer abbreviation	_____	Y-mandated	No. 1-2	Section 3.3	_____	
Polymer type	_____	Y-mandated	No. 1-2	Table 1	_____	
Application/process and special characteristics	_____	Y-mandated	No. 2-1	Table 2-1	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
	_____	Y N (optional)	No. 2-2	Table 2-2	_____	
Properties	_____				_____	
Melt temperature	_____ °C	Y-mandated	No. 3-1	Table 4-1	* _____	Test Method D 4591
MFR	_____ g/10 min	Y-mandated	DB 3-2a	Table 4.1	* _____	Test Method D 1238
Load	_____ kg	[or use]	DB 3-2b	Table 4.2	* _____	Test Method D 1238
Melt viscosity	_____ Pa/s	Y-mandated	DB 3-2c	Table 4.3	* _____	Test Method D 3835
Temperature	_____ °C	Y-mandated	DB 3-2d	Table 4.4	* _____	
Tensile strength:					_____	
Yield	_____ MPa	Y-mandated	DB 3-3a	Table 4.3a	* _____	Test Method D 638/ISO 527
Break	_____ MPa	Y N (optional)	DB 3-3a	Table 4.3b	_____	Test Method D 638/ISO 527
Modulus	_____ MPa	Y-mandated	DB 3-3b	Table 4.3c	* _____	Test Method D 638/ISO 527
Tensile elongation:					_____	
Yield	_____ MPa	Y N (optional)	DB 3-4a	Table 4.4a	_____	Test Method D 638/ISO 527
Break	_____ MPa	Y N (optional)	DB 3-4b	Table 4.4	_____	Test Method D 638/ISO 527
Density	_____ g/cm <sup>3</sup>	Y-mandated	DB 3-5	Table 4.5	* _____	Test Method D 1505
Electricals:						
d-c volume resistivity	_____ Ω	Y N (optional)	DB 3-6	Table 4.6c	_____	Test Methods D 257
Frequency No. 1	_____ Hz	Y N (optional)	DB 3-6	exponent	_____	
Dielectric constant	_____	Y N (optional)	DB 3-6	Table 4.6a	_____	Test Methods D 150/IEC 250
Loss	_____	Y N (optional)	DB 3-6	Table 4.6	_____	Test Methods D 150/IEC 250
Frequency No. 2	_____ Hz	Y N (optional)	DB 3-6	exponent	_____	
Dielectric constant	_____	Y N (optional)	DB 3-6	Table 4.6a	_____	Test Methods D 150/IEC 250
Loss	_____	Y N (optional)	DB 3-6	Table 4.6b	_____	Test Methods D 150/IEC 250
Frequency No. 3	_____ Hz	Y N (optional)	DB 3-6	exponent	_____	
Dielectric constant	_____	Y N (optional)	DB 3-6	Table 4.6a	_____	Test Methods D 150/IEC 250
Loss	_____	Y N (optional)	DB 3-6	Table 4.6b	_____	Test Methods D 150/IEC 250
Frequency No. 4	_____ Hz	Y N (optional)	DB 3-6	exponent	_____	
Dielectric constant	_____	Y N (optional)	DB 3-6	Table 4.6a	_____	Test Methods D 150/IEC 250
Loss	_____	Y N (optional)	DB 3-6	Table 4.6b	_____	Test Methods D 150/IEC 250
Flammability (OI)	_____	Y N (optional)	DB 3-7	Table 4.7	_____	Test Method D 2863/ISO 4583
Molding method	_____	Y as specified	DB 3-8	Table 2-1	_____	
Specimen type (above 2 %)	_____	Y as specified	DB 3-8	Table 4.8	_____	
Additives type	_____	Y N (optional)	DB 4-1	Table 5.1	_____	
Form	_____	Y N (optional)	DB 4-2	Table 5.2	_____	
Form	_____	Y N (optional)	DB 4-2	Table 5.2	_____	
Alternate:						
Property range No. 1	_____	Y if used	_____	_____	_____	_____
Property range No. 2	_____	Y if used	_____	_____	_____	_____
Method specification	_____	Y If used	_____	_____	_____	_____
Designation code: ASTM	_____					
D 5XXX	_____					

**X2. DEVELOPMENT OF DESIGNATION FOR 7.1.2.1**

Test/Parameter	Actual Lot Data		Specification Y N	Data Block	Data Table	Code Used	Other Comments
Polymer abbreviation	VDF/CTFE		Y-mandated	No. 1-2	Section 3.3	VDF/CTFE	
Polymer type	copolymer		Y-mandated	No. 1-2	Table 1	K	
Application/process and	general		Y-mandated	No. 2-1	Table 2-1	Gn	
special characteristics	granules		Y N (optional)	No. 2-2	Table 2-2	G	
	natural		Y N (optional)	No. 2-2	Table 2-2	N	
			Y N (optional)	No. 2-2	Table 2-2		
			Y N (optional)	No. 2-2	Table 2-2		
			Y N (optional)	No. 2-2	Table 2-2		
			Y N (optional)	No. 2-2	Table 2-2		
			Y N (optional)	No. 2-2	Table 2-2		
Properties							
Melt temperature	168	°C	Y-mandated	No. 3-1	Table 4-1	*P	Test Method D 4591
MFR	...	g/10 min	Y-mandated	DB 3-2a	Table 4.1	Z	Test Method D 1238
Load	...	kg	[or use]	DB 3-2b	Table 4.2	Z	Test Method D 1238
Melt Viscosity	1500	Pa/s	Y-mandated	DB 3-2c	Table 4.3	*E	Test Method D 3835
Temperature	230	°C	Y-mandated	DB 3-2d	Table 4.4	*F	
Tensile strength:							
Yield	28	MPa	Y-mandated	DB 3-3a	Table 4.3a	*D	Test Method D 638/ISO 527
Break	...	MPa	Y N (optional)	DB 3-3a	Table 4.3b	Z	Test Method D 638/ISO 527
Modulus	800	MPa	Y-mandated	DB 3-3b	Table 4.3c	*C	Test Method D 638/ISO 527
Tensile elongation:							
Yield	9	MPa	Y N (optional)	DB 3-4a	Table 4.4a	B	Test Method D 638/ISO 527
Break	450	MPa	Y N (optional)	DB 3-4b	Table 4.4	I	Test Method D 638/ISO 527
Density	1.78	g/cm <sup>3</sup>	Y-mandated	DB 3-5	Table 4.5	C	Test Method D 1505
Electricals:							
d-c volume resistivity	>2.4E14	Ω	Y N (optional)	DB 3-6	Table 4.6c	C	Test Methods D 257
Frequency No. 1	1K	Hz	Y N (optional)	DB 3-6	exponent	3	
Dielectric constant	10.1		Y N (optional)	DB 3-6	Table 4.6a	V	Test Methods D 150/IEC 250
Loss	0.021		Y N (optional)	DB 3-6	Table 4.6b	U	Test Methods D 150/IEC 250
Frequency No. 2	10K	Hz	Y N (optional)	DB 3-6	exponent	4	
Dielectric constant	9.3		Y N (optional)	DB 3-6	Table 4.6a	U	Test Methods D 150/IEC 250
Loss	0.031		Y N (optional)	DB 3-6	Table 4.6b	V	Test Methods D 150/IEC 250
Frequency No. 3	1M	Hz	Y N (optional)	DB 3-6	exponent	6	
Dielectric constant	7.3		Y N (optional)	DB 3-6	Table 4.6a	S	Test Methods D 150/IEC 250
Loss	0.15		Y N (optional)	DB 3-6	Table 4.6b	U	Test Methods D 150/IEC 250
Frequency No. 4		Hz	Y N (optional)	DB 3-6	exponent		
Dielectric constant			Y N (optional)	DB 3-6	Table 4.6a		Test Methods D 150/IEC 250
Loss			Y N (optional)	DB 3-6	Table 4.6b		Test Methods D 150/IEC 250
Flammability (OI)	53		Y N (optional)	DB 3-7	Table 4.7	C	Test Method D 2863/ISO 4583
Molding method	compression		Y as specified	DB 3-8	name	Q	
Specimen type (above 2 %)	527—Type 6a		Y as specified	DB 3-8	Table 4.	G	
Additives type	none		Y N (optional)	DB 4-1	Table 5.1	Z	
Form			Y N (optional)	DB 4-2	Table 5.2		
Form			Y N (optional)	DB 4-2	Table 5.2		
Alternate:							

Test/Parameter	Actual Lot Data	Specification Y N	Data Block	Data Table	Code Used	Other Comments
Property range No. 1	_____	Y if used	_____	_____	_____	_____
Property range No. 2	_____	Y if used	_____	_____	_____	_____
Method specification	_____	Y if used	_____	_____	_____	_____
Designation code: ASTM D 5XXX	VDF/CTFE-K, GGN, *P-*ZZEF-*DZC-BI-*C-C3VU4VU6SU-C-QG, Z, ,					

### X3. DEVELOPMENT OF DESIGNATION AND SPECIFICATION FOR 7.1.3.2

Test/Parameter	Actual Lot	Data	Specification Y N	Data Block	Data Table	Code Used	Other Comments
Polymer abbreviation	VDF/HFP		Y-mandated	No. 1-2	Section 3.3	VDF/HFP	
Polymer type	modified		Y-mandated	No. 1-2	Table 1	A	
Application/process and special characteristics	extrusion		Y-mandated	No. 2-1	Table 2-1	E	
	specification burn		Y N (optional)	No. 2-2	Table 2-2	F	
	low smoke		Y N (optional)	No. 2-2	Table 2-2	F4	
	pellets		Y N (optional)	No. 2-2	Table 2-2	G1	
	lubricated		Y N (optional)	No. 2-2	Table 2-2	S	
	opaque		Y N (optional)	No. 2-2	Table 2-2	T1	
			Y N (optional)	No. 2-2	Table 2-2		
			Y N (optional)	No. 2-2	Table 2-2		
Properties							
Melt temperature	143	°C	Y-mandated	No. 3-1	Table 4-1	*N	Test Method D 4591
MFR	...	g/10 min	Y-mandated	DB 3-2a	Table 4.1	Z	Test Method D 1238
Load	...	kg	[or use]	DB 3-2b	Table 4.2	Z	Test Method D 1238
Melt Viscosity	1300–1400	Pa/s	Y-mandated	DB 3-2c	Table 4.3	*?	Test Method D 3835
Temperature	230	°C	Y-mandated	DB 3-2d	Table 4.4	F	
Tensile strength:							
Yield	24	MPa	Y-mandated	DB 3-3a	Table 4.3a	*C	Test Method D 638/ISO 527
Break	...	MPa	Y N (optional)	DB 3-3a	Table 4.3b	Z	Test Method D 638/ISO 527
Modulus	1000	MPa	Y-mandated	DB 3-3b	Table 4.3c	*C	Test Method D 638/ISO 527
Tensile elongation:							
Yield	12	MPa	Y N (optional)	DB 3-4a	Table 4.4a	C	Test Method D 638/ISO 527
Break	350	MPa	Y N (optional)	DB 3-4b	Table 4.4	H	Test Method D 638/ISO 527
Density	1.79	g/cm <sup>3</sup>	Y-mandated	DB 3-5	Table 4.5	*C	Test Method D 1505
Electricals:							
d-c volume resistivity	none	Ω	Y N (optional)	DB 3-6	Table 4.6c	Z	Test Methods D 257
Frequency No. 1	none	Hz	Y N (optional)	DB 3-6	exponent	Z	
Dielectric constant			Y N (optional)	DB 3-6	Table 4.6a		Test Methods D 150/IEC 250
Loss			Y N (optional)	DB 3-6	Table 4.6b		Test Methods D 150/IEC 250
Frequency No. 2		Hz	Y N (optional)	DB 3-6	exponent		
Dielectric constant			Y N (optional)	DB 3-6	Table 4.6a		Test Methods D 150/IEC 250
Loss			Y N (optional)	DB 3-6	Table 4.6b		Test Methods D 150/IEC 250
Frequency No. 3		Hz	Y N (optional)	DB 3-6	exponent		
Dielectric constant			Y N (optional)	DB 3-6	Table 4.6a		Test Methods D 150/IEC 250
Loss			Y N (optional)	DB 3-6	Table 4.6b		Test Methods D 150/IEC 250
Frequency No. 4		Hz	Y N (optional)	DB 3-6	exponent		

Test/Parameter	Actual Lot	Data	Specification Y N	Data Block	Data Table	Code Used	Other Comments
Dielectric constant	_____		Y N (optional)	DB 3-6	Table 4.6a	_____	Test Methods D 150/IEC 250
Loss	_____		Y N (optional)	DB 3-6	Table 4.6b	_____	Test Methods D 150/IEC 250
Flammability (OI)	>80		Y N (optional)	DB 3-7	Table 4.7	*F	Test Method D 2863/ISO 4583
Molding method	compression		Y as specified	DB 3-8	Table 2-1	*Q	_____
Specimen type (above 2 %)	D 638 TYPE I		Y as specified	DB 3-8	Table 4.8	A	_____
Additives type	...		Y N (optional)	DB 4-1	Table 5.1	Z	_____
Form	_____		Y N (optional)	DB 4-2	Table 5.2	_____	_____
Form	_____		Y N (optional)	DB 4-2	Table 5.2	_____	_____
Alternate:							
Property range No. 1	1300–1700		Y if used	_____	_____	?1300–1700	_____
Property range No. 2	_____		Y if used	_____	_____	_____	_____
Method specification	_____		Y if used	_____	_____	_____	_____
Designation code: ASTM D 5XXX VDF/HFP-A, EFF4G1ST2, *N-*ZZ?F-*CZC-CH-*C-ZZ-*F-*QA, Z, ?1300–1700							

### SUMMARY OF CHANGES

This section identifies the location of selected changes to this specification. For the convenience of the user, Committee D20 has highlighted those changes that may impact the use of this specification. This section may also include descriptions of the changes or reasons for the changes, or both.

*D 5575 – 99:*

(1) Revised designations and titles.

(2) Revised Section 11.

(3) Added definition for *lot*.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).*