

# British Standard

A single copy of this  
British Standard is licensed to  
Giorgio Cavalieri  
on March 07, 2001

This is an uncontrolled copy.  
Ensure use of the most current  
version of this standard by  
searching British Standards Online  
at [bsonline.techindex.co.uk](http://bsonline.techindex.co.uk)

Specification for

# Wrought steels for mechanical and allied engineering purposes —

**Part 1: General inspection and testing  
procedures and specific requirements  
for carbon, carbon manganese, alloy  
and stainless steels**

# Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee ISE/31, Wrought steels, upon which the following bodies were represented:

Lloyd's Register of Shipping  
 National Association of Steel Stockholders  
 Road Vehicle Spring Society  
 Society of Motor Manufacturers and Traders Limited  
 Spring Research and Manufacturers' Association  
 Department of Trade and Industry (National Physical Laboratory)  
 Ministry of Defence  
 British Chain Manufacturers' Association  
 British Engineers' Cutting Tools Association  
 British Forging Industry Association  
 British Industrial Fasteners' Association  
 British Iron and Steel Producers' Association  
 British Stainless Steel Association

This British Standard, having been prepared under the direction of the Engineering Sector Board, was published under the authority of the Standards Board and comes into effect on 15 May 1996

© BSI 10-1998

First published July 1941  
 Second edition October 1942  
 Third edition March 1947  
 Fourth edition January 1955  
 Fifth edition (Part 1)  
 February 1972  
 (Part 2) September 1970  
 (Part 2) July 1971  
 (Supplement No. 1 to Part 3)  
 May 1973  
 (Part 4) February 1970  
 Sixth edition (combined, as  
 Part 1) May 1983  
 Seventh edition November 1991  
 Eighth edition May 1996

The following BSI references relate to the work on this standard:  
 Committee reference ISE/31  
 Draft announced in *BSI News*  
 September 1995

ISBN 0 580 25120 9

## Amendments issued since publication

Amd. No.	Date	Comments

# Contents

	Page
Committees responsible	Inside front cover
Foreword	iii
<hr/>	
Section 1. General inspection and testing procedure	
1.1 Scope	1
1.2 References	1
1.3 Definitions	1
1.4 Symbols	1
1.5 General	2
1.6 Information to be supplied by the purchaser	2
1.7 Steelmaking and casting process	3
1.8 Chemical composition	4
1.9 Product analysis and permitted variations	5
1.10 Freedom from defects	5
1.11 Condition of material on delivery	6
1.12 Heat treatment	8
1.13 Mechanical properties	8
1.14 Selection and preparation of material for mechanical testing	8
1.15 Frequency of other tests	9
1.16 Test methods and test results	10
1.17 Retests	11
1.18 Inspection	11
1.19 Manufacturer's statement	11
1.20 Marking	11
<hr/>	
Section 2. Specific requirements for as-rolled, as-rolled and softened and micro-alloyed carbon manganese steels	
2.1 Specific requirements for as-rolled, and as-rolled and softened steels	12
2.2 Specific requirements for micro-alloyed carbon manganese steels	12
<hr/>	
Section 3. Specific requirements for steels for surface hardening by nitriding	15
<hr/>	
Section 4. Specific requirements for case hardening steels	16
<hr/>	
Section 5. Specific requirements for stainless and heat resisting steels	24
<hr/>	
Section 6. Specific requirements for sizes and tolerances	
6.1 Sizes	27
6.2 Mass/unit length tolerances	27
6.3 Dimensional tolerances	27
6.4 Straightness	27
6.5 Length	27
<hr/>	
Annex A Hardenability curves for case hardening steels	31
Annex B Deoxidation of steel	43
<hr/>	
Figure A.1 — Hardenability curves for case hardening steels	32
Figure A.1.1 — Alloy steels	32
Figure A.1.1.1 — Steel 523H15	32
Figure A.1.1.2 — Steel 527H17	33
Figure A.1.1.3 — Steel 590H17	34
Figure A.1.1.4 — Steel 635H15	34
Figure A.1.1.5 — Steel 637H17	35
Figure A.1.1.6 — Steel 655H13	35
Figure A.1.1.7 — Steel 665H17	36

	Page
Figure A.1.1.8 — Steel 665H20	36
Figure A.1.1.9 — Steel 665H23	37
Figure A.1.1.10 — Steel 708H20	37
Figure A.1.1.11 — Steel 805H17	38
Figure A.1.1.12 — Steel 805H20	38
Figure A.1.1.13 — Steel 805H22	39
Figure A.1.1.14 — Steel 808H17	39
Figure A.1.1.15 — Steel 815H17	40
Figure A.1.1.16 — Steel 820H17	40
Figure A.1.1.17 — Steel 822H17	41
Figure A.1.1.18 — Steel 832H13	41
Figure A.1.1.19 — Steel 835H15	42
<hr/>	
Table 1 — Sulfur and phosphorus composition of steels	4
Table 2 — Incidental percentages of elements in steels	4
Table 3 — Permitted variations of product analysis from specified range	6
Table 4 — As-rolled and as-rolled and softened steels: chemical composition and mechanical property requirements	13
Table 5 — Micro-alloyed carbon manganese steels: chemical composition and mechanical property requirements	14
Table 6 — Steel for surface hardening by nitriding: chemical composition	15
Table 7 — Case hardening alloy steels: chemical composition and hardenability requirements	17
Table 8 — Case hardening steels: chemical composition and mechanical property requirements	19
Table 9 — Case hardening steels: heat treatment and maximum hardness requirements	22
Table 10 — Ferritic and martensitic stainless and heat resisting steels in the form of forgings: chemical composition, heat treatment and mechanical property requirements	25
Table 11 — Austenitic stainless and heat resisting steels in the form of forgings and heat resisting steel 310S31 in all product forms: chemical composition, softening treatment and mechanical property requirements	26
Table 12 — Billets (other than stainless steel) for forging: standard mass per metre and tolerances	28
Table 13 — Tolerances for hot rolled round and square bar and rough turned rounds	29
Table 14 — Tolerances for hot rolled hexagonal bar	29
Table 15 — Tolerances for hot rolled flat bar	30
<hr/>	
List of references	Inside back cover

# Foreword

This Part of BS 970 has been prepared by Technical Committee ISE/31 and is technically equivalent to BS 970-1:1991 except that requirements for boron steels have been deleted. In addition this standard now only applies to stainless steels when in the form of forgings. This standard, together with BS EN 10083-3, BS EN 10088-1, and BS EN 10088-3 supersedes BS 970-1:1991 which is withdrawn. This edition introduces technical changes but it does not reflect a full review or revision of the standard, which will be undertaken in due course.

The European requirements for stainless steels in flat rolled and long rolled product forms, but not forgings, are specified in BS EN 10088-1, and BS EN 10088-3 which are the English language versions of EN 10088-1, and EN 10088-3.

The European requirements for boron steels are specified in BS EN 10083-3 which is published simultaneously with this standard.

Work is continuing in Europe to prepare standards covering heat resisting steels, surface quality and case hardening steels.

As the European Standards are published, the appropriate tables and text will be deleted from BS 970-1:1996 until it is eventually withdrawn.

This edition of BS 970-1 still specifies Izod impact values for steels. It should be noted, however, that the Izod test is not accepted in Europe and that only Charpy impact tests will be specified in European Standards.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

## Summary of pages

This document comprises a front cover, an inside front cover, pages i to iv, pages 1 to 44, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.



# Section 1. General inspection and testing procedure

## 1.1 Scope

Section 1 of this Part of BS 970 specifies the requirements for steelmaking and general testing and inspection procedures for the release of steel in the form of blooms, billets, slabs, bars, rods and forgings, used in the as-rolled, as-forged or softened condition as appropriate and in accordance with the specific requirements for the steels in sections 2 to 5 inclusive. This standard applies to stainless steels only in the form of forgings but to the heat resisting steel 310S31 in both rolled and forged product forms.

NOTE 1 Forgings above 150 mm ruling section in carbon and alloy steels may be ordered in accordance with BS 29 and BS 4670 respectively and released to the requirements of those standards.

NOTE 2 Particular attention is also drawn to the information given in the foreword.

Sections 2 to 6 cover specific requirements for the supply of steels as follows:

- Section 2: As-rolled and as-rolled and softened steels and micro-alloyed carbon manganese steels;
- Section 3: Steels for surface hardening by nitriding;
- Section 4: Case hardening steels;
- Section 5: Stainless and heat resisting steels;
- Section 6: Specifies sizes and tolerances.

## 1.2 References

### 1.2.1 Normative references

This Part of BS 970 incorporates, by dated or undated reference, provisions from other publications. These normative references are made at the appropriate places in the text and the cited publications are listed on the inside back cover. For dated references, only the edition cited applies; any subsequent amendments to or revisions of the cited publication apply to this Part of BS 970 only when incorporated in the reference by amendment or revision. For undated references, the latest edition of the cited publication applies, together with any amendments.

### 1.2.2 Informative references

This Part of BS 970 refers to other publications that provide information or guidance. Editions of these publications current at the time of issue of this standard are listed on the inside back cover, but reference should be made to the latest editions.

## 1.3 Definitions

### 1.3.1 ruling section

equivalent diameter of that portion of the product at the time of heat treatment that is most important in relation to mechanical properties

### 1.3.2 limiting ruling section

for any composition of steel, the largest diameter in which certain specified mechanical properties are achieved after a specified heat treatment

### 1.3.3 equivalent diameter

for any product, or part of a product, the diameter at the time of heat treatment of a hypothetical very long bar effectively of infinite length of uniform circular cross-section which, if subjected to the same cooling conditions as the product, i.e. same initial and final temperature and same cooling medium, would have a cooling rate at its axis equivalent to that at the slowest cooling position in the product or relevant part

NOTE Further information is given in BS 5046.

### 1.3.4 test sample

portion of the material selected for testing

### 1.3.5 test bar

test sample after preparation for heat treatment

### 1.3.6 test piece

test sample or test bar as finally prepared for testing

## 1.4 Symbols

For the purposes of this Part of BS 970 the following symbols apply.

### 1.4.1 Tensile properties

$R_m$	tensile strength
$R_e$	yield strength
$A$	percentage elongation after fracture
$S_o$	original cross-sectional area of the gauge length
$R_{p0.2}$	0.2 % proof stress (non-proportional elongation)
$R_{p1.0}$	1.0 % proof stress (non-proportional elongation)
$R_{t0.5}$	0.5 % proof stress (total elongation)
$R_{t1.0}$	1.0 % proof stress (total elongation)
$R_{eH}$	upper yield stress

### 1.4.2 Impact properties

KCV	Charpy V-notch impact value
-----	-----------------------------



### 1.4.3 Hardness

HB	Brinell hardness
HV	Vickers hardness
HRC	Rockwell hardness (C scale)

### 1.4.4 Other

LRS	limiting ruling section
-----	-------------------------

## 1.5 General

### 1.5.1 Quality

The steel shall be selected and ordered by the purchaser and shall be supplied in accordance with the appropriate general requirements specified in this section and with the specific material requirements specified in sections 2 to 5 inclusive (see also note to 1.8.1) and with the tolerances specified in section 6. The manufacturer shall be responsible to the purchaser with respect to the conformance of the steel with these requirements and any additional requirements specified by the purchaser. All these requirements shall apply equally to steels given in categories 1 and 2.

NOTE When category 1 and category 2 steels are available, selection should be made from category 1 whenever possible. To facilitate this selection, category 1 steels are printed throughout the standard in normal (upright) type, and category 2 steels in italic (sloping) type.

### 1.5.2 Supply options

Where appropriate, the specific requirements of sections 2 to 5 cover supply options as follows.

- a) To close limits of chemical composition (A grades) where no mechanical properties or hardenability are specified.

NOTE For special applications, e.g. induction hardening, these steels may also be supplied with mechanical properties or hardenability specified by agreement between the purchaser and the supplier.

- b) To a combination of mechanical properties (M grades) or hardenability requirements (H grades) and chemical composition.

### 1.5.3 Machinability

Machinability is enhanced by higher sulfur content (see 1.8.2.2), by a lead addition (see 1.8.4) or by special heat treatment to promote optimum structure. Where extremely high machinability is needed, both sulfur and lead or other elements can be used in conjunction.

NOTE The presence of titanium may have an adverse effect on machinability.

### 1.5.4 Ruling section and hardenability

#### 1.5.4.1 Mechanical properties

1.5.4.1.1 For carbon and carbon manganese case-hardening steels, it is customary to test and release steel to specified mechanical property levels using a standard size of test bar. However, because of the effect of section size, the properties are quoted for different test bar sizes in the oil-quenched conditions, i.e. 13 mm, 19 mm and 29 mm, but the 19 mm size shall be used, except by agreement.

1.5.4.1.2 For alloy case-hardening steels, it is now customary to test and release steel to hardenability requirements. Hardenability bands for these steels (based on BS 4437) are included in section 4. These hardenability bands may be used as a guide to estimate the tensile strength of a ruling section at the time of heat treatment. When M steels are ordered, the properties quoted are for a test bar size of 19 mm (see 1.14.2.4.1).

NOTE The properties specified for both carbon and alloy steels apply only to the test bar size used and the heat treatment specified. If other heat treatments and/or sizes of test bar are used, then different results may be obtained. The conditions for these heat treatments and tests shall be agreed between the purchaser and the supplier.

### 1.6 Information to be supplied by the purchaser

The following information shall be stated on the enquiry and order. Purchasers should pay particular attention to the fact that this Part of BS 970 permits the options shown in the following list and where no specific choice is made by the purchaser, the supplier may select those considered appropriate, excepting that for items a, b, c, d, e, f and u he shall refer the matter to the purchaser.

NOTE A drawing of the part to be made may be useful in appropriate cases.

- a) The steel selected from 2.1 or 2.2, section 3, section 4 or section 5, or specific requirements for a non-standard steel to be released to the requirements of section 1.
- b) The applications of the billets and bars required, e.g. for forging, re-rolling, cold forming, metal coating, induction hardening and welding; the end use, if known, of the material (see 1.10.2); and whether the component is to be nitrided.
- c) Whether the steel is to be supplied to A, M, or H grade requirements (see 1.5.2).
- d) If ordered to the requirements of 2.2, the condition (see Table 5).

If ferritic or martensitic steels are ordered to the mechanical property requirements of section 5, the ruling section and tensile strength ranges required (see Table 13).

- e) If ordered to the hardenability requirements of sections 3 or 4, the hardness values at the required distances (see 1.16.4 and Table 7).
- f) In the case of carbon steels supplied to composition only which are not required for forgings and drop forgings, whether rimmed, balanced or killed steel is required (see 1.7.3.1 and annex B).
- g) If a specific steelmaking or casting process is required or, conversely, is not acceptable (see 1.7.1 and 1.7.2) and, if required, the minimum reduction from the as-cast state to the hot worked product (see note to 1.7.2, 1.10.1.2 and 1.19).
- h) If a steel having a controlled grain size is required (see 1.7.4) and the method of measurement if other than method 1 of BS 4490.
- i) The phosphorus and sulfur contents required if different from the standard limits (see 1.8.2).
- j) If a steel containing lead is required (see 1.8.4).
- k) Whether there are special requirements with regard to the amount of residual elements and/or what information is required on the certificate (see 1.8.3 and 1.19).
- l) If any other special quality criteria, e.g. vacuum degassing, ultrasonic testing and cleanness check, are required (see 1.10).
- m) The condition on delivery in which the material is to be supplied (see 1.11 and Table 9 and Table 10).
- n) Whether, in the case of billets and bars, the material shall be suitable for cold shearing.
- o) If a maximum decarburization limit is required (see 1.10.2.5).
- p) In the case of austenitic stainless steels, whether an intercrystalline corrosion test is required (see 1.16.6).
- q) If a 0.2 % proof stress, and in the case of austenitic steels, and/or a 1.0 % proof stress, is to be determined (see 1.16.1.4).
- r) If a representative will be sent to witness manufacture and/or testing (see 1.18).
- s) If a statement giving the cast analysis and/or the results of mechanical or other tests is required (see 1.19).
- t) If special identification of the steel is required (see 1.20).
- u) Sizes, lengths and tolerances required (see section 6).

## 1.7 Steelmaking and casting process

### 1.7.1 General

The steelmaking and casting process shall be chosen by the manufacturer unless otherwise specified on the enquiry and order. The air or mixed air and oxygen bottom blown basic converter process is not permitted.

NOTE *Electric quality* steel is steel melted in an induction furnace or in a basic lined electric arc furnace. When produced in the arc furnace the conventional double slag process is used. The steel is characterized by a high standard of cleanness and by low sulfur and phosphorus contents which can also be achieved by various alternative techniques, e.g. by selection of raw materials and/or secondary steelmaking.

*Electrically melted* steel is steel made in an electric furnace under conditions not necessarily conforming to the requirements for electric quality steel and which conform to standards similar to those required of open hearth steel.

### 1.7.2 Casting process

The steel shall be cast into ingots or shall be continuously cast unless the purchaser specifies a particular method on the enquiry and order.

NOTE Material in the as-cast condition is not covered by this Part of BS 970. When specifically required, the purchaser may specify a minimum reduction from the as-cast state to the hot worked product (see also 1.10.1.2).

### 1.7.3 Deoxidation

#### 1.7.3.1 Carbon and carbon manganese steels

Carbon and carbon manganese steels supplied as A grades shall be deoxidized as stated in annex B. If a choice is available, this shall be made by the purchaser and shall be stated on the enquiry and order.

Steels supplied as M or H grades shall be killed unless otherwise agreed and stated on the order.

Steels for case-hardening shall be killed. Steels for forgings and drop forgings shall be killed unless otherwise agreed and stated on the order.

#### 1.7.3.2 Micro-alloyed steels

Micro-alloyed steels shall be killed.

#### 1.7.3.3 Alloy and stainless steels

Alloy and stainless steels shall be killed.

### 1.7.4 Controlled grain size

#### 1.7.4.1 Carbon and carbon manganese steels

If required, many of the steels can be supplied having a controlled grain size of 1 to 5 (coarse grain) or 5 to 8 (fine grain) determined in accordance with BS 4490.

NOTE 1 Other methods for the determination of grain size may be used by agreement, see also note 1 to 1.7.4.2.

NOTE 2 Where conformance with a specific impact test is required, fine grain steel will normally be supplied.

### 1.7.4.2 Alloy steels

Alloy steels can be supplied with a grain size of 5 to 8 determined in accordance with BS 4490 or another method by agreement. Steels supplied to hardenability requirements are supplied fine-grained and if coarse grain steel is specifically required, then the hardenability shall be subject to negotiation.

NOTE 1 Steel is normally fine-grained if the total aluminium content is >0.018 %. However, in cases of dispute it should conform to BS 4490.

NOTE 2 Grain sizes finer than 8 may be permitted by agreement.

NOTE 3 Micro-alloyed steels are not subject to grain size control.

### 1.7.5 Cleaness

If required, standards for the degree of freedom from non-metallic inclusions and methods of determination shall be agreed between the purchaser and the supplier.

## 1.8 Chemical composition

### 1.8.1 Composition ranges

The chemical composition of the steel, based on cast analysis, shall conform to the requirements of the appropriate material specification in sections 2 to 5.

NOTE Where, in exceptional cases, the purchaser requires a steel of other than standard composition, this should be agreed at the time of the enquiry and order.

### 1.8.2 Sulfur and phosphorus contents

1.8.2.1 Carbon and carbon manganese steels shall be supplied with sulfur and phosphorus contents each of 0.050 % maximum. For alloy steels, the sulfur content shall be 0.040 % maximum and the phosphorus content 0.035 % maximum.

NOTE Where specifically ordered, a lower content of sulfur and phosphorus, with each element at 0.025 % maximum, may be supplied. This is recommended for certain alloy nitriding steels and for tensile strength ranges of 1225 N/mm<sup>2</sup> minimum and greater. Other limits for sulfur and phosphorus may be agreed between the purchaser and the supplier and stated on the order.

1.8.2.2 Unless otherwise stated in the material specification, steels can be supplied to controlled sulfur ranges, with associated phosphorus contents as given in Table 1. These shall be agreed between purchaser and supplier and stated on the order.

**Table 1 — Sulfur and phosphorus composition of steels**

Steels	Sulfur %	Phosphorus %
Carbon and carbon manganese steels	0.025 – 0.050	0.050 max.
	0.015 – 0.040	0.025 max.
Alloy steels	0.025 – 0.050	0.035 max.
	0.015 – 0.040	0.025 max.

NOTE 1 Other ranges can be supplied by agreement between the purchaser and the supplier.

NOTE 2 These ranges should be used when it is considered desirable to minimize the adverse effect which low sulfur content can have on machinability.

1.8.2.3 The sulfur and phosphorus contents for stainless steels are given in Table 10 and Table 11.

### 1.8.3 Residual elements

1.8.3.1 Elements not quoted in the relevant specification shall not be added to the steel without the agreement of the purchaser other than for the purpose of finishing the heat or to achieve anticipated or specified properties.

NOTE If required, the purchaser, by agreement with the manufacturer, may specify a maximum content of one or more residual elements and/or may require the amount of stated elements to be reported on the appropriate certificate.

1.8.3.2 In carbon, carbon manganese, and alloy steels, percentages of elements up to the following maxima shall be considered as incidental: chromium 0.30 %; molybdenum 0.15 %; nickel 0.40 %.

1.8.3.3 In micro-alloyed steels, maxima for residual elements shall be agreed between the purchaser and the supplier.

1.8.3.4 In stainless steels, percentages of elements up to a given maxima shall be considered as incidental, as given in Table 2.

**Table 2 — Incidental percentages of elements in stainless steels**

Elements	Non-austenitic steels %	Austenitic steels %
Molybdenum	0.30	1.00
Niobium	—	0.20
Titanium	—	0.10
Copper	0.30	0.70

#### 1.8.4 Steels containing lead

Steels containing lead may be supplied by agreement and the agreed lead range shall be stated on the order. In the absence of this agreement it shall be not less than 0.12 % nor greater than 0.35 % on the product analysis and shall be evenly and finely distributed.

NOTE If requested by the purchaser, the distribution may be checked by either a lead print, lead exudation test or by ultrasonic methods, the details for which should be agreed between the purchaser and the supplier.

The supplier shall endorse the invoice, delivery document, or appropriate certificate to indicate that lead has been added to conform to the specified requirement, and the steel shall be identifiable by a distinguishing mark agreed between the purchaser and the supplier.

### 1.9 Product analysis and permitted variations

**1.9.1** Analysis of the product may vary from the specified cast analysis due to heterogeneity arising during solidification. Table 3 shows the variations permitted in product analysis in relation to cross-sections not greater than 65 000 mm<sup>2</sup>.

The table only applies to fully killed steels and not to rimmed or balanced steels. Except in the case of stainless steels, it does not apply to resulfurized free-cutting steel with respect to the elements sulfur and phosphorus.

The variations may occur either above or below the individual element ranges but shall not apply both above and below the specified range for any one element in any one cast of steel.

**1.9.2** Any product which on subsequent analysis falls outside the permitted variations of the composition range specified for any element, shall be deemed not to conform to the requirements of this Part of BS 970.

**1.9.3** In the event of the results of the analysis of a single sample falling outside the permitted variations in the product analysis, further samples shall be selected for analysis from the remainder of the consignment as follows:

- a) at least two samples from the same cast for delivered masses up to 5 t;
- b) at least five samples from the same cast for delivered masses up to 20 t;
- c) at least eight samples from the same cast for delivered masses over 20 t.

The results of the analysis of these samples shall fall within the permitted variations. If any of these further samples are proved to be outside the permitted variations for any specified element, the consignment shall be deemed not to conform to the requirements of this Part of BS 970.

**1.9.4** Samples for product analysis shall be taken in accordance with BS 6200-2.1 and BS 6200-2.2 and in the event of dispute, analysed in accordance with the appropriate methods of BS 6200-3.

### 1.10 Freedom from defects

#### 1.10.1 General

**1.10.1.1** Special testing and inspection arrangements may, if required, be agreed between the purchaser and the supplier and should be stated at the time of enquiry and order.

**1.10.1.2** The procedures for casting, working, reheating and cooling and the amount of working shall ensure that the product is free from piping, central unsoundness, harmful segregation and other harmful internal and external defects.

#### 1.10.2 Surface defects

**1.10.2.1** Products intended for applications such as hot forgings which are not required for subsequent overall machining (see **1.10.2.2**) shall have a high standard of surface quality and the surface conditioning shall be such as to remove defects detrimental to the appropriate processing and, where specified, the end use.

Products intended for applications such as upset forging, cold heading or cold forging may require a higher degree of freedom from surface imperfection which shall be agreed between the purchaser and the supplier.

**1.10.2.2** Products intended for subsequent overall machining need not have the same freedom from surface defects as specified in **1.10.2.1**. Surface conditioning need only be such as to remove harmful defects taking into account the machining allowance.

The machining allowance shall be not less than 2 % of depth of the minimum permissible diameter of rounds or 2 % per side of the minimum permissible dimensions of flats or other solid sections.

NOTE Machining allowances less than these may be agreed between the purchaser and the supplier.

**1.10.2.3** Products for re-rolling or for applications other than those covered by **1.10.2.1** and **1.10.2.2** shall be free from defects harmful to their appropriate processing and, where specified, the end use. Material supplied to these conditions may not be suitable for the applications covered by **1.10.2.1** and **1.10.2.2**.

**1.10.2.4** Forgings and drop forgings shall be finished in a workmanlike manner and shall be free from flaws and harmful defects.

**1.10.2.5** When required, maximum decarburization levels shall be agreed between the purchaser and the supplier.

NOTE The surfaces of bars for induction hardening may be required to be free from decarburization and they will usually be turned or ground. If supplied in the black condition, overall grinding or turning may be permitted to clear decarburization, if necessary.

## 1.11 Condition of material on delivery

### 1.11.1 Carbon, carbon manganese, micro-alloyed and alloy steels

#### 1.11.1.1 Blooms, billets, slabs, black bars and rods

Blooms, billets, slabs, black bars and rods shall be supplied as-rolled or as-forged unless otherwise agreed between purchaser and supplier and stated on the order.

#### 1.11.1.2 Forgings and drop forgings

Forgings and drop forgings shall be supplied in the condition stated on the order.

#### 1.11.1.3 Normalized bars

Normalized bars shall be supplied to the specified mechanical properties and in the condition stated on the order.

### 1.11.1.4 Material used in non-heat-treated condition

Material to be used in the non-heat treated condition may be supplied to Brinell hardness values, by agreement between the purchaser and the supplier.

## 1.11.2 Stainless steels

### 1.11.2.1 Ferritic steels

Products in ferritic steels shall be supplied in the softened condition.

### 1.11.2.2 Martensitic steels

**1.11.2.2.1** Products for subsequent hot working shall be supplied in the softened condition.

**1.11.2.2.2** Forgings and drop forgings shall be supplied in the condition stated on the order.

### 1.11.2.3 Austenitic steels

**1.11.2.3.1** Products for subsequent hot working shall normally be supplied in the as-forged or as-rolled condition.

**1.11.2.3.2** Forgings, drop forgings and bars for machining shall be supplied in the softened condition and, if required, subsequently descaled. The softening treatment may be omitted if free cooling of the product from hot working does not lead to the formation of carbide precipitates or sigma or other detrimental phases and if it conforms to the requirements for the mechanical and intercrystalline corrosion tests.

**Table 3 — Permitted variations of product analysis from specified range**

Element	Range in which maximum of specified element falls %	Variation on specified range	
		Over max. %	Under min. %
a) Carbon, carbon manganese and micro-alloyed steels			
Carbon <sup>a</sup>	≤ 0.25	0.02	0.02
	> 0.25 ≤ 0.50 <sup>a</sup>	0.03	0.03
	> 0.50 ≤ 1.05	0.04	0.04
Silicon	≤ 0.40	0.03	0.03
Manganese	≤ 1.0	0.04	0.04
	> 1.0 ≤ 1.5	0.08	0.08
	> 1.5	0.10	0.10
Phosphorus	≤ 0.025	0.005	
	> 0.025 ≤ 0.040	0.006	
	> 0.040 ≤ 0.060	0.008	
Sulfur	≤ 0.025	0.005	
	> 0.025 ≤ 0.040	0.006	
	> 0.040 ≤ 0.060	0.008	
	> 0.060 ≤ 0.10	0.010	
	When range is specified:		
	0.015 – 0.040	0.006	0.003
	0.025 – 0.050	0.008	0.005
0.050 – 0.10	0.010	0.008	

Table 3 — Permitted variations of product analysis from specified range

Element	Range in which maximum of specified element falls %	Variation on specified range	
		Over max. %	Under min. %
<i>b) Alloy steels</i>			
Carbon	$\leq 0.25$	0.01	0.01
	$> 0.25 \leq 0.50$	0.02	0.02
	$> 0.50$	0.03	0.03
Silicon	$\leq 0.45$	0.03	0.03
Manganese	$\leq 0.70$	0.03	0.03
	$> 0.70 \leq 1.0$	0.04	0.04
	$> 1.0 \leq 2.0$	0.05	0.05
Phosphorus	$\leq 0.030$	0.003	
	$> 0.030 \leq 0.040$	0.004	
Sulfur <sup>b</sup>	$\leq 0.030$	0.003	
	$> 0.030 \leq 0.040$	0.004	
	$> 0.040 \leq 0.050$	0.005	
	When range is specified 0.015 – 0.040	0.004	0.003
	0.025 – 0.050	0.005	0.003
Chromium	$\leq 0.60$	0.03	0.03
	$> 0.60 \leq 1.25$	0.04	0.04
	$> 1.25 \leq 2.50$	0.05	0.05
	$> 2.50 \leq 4.0$	0.10	0.10
Molybdenum	$\leq 0.50$	0.02	0.02
	$> 0.50$	0.03	0.03
Nickel	$\leq 1.0$	0.03	0.03
	$> 1.0 \leq 3.0$	0.05	0.05
	$> 3.0 \leq 5.0$	0.07	0.07
Aluminium	$> 0.80 \leq 1.50$	0.10	0.10
Vanadium	$\leq 0.30$	0.03	0.03
<i>c) Stainless and heat resisting steels</i>			
Carbon	$\leq 0.03$	0.005	
	$> 0.03 \leq 0.25$	0.01	0.01
	$> 0.25 \leq 0.50$	0.02	0.02
Silicon	$\leq 1.0$	0.05	0.05
	$> 1.0 \leq 2.0$	0.07	0.07
Manganese	$\leq 1.0$	0.03	0.03
	$> 1.0 \leq 2.0$	0.04	0.04
Phosphorus	$\leq 0.030$	0.003	
	$> 0.030 \leq 0.045$	0.004	
	$> 0.045$	0.005	
Sulfur	$\leq 0.030$	0.003	
	$> 0.030 \leq 0.080$	0.005	
	Specified range 0.15 – 0.35	0.02	0.02
Chromium	$\leq 10.0$	0.10	0.10
	$> 10.0 \leq 15.0$	0.15	0.15
	$> 15.0 \leq 20.0$	0.20	0.20
	$> 20.0$	0.25	0.25
Molybdenum	$\leq 1.0$	0.03	0.03
	$> 1.0 \leq 2.0$	0.05	0.05
	$> 2.0 \leq 3.0$	0.08	0.08
Nickel	$\leq 1.0$	0.03	0.03
	$> 1.0 \leq 3.0$	0.05	0.05
	$> 3.0 \leq 5.0$	0.07	0.07
	$> 5.0 \leq 10.0$	0.10	0.10
	$> 10.0 \leq 20.0$	0.15	0.15
	$> 20.0$	0.20	0.20

Table 3 — Permitted variations of product analysis from specified range

Element	Range in which maximum of specified element falls %	Variation on specified range	
		Over max. %	Under min. %
Niobium	All ranges	0.05	0.05
Selenium	All ranges	0.03	0.03
Titanium	All ranges	0.05	0.05

<sup>a</sup> When required by the purchaser and subject to agreement with the supplier, smaller variations for the carbon range over 0.25 % up to and including 0.50 % may be agreed.

<sup>b</sup> For 606M36, deviations from the sulfur analysis are not specified.

## 1.12 Heat treatment

The heat treatment to be given to the test bars and to material required in the finally heat treated condition shall be as specified in Table 9, Table 10 and Table 11.

## 1.13 Mechanical properties

In the material specifications included in this Part of BS 970, all the specified mechanical properties refer to tests taken in the longitudinal direction (see 1.14.2.3 and 1.14.3.2).

## 1.14 Selection and preparation of material for mechanical testing (not applicable to micro-alloyed steels)

### 1.14.1 Tensile strength of 1225 N/mm<sup>2</sup> or greater

Where the tensile strength of alloy steel is specified as 1225 N/mm<sup>2</sup> minimum or more, the test bar may be machined to test piece size, plus a grinding allowance if required, before heat treatment. In such cases, the properties obtained are representative of those parts heat treated in the same ruling section as that of the test piece and may not represent larger ruling sections.

### 1.14.2 Selection and preparation of test bars for tensile and impact tests

#### 1.14.2.1 Material not supplied in the finally heat treated condition

Where the ruling section of the material does not differ appreciably from that of the forging or parts to be produced, test samples may be taken directly from the material and heat treated in the original size. Alternatively, when it is considered either by the purchaser or by the supplier that the results of heat treating in the original size would not be representative of the properties that would be obtained on the forgings or parts to be produced, test samples shall be forged and/or machined to test bars of a diameter, or equivalent diameter, corresponding to the ruling section of the forgings or parts at the time of heat treatment. Test bars shall be given the representative heat treatment for the parts concerned.

Subject to the requirements of 1.5.1, one tensile test and, where relevant, one Izod impact test, comprising three notches, or three Charpy V-notch impact tests shall be carried out on any batch of material of similar ruling section from the same cast. For the purpose of subsequent orders, these tests shall be taken as representing all sizes of material from the same cast where the ruling section of the forgings or parts does not exceed the ruling section of the test bar already tested.

#### 1.14.2.2 Bars for machining supplied in the finally heat treated condition

The samples shall be cut from the heat treated bars and shall not be further heat treated or mechanically worked after their removal.

Subject to the requirements of 1.5.1, one tensile test and, where relevant, one Izod impact test, comprising three notches, or three Charpy V-notch impact tests shall be carried out on any batch of bars of similar size from the same cast and heat treated together, when applicable.

#### 1.14.2.3 Forgings, drop forgings and machined parts

For forgings and drop forgings with a ruling section equivalent to a diameter greater than 29 mm, integral test samples may be provided by agreement between the purchaser and the supplier, when a prolongation shall be provided on an agreed proportion of forgings or drop forgings. Unless otherwise agreed, the prolongation shall have a diameter approximately equal to the ruling section of the forging or drop forging at the time of heat treatment and it shall not be finally severed until after heat treatment.

Where integral test samples are not practicable or are not required, for small forgings and drop forgings with ruling sections equivalent to a diameter of 29 mm or less, and for parts machined from bars not finally heat treated, separate test samples shall be provided. These shall be provided from the bars or billets from which the forgings, drop forgings or parts are made, or may be additional forgings, drop forgings or parts. The test samples shall be forged and/or machined to test bars of a diameter, or equivalent diameter, corresponding to the ruling section of the forgings, drop forgings or parts and shall be heat treated with the material they represent. The number of tests shall be agreed between the purchaser and the supplier.

Where integral test samples are required and it is not practicable to take tests in a longitudinal direction, tests may be taken in an alternative direction and the properties obtained shall be subject to agreement between the purchaser and the supplier (see 1.14.3.2).

#### 1.14.2.4 Steels for case-hardening

##### 1.14.2.4.1 Size of test bar

The test bar size shall be 19 mm diameter.

NOTE 1 For carbon and carbon manganese steels, 13 mm or 29 mm diameter test bar may be used by agreement (see 1.5.4.1.2).

NOTE 2 For alloy steels with a tensile strength of 1225 N/mm<sup>2</sup> or greater, see 1.14.1.

##### 1.14.2.4.2 Selection of samples

Subject to the requirements of 1.5.1, one test sample shall be selected to represent each cast. If the size of the test sample is greater than the specified test bar size, test bars shall be prepared by forging and/or machining to that size; but for sizes smaller than 13 mm diameter for carbon and carbon manganese steels and for sizes smaller than 19 mm diameter for alloy steels, the test bar shall be heat treated in the full section of the sample.

NOTE The properties specified in section 4 apply only to ruling sections equivalent to the preferred test bars. When components of different ruling section are carburized and heat treated, different core properties will be obtained. Similarly, it may be necessary to agree mechanical properties when the test sample size is less than the specified test bar sizes.

Attention is also drawn to the influence of several factors such as steel composition, ruling section and heat treatment, on the hardness of the case. For example, even if a low core strength suffices it will be necessary to use an alloy steel for acceptable case hardenability of the largest section sizes.

##### 1.14.2.4.3 Heat treatment of test bars

The test bars shall be blank carburized for at least 1 h at a temperature between 880 °C and 930 °C. After cooling to room temperature, they shall be reheated to the single quenching temperature, as stated in Table 9 and quenched in oil.

#### 1.14.3 Location of test pieces for mechanical testing

##### 1.14.3.1 General

In the general case where longitudinal tests are required, the test piece shall be prepared in accordance with the following.

- a) For ruling sections up to and including 25 mm, the test piece shall be machined coaxially from the test bars.
- b) For ruling sections over 25 mm, the longitudinal axis of the test pieces shall be 12.5 mm from the surface of the test bars.

##### 1.14.3.2 Transverse and other tests

When transverse tests or tests in other directions are required, the location of the test pieces and values for mechanical properties shall be agreed between the purchaser and the supplier.

#### 1.15 Frequency of other tests

##### 1.15.1 Number of hardness tests

The manufacturer shall carry out sufficient tests in accordance with 1.16.3 and 1.16.4 in order to ensure that the material conforms to the specified hardness.

##### 1.15.2 Number of hardenability tests

Subject to the requirements of 1.5.1, unless otherwise agreed, one test sample selected to represent each cast shall be reduced by forging or rolling to a size not greater than 38 mm diameter which shall represent the full cross-section of the material. This test bar shall also be of sufficient size to ensure the complete removal of carburization in machining to the standard test piece of 25 mm diameter.

##### 1.15.3 Number of grain size tests

Subject to the requirements of 1.5.1, when a grain controlled steel is required and unless otherwise agreed, one test sample for the determination of austenitic grain size shall be selected to represent each cast.



#### 1.15.4 Number of intercrystalline corrosion tests (Applicable to austenitic stainless steels only.)

If specified and agreed at the time of enquiry and order, one intercrystalline corrosion test shall be carried out per cast per heat treatment batch on the product having the largest equivalent diameter in the batch.

### 1.16 Test methods and test results

#### 1.16.1 Tensile test

**1.16.1.1** The tensile test shall be carried out in accordance with BS EN 10002-1.

**1.16.1.2** In cases of dispute, and except as provided in **1.16.1.3**, tensile test pieces shall be machined from blooms, billets, slabs, bars, forgings and drop forgings to the dimensions of the 11.28 mm diameter (100 mm<sup>2</sup> cross-sectional area) test piece or, if the test bar is too small, to the dimensions of the largest recommended round test piece that can be obtained having a gauge length equal to  $5.65 \sqrt{S_0}$ .

**1.16.1.3** When agreed between the purchaser and the supplier or for material not greater than 15 mm diameter or width across flats, unmachined test pieces having a gauge length equal to  $5.65 \sqrt{S_0}$  may be used.

**1.16.1.4** The properties specified in the relevant material specification or on the order shall be determined and the results obtained shall conform to the requirements.

For the yield strength  $R_e$  of non-austenitic steels, the following properties shall be determined for acceptance purposes unless otherwise agreed. Either the upper yield stress,  $R_{eH}$ , or the 0.5 % proof stress (total elongation),  $R_{t0.5}$ , may be determined. If either value satisfies the value of the yield strength  $R_e$ , then the material is deemed acceptable. In cases of dispute, the 0.5 % proof stress (total elongation),  $R_{t0.5}$ , shall be determined.

When specifically ordered and permitted by the material specification, the 0.2 % proof stress (non-proportional elongation) ( $R_{p0.2}$ ) of non-austenitic steels shall be measured and the value obtained shall conform to the specified requirement.

For austenitic steels, the 0.2 % proof stress ( $R_{p0.2}$ ), and/or the 1.0 % proof stress ( $R_{p1.0}$ ), shall be measured when specifically ordered, and the value obtained shall conform to the specified requirements. The 1.0 % proof stress may only be ordered when appropriate for the material specified.

#### 1.16.2 Impact tests

Either one or other of the following tests shall be carried out. The choice shall be made by the supplier.

- a) *Charpy V-notch impact test*. This test shall be carried out in accordance with BS EN 10045-1.
- b) *Izod impact test*. This test shall be carried out in accordance with BS 131-1.

The average value of the results obtained for three notches shall conform to the relevant requirements of the material specification. One individual value may be below the specified value, provided it is not less than 70 % of that value.

NOTE It is not possible to convert values from one type of impact test to the other.

#### 1.16.3 Hardness test

The hardness test shall be carried out:

- a) using the Brinell method in accordance with BS 240 using, where possible, a 10 mm diameter ball and a load of 3000 kg; or
- b) using Vickers and Rockwell methods of hardness testing in accordance with BS 427 and BS 891, respectively.

NOTE Considerable caution should be exercised when converting from one hardness scale to another and in cases of dispute the Brinell hardness test shall be used.

#### 1.16.4 Hardenability test

Hardenability tests shall be carried out in accordance with BS 4437. The values to be verified shall be selected by the purchaser in accordance with BS 4437.

NOTE Graphs for the comparison of the various H grades are given in annex A. These are for guidance only.

#### 1.16.5 Grain size test

Grain size tests shall be carried out in accordance with the appropriate method given in BS 4490.

NOTE Other methods may be used by agreement between the purchaser and the supplier, see 1.7.4.

#### 1.16.6 Intercrystalline corrosion test

(applicable to austenitic stainless steels only).

A bend test piece shall be prepared and tested in accordance with BS 5903. It shall be sensitized by heating at a temperature of 650 °C for the time specified in Table 11 followed by cooling in still air.

## 1.17 Retests

### 1.17.1 General

Subject to the requirements of 1.5.1, retests shall be carried out as specified in 1.17.2 to 1.17.6. However, if any test sample or test piece fails to conform to the requirements of 1.16 as a result of incorrect test procedure or faulty equipment, the test results shall be discarded and a further test sample(s) shall be retested in accordance with 1.16.

### 1.17.2 Tensile tests

**1.17.2.1** Should any of the original test pieces fail, twice the original number of test samples shall be selected for retesting, one of which shall be taken from the bar, billet, forging or drop forging from which the original test sample was taken, unless that item has been withdrawn by the manufacturer.

**1.17.2.2** The mechanical properties obtained from the test pieces prepared from the further test samples shall conform to the specified requirements. Should any of the retests fail, the material represented shall be deemed not to conform to the requirements of this Part of BS 970.

**1.17.2.3** In the case of material supplied in the heat treated condition, the manufacturer shall have the right to reheat treat the material and resubmit it for testing.

### 1.17.3 Charpy V-notch impact and Izod impact tests

**1.17.3.1** If the average of three impact values is lower than the specified value, or if any one value is lower than 70 % of this specified value, three additional test pieces shall be taken from the same sample and tested. The average value of the six tests shall be not less than the specified value. Not more than two of the individual values may be lower than the specified value and not more than one may be lower than 70 % of this value.

**1.17.3.2** In the case of material supplied in the heat treated condition, the manufacturer shall have the right to reheat treat the material and resubmit it for testing.

### 1.17.4 Hardness test

**1.17.4.1** Should the hardness value determined on any bloom, billet, slab, bar, forging, drop forging or machined part fail to conform to the specified requirements, then an adequate number of items shall be selected for retesting, one of which shall be the original bloom, billet, slab, bar, forging, drop forging or machined part, unless that item has been withdrawn by the manufacturer.

**1.17.4.2** Should the hardness results obtained on all the retest items conform to specification requirements, then the batch shall be deemed to conform to this Part of BS 970.

**1.17.4.3** Should any retest item exhibit hardness values not conforming to the specified requirements, then tensile test pieces may be prepared, as applicable, from the items showing the widest deviation, above and/or below the agreed hardness range. Should the results obtained from such tensile test pieces conform to the tensile test requirements of the specification, then the material shall be deemed to conform to this Part of BS 970.

Failing this, the batch represented by the original tests may be reheat treated and resubmitted for testing.

### 1.17.5 Hardenability and grain size tests

Should the results of either of these tests fail to conform to the specified requirements and this is confirmed on retesting, the material shall be deemed not to conform to this Part of BS 970.

### 1.17.6 Intercrystalline corrosion test

The relevant provisions of BS 5903 shall apply.

## 1.18 Inspection

The purchaser or his representative shall have access at all reasonable times to those parts of the manufacturer's works engaged on the order. He shall be at liberty to inspect the manufacture at any stage and to witness the required tests. When the material is to be inspected and tested in the presence of the purchaser's representative, it shall be so stated on the enquiry and order.

## 1.19 Manufacturer's statement

If required by the order, the manufacturer shall supply a certificate stating the cast analysis of the material, the heat treatment, the results of the mechanical or other tests, or any combinations of these.

The document supplied shall state the steelmaking and casting process and, when requested, the reduction from the as-cast state (see 1.7.1 and 1.7.2).

## 1.20 Marking

If the purchaser requires special marking to be applied to the material then the manner of marking shall be the subject of agreement between the purchaser and the supplier. If this marking is required it shall be stated on the enquiry and order (see also 1.8.4 regarding the marking of lead containing steels).

## Section 2. Specific requirements for as-rolled, as-rolled and softened and micro-alloyed carbon manganese steels

### 2.1 Specific requirements for as-rolled and as-rolled and softened steels

NOTE For requirements for through hardening steels, see section 3.

Category 1 steels shall be used for new designs and for established designs whenever possible.

The chemical composition and mechanical properties shall be as given in Table 4.

### 2.2 Specific requirements for micro-alloyed carbon manganese steels

NOTE 1 The steels included in this clause develop their properties by the addition of small amounts of vanadium or other micro-alloying elements, together with control of hot working temperature and subsequent air cooling<sup>1)</sup> and in the finished condition have a ferrite/pearlite structure, free from bainite. They offer, for certain applications, an alternative route to obtaining hardness and tensile strength normally associated with medium carbon and alloy steels in the hardened and tempered condition.

Since the analysis of the steel necessary to attain the specified properties depends on processing conditions and section size, it is not possible to state specific analysis requirements; the analysis, however, shall be selected from within the broad range given in Table 5, according to the particular end conditions and strength grade required. In order to be free from bainite, due account shall be taken of those elements which may form this constituent, e.g. Mo, Mn, Cr, Ni and Cu. When necessary, metallurgical advice shall be sought.

NOTE 2 To aid machinability, it may be necessary for the microstructure of the forged part to be agreed.

---

<sup>1)</sup> For this reason the use of separate test bars is not recommended.

**Table 4 — As-rolled and as-rolled and softened steels: chemical composition and mechanical property requirements**

Steel		Chemical composition %			LRS	$R_m$ min.	$R_e$ min.	A min. on	Impact <sup>c</sup>		HB
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>	C	Mn	Others	mm	<sup>b</sup> N/mm <sup>2</sup>	<sup>b</sup> N/mm <sup>2</sup>	5.65√ $S_0$	Izod min. ft · lb	KCV min. J	
<b>Carbon steels (as-rolled)</b>											
040A04		0.08 max.	0.30–0.50								
040A10		0.08–0.13	0.30–0.50								
040A12		0.10–0.15	0.30–0.50								
080A15		0.13–0.18	0.70–0.90								
080A20		0.18–0.23	0.70–0.90								
055M15		0.20 max.	0.80 max.		150	310	—	25	—	—	121 min.
<b>Carbon steels (as-rolled and softened)</b>											
060A62		0.60–0.65	0.50–0.70								207 max.
060A67		0.65–0.70	0.50–0.70								217 max.
080A67		0.65–0.70	0.70–0.90								229 max.
060A72		0.70–0.75	0.50–0.70								241 max.
060A78		0.75–0.82	0.50–0.70								255 max.
060A81		0.78–0.85	0.50–0.70								269 max.
<sup>a</sup> See note to 1.5.1. <sup>b</sup> 1 N/mm <sup>2</sup> = 1 MPa. <sup>c</sup> Only applicable if fine grain controlled material is ordered.											

Table 5 — Micro-alloyed carbon manganese steels: chemical composition and mechanical property requirements

Steel <sup>b</sup>	Chemical composition							Condition <sup>c</sup>	LRS	$R_m$	$R_e$ min.	$A$ min. on $5.65\sqrt{S_0}$	Impact KCV min.	HB
	%													
	C	Si	Mn	P	S	V	Al		mm.	<sup>a</sup> Nmm <sup>2</sup>	<sup>a</sup> Nmm <sup>2</sup>		J	
280M01	0.30–0.55	0.15–0.60	0.60–1.50	0.035 max.	0.045–0.065 <sup>d</sup>	0.08–0.20 <sup>e</sup>	0.035 max.	S	100	775–925	530	14	10	223–277
								T	100	850–1000	560	12	8	248–302
								U	100	925–1075	600	10	8	269–331

<sup>a</sup> 1 N/mm<sup>2</sup> = 1 MPa.  
<sup>b</sup> Category 1 steel.  
<sup>c</sup> These tensile strength ranges are not achieved by hardening and tempering (see note 3 to 1.7.4.2 with respect to grain size).  
<sup>d</sup> The steel may be supplied with a sulfur content of 0.050 % maximum or, to obtain improved machinability, with 0.065 % to 0.10 % sulfur.  
<sup>e</sup> Other micro-alloying additions (such as Nb, Ti) may be made, either singly or in combination, in which case the total, as determined by product analysis, shall be in the range 0.08 % to 0.20 %.

## Section 3. Specific requirements for steels for surface hardening by nitriding

Specific requirements for steels for surface hardening by nitriding shall be as given in Table 6.

**Table 6 — Steel for surface hardening by nitriding: chemical composition**

Steel	Chemical composition				
	%				
Alloy steel	C	Mn	Cr	Mo	Others
708M40	0.36–0.44	0.70–1.00	0.90–1.20	0.15–0.25	$4 \times P + Sn \leq 0.15$
709M40	0.36–0.44	0.70–1.00	0.90–1.20	0.25–0.35	$4 \times P + Sn \leq 0.15$
720M32	0.28–0.35	0.40–0.70	2.80–3.30	0.40–0.60	
722M24	0.20–0.28	0.45–0.70	3.00–3.50	0.45–0.65	$4 \times P + Sn \leq 0.12$
897M39	0.35–0.43	0.45–0.70	3.00–3.50	0.80–1.10	P 0.025 max. S 0.025 max. V 0.15 – 0.25
905M39	0.35–0.43	0.40–0.65	1.40–1.80	0.15–0.25	$4 \times P + Sn \leq 0.10$ P 0.025 max. S 0.025 max. Al 0.90 – 1.30 $4 \times P + Sn \leq 0.10$

## Section 4. Specific requirements for case-hardening steels

Table 7 to Table 9 give requirements for carbon or alloy case-hardening steels. Additionally, as with some other sections, the steels have been divided into two categories. Category 1 steels should be used for new designs and for established designs whenever possible.

In selecting a case-hardening steel for components with larger section sizes, attention has to be given to achieving the required surface hardness as well as the core properties. This applies particularly where core strength requirements are not high and a carbon or an alloy steel at the low end of the range would give the required core strength. If water hardening is not an option because of distortion, the use of an appropriate alloy steel may be necessary to achieve satisfactory case-hardness.

Attention is drawn to the advantages of specifying hardenability requirements for alloy steels (see Table 10).

**Table 7 — Case-hardening alloy steels: chemical composition and hardenability requirements<sup>a</sup>**

Steel		Chemical composition						HV 20 or 30 values at distance															
		%						mm															
Category 1 <sup>b</sup>	Category 2 <sup>b</sup>	C	Mn	Cr	Mo	Ni	Others		1.25	2.00	2.75	3.50	4.25	5.00	5.75	6.50	7.25	9.00	10.5	12.0	15.0	20.0	25.0
<b>Alloy Steels (HV values)</b>																							
523H15		0.12–0.18	0.30–0.60	0.30–0.60				max.	510	490	445	385	340	315	295	280	260	235	220	215	210	205	200
								min.	380	340	280	240	200	180									
527H17		0.14–0.20	0.70–1.00	0.60–0.90				max.	460	450	440	415	385	355	330	310	300	285	275	270	270	255	240
								min.	380	365	345	320	295	270	255	250	240	230	220	210	210	190	
<b>Alloy steels (HRC values)</b>																							
Steel		Chemical composition						HRC values at distance															
Category <sup>b</sup>	Category <sup>b</sup>	C	Mn	Cr	Mo	Ni	Others		1.5	3	5	7	9	11	13	15	20	25	30	35	40	45	50
590H17		0.14–0.20	1.00–1.30	0.80–1.10				max.	47	46	44	42	39	37	34	33	31	30	29	28	27		
								min.	39	36	32	29	26	24	22	20							
	<i>635H15</i>	<i>0.12–0.18</i>	<i>0.60–0.90</i>	<i>0.40–0.80</i>		<i>0.70–1.10</i>		max.	45	43	40	36	33	30	28	26	24	23	22	20			
								min.	38	32	26	23	21										
	<i>637H17</i>	<i>0.14–0.20</i>	<i>0.60–0.90</i>	<i>0.60–1.00</i>		<i>0.85–1.25</i>		max.	45	45	44	42	40	37	35	33	31	30	29	28	28	27	26
								min.	39	37	34	29	27	24	23	21	20						
	<i>655H13</i>	<i>0.10–0.16</i>	<i>0.35–0.60</i>	<i>0.70–1.00</i>		<i>3.00–3.75</i>		max.	44	44	44	43	42	41	40	39	37	35	34	33	32	32	31
								min.	37	36	34	32	30	28	27	25	23	22	21				
	<i>665H17</i>	<i>0.14–0.20</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		max.	46	44	41	36	31	28	25	24	22	21	20				
								min.	39	33	24	21											
	<i>665H20</i>	<i>0.17–0.23</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		max.	48	45	41	37	32	29	27	25	23	21	20				
								min.	41	35	26	22	20										
	<i>665H23</i>	<i>0.20–0.26</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		max.	51	49	46	43	39	34	31	29	27	25	24	23	22	22	
								min.	44	40	33	28	26	23	22	21	20						



**Table 7 — Case-hardening alloy steels: chemical composition and hardenability requirements<sup>a</sup>**

Steel		Chemical composition						HRC values at distance														
Category 1 <sup>b</sup>	Category 2 <sup>b</sup>	%						mm														
		C	Mn	Cr	Mo	Ni	Others	1.5	3	5	7	9	11	13	15	20	25	30	35	40	45	50
<b>Alloy steels (HRC values)</b>																						
708H20	805H17	0.17–0.23	0.60–0.90	0.85–1.15	0.15–0.25			max.	47	47	46	44	41	39	36	35	33	31	30	29	28	28
			0.14–0.20	0.60–0.95	0.35–0.65	0.15–0.25	0.35–0.75		min.	39	38	35	32	29	26	22	22	20				
								max.	46	44	40	36	32	28	27	25	23	21	20			
								min.	39	33	26	22	20									
805H20		0.17–0.23	0.60–0.95	0.35–0.65	0.15–0.25	0.35–0.75		max.	48	47	44	40	35	32	30	28	25	24	23	23	23	22
								min.	41	37	31	25	22	20								
805H22		0.19–0.25	0.60–0.95	0.35–0.65	0.15–0.25	0.35–0.75		max.	50	49	46	43	38	34	32	30	27	25	25	24	24	24
								min.	43	39	33	28	25	22	20							
808H17		0.14–0.20	0.70–1.05	0.35–0.65	0.30–0.40	0.35–0.75		max.	46	45	44	41	38	34	32	30	28	27	26	26	25	25
								min.	39	38	33	27	24	23	21	21	19	18				
815H17		0.14–0.20	0.60–0.90	0.80–1.20	0.10–0.20	1.20–1.70		max.	46	46	45	45	44	43	42	41	38	35	34	34	33	33
								min.	39	37	35	33	32	30	29	27	25	22	20			
820H17		0.14–0.20	0.60–0.90	0.80–1.20	0.10–0.20	1.50–2.00		max.	46	46	46	46	45	45	44	44	42	40	38	38	37	37
								min.	39	39	38	37	35	33	32	30	28	26	25	25	24	24
822H17		0.14–0.20	0.40–0.70	1.30–1.70	0.15–0.25	1.75–2.25		max.	46	46	46	46	45	45	45	45	45	44	43	43	42	42
								min.	39	39	39	38	38	37	37	36	35	33	32	31	30	29
	832H13	0.10–0.16	0.35–0.60	0.70–1.00	0.10–0.25	3.00–3.75		max.	44	44	44	44	44	44	44	43	42	40	38	36	35	34
								min.	37	37	37	36	34	32	30	28	26	23	22	21	21	21
835H15		0.12–0.18	0.25–0.50	1.00–1.40	0.15–0.30	3.90–4.30		max.	45	45	45	45	45	45	45	45	45	44	44	44	43	
								min.	38	38	38	38	38	38	38	38	37	36	35	34	33	32

<sup>a</sup> For guidance see also annex A; for mechanical property requirements see Table 10.

<sup>b</sup> See note to 1.5.1.

**Table 8 — Case hardening steels: chemical composition and mechanical property requirements**

Steel		Chemical composition						Test bar diameter	$R_m$ min.	A min. on $5.65\sqrt{S_0}$	Impact	
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>	%									Izod min.	KCV min.
		C	Mn	Cr	Mo	Ni	Others	mm	<sup>b</sup> N/mm <sup>2</sup>	ft · lb	J	
<b>Carbon steels</b>												
045M10		0.07–0.13	0.30–0.60					13	430	18	35	42
								19 <sup>c</sup>	430	18	35	42
080M15	<i>045A10</i>	<i>0.08–0.13</i>	<i>0.30–0.60</i>									
		0.12–0.18	0.60–1.00					13	490	16	30	35
								19 <sup>c</sup>	460	16	30	35
	<i>080A15</i>	<i>0.13–0.18</i>	<i>0.70–0.90</i>					29	430	18	30	35
<b>Carbon manganese steels</b>												
130M15		0.12–0.18	1.10–1.50					13	740	13	25	28
								19 <sup>c</sup>	650	14	30	35
								29	590	15	35	42
210M15	<i>125A15</i>	<i>0.13–0.18</i>	<i>1.10–1.40</i>									
		0.12–0.18	0.90–1.30				S 0.10 – 0.18	13	490	16	30	35
								19 <sup>c</sup>	460	16	30	35
								29	430	18	30	35
214M15	<i>210A15</i>	<i>0.13–0.18</i>	<i>0.90–1.20</i>				S 0.10 – 0.18					
		0.12–0.18	1.20–1.60				S 0.10 – 0.18	13	740	12	25	28
								19 <sup>c</sup>	650	12	30	35
								29	590	13	35	42
	<i>214A15</i>	<i>0.13–0.18</i>	<i>1.20–1.50</i>				S 0.10 – 0.18					

**Table 8 — Case hardening steels: chemical composition and mechanical property requirements**

Steel		Chemical composition						Test bar diameter	$R_m$ min.	A min. on $5.65\sqrt{S_0}$	Impact	
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>	%									Izod min.	KCV min.
		C	Mn	Cr	Mo	Ni	Others	mm	<sup>b</sup> N/mm <sup>2</sup>	ft · lb	J	
<b>Alloy steel</b>												
523M15		0.12–0.18	0.30–0.60	0.30–0.60				19	620	13	25	28
527M17		0.14–0.20	0.70–1.00	0.60–0.90				19	770	12	15 <sup>d</sup>	16 <sup>d</sup>
	<i>527A17</i>	<i>0.14–0.19</i>	<i>0.70–0.90</i>	<i>0.70–0.90</i>								
590M17		0.14–0.20	1.00–1.30	0.80–1.10				19	930	10	15 <sup>d</sup>	16 <sup>d</sup>
	<i>590A15</i>	<i>0.13–0.18</i>	<i>0.90–1.20</i>	<i>0.90–1.20</i>								
	<i>635M15</i>	<i>0.12–0.18</i>	<i>0.60–0.90</i>	<i>0.40–0.80</i>		<i>0.70–1.10</i>		<i>19</i>	<i>770</i>	<i>12</i>	<i>20</i>	<i>22</i>
	<i>635A14</i>	<i>0.12–0.17</i>	<i>0.70–0.90</i>	<i>0.50–0.75</i>	$\leq 0.10$	<i>0.70–1.00</i>						
	<i>637M17</i>	<i>0.14–0.20</i>	<i>0.60–0.90</i>	<i>0.60–1.00</i>		<i>0.85–1.25</i>		<i>19</i>	<i>930</i>	<i>10</i>	<i>15</i>	<i>16</i>
	<i>637A16</i>	<i>0.14–0.19</i>	<i>0.70–0.90</i>	<i>0.70–1.00</i>	$\leq 0.10$	<i>0.90–1.20</i>						
	<i>655M13</i>	<i>0.10–0.16</i>	<i>0.35–0.60</i>	<i>0.70–1.00</i>		<i>3.00–3.75</i>		<i>19</i>	<i>1000</i>	<i>9</i>	<i>30</i>	<i>35</i>
	<i>665M17</i>	<i>0.14–0.20</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		<i>19</i>	<i>770</i>	<i>12</i>	<i>30</i>	<i>35</i>
	<i>665M20</i>	<i>0.17–0.23</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		<i>19</i>	<i>850</i>	<i>11</i>	<i>20</i>	<i>22</i>
	<i>665M23</i>	<i>0.20–0.26</i>	<i>0.35–0.75</i>		<i>0.20–0.30</i>	<i>1.50–2.00</i>		<i>19</i>	<i>930</i>	<i>10</i>	<i>12</i>	<i>13</i>
708M20		0.17–0.23	0.60–0.90	0.85–1.15	0.15–0.25			19	930	10	15 <sup>d</sup>	16 <sup>d</sup>
	<i>805M17</i>	<i>0.14–0.20</i>	<i>0.60–0.95</i>	<i>0.35–0.65</i>	<i>0.15–0.25</i>	<i>0.35–0.75</i>	P $\leq$ 0.035 S $\leq$ 0.035	<i>19</i>	<i>770</i>	<i>12</i>	<i>20</i>	<i>22</i>
	<i>805A17</i>	<i>0.15–0.20</i>	<i>0.70–0.90</i>	<i>0.40–0.60</i>	<i>0.15–0.25</i>	<i>0.40–0.70</i>						
805M20		0.17–0.23	0.60–0.95	0.35–0.65	0.15–0.25	0.35–0.75		19	850	11	15	16
805A20		0.18–0.23	0.70–0.90	0.40–0.60	0.15–0.25	0.40–0.70						
805M22		0.19–0.25	0.60–0.95	0.35–0.65	0.15–0.25	0.35–0.75		19	930	10	10	11
805A22		0.20–0.25	0.70–0.90	0.40–0.60	0.15–0.25	0.40–0.70						
808M17		0.14–0.20	0.70–1.05	0.35–0.65	0.30–0.40	0.35–0.75		19	930	10	20	22
815M17		0.14–0.20	0.60–0.90	0.80–1.20	0.10–0.20	1.20–1.70		19	1080	8	20	22

**Table 8 — Case hardening steels: chemical composition and mechanical property requirements**

Steel		Chemical composition						Test bar diameter	$R_m$ min.	A min. on $5.65\sqrt{S_0}$	Impact	
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>	%									mm	<sup>b</sup> N/mm <sup>2</sup>
		C	Mn	Cr	Mo	Ni	Others					
820M17		0.14–0.20	0.60–0.90	0.80–1.20	0.10–0.20	1.50–2.00		19	1160	8	20	22
822M17		0.14–0.20	0.40–0.70	1.30–1.70	0.15–0.25	1.75–2.25		19	1310	8	20	22
	<i>832M13</i>	<i>0.10–0.16</i>	<i>0.35–0.60</i>	<i>0.70–1.00</i>	<i>0.10–0.25</i>	<i>3.00–3.75</i>		<i>19</i>	<i>1080</i>	8	<i>25</i>	<i>28</i>
835M15		0.12–0.18	0.25–0.50	1.00–1.40	0.15–0.30	3.90–4.30		19	1310	8	25	28

<sup>a</sup> See note to 1.5.1.  
<sup>b</sup> 1 N/mm<sup>2</sup> = 1 MPa.  
<sup>c</sup> Preferred size.  
<sup>d</sup> These are new steels which may have been conservatively rated due to limited data.

Table 9 — Case hardening steels: heat treatment and maximum hardness requirements

Steel		Hardening temperature °C	Requirements for hardenability test		Maximum hardness HB (when specified on the order) in the condition of delivery			
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>		Preheat treatment temperature °C	Austenitizing temperature °C	Bars and billets for forging	Forgings and bars for machining		
						Normalized	Sub-critically annealed	Normalized and tempered
<b>Carbon, carbon manganese steels</b>								
045M10		900 – 930						
080M15		900 – 930						
130M15		900 – 930						
210M15		900 – 930						
214M15		900 – 930						
<b>Alloy steels</b>								
523H15		—	930 – 950	925	207	207		
523M15		820 – 840	—	—	207	207		
527H17		—	930 – 950	925	—	217		
527M17		820 – 840	—	—	—	217		
590H17		—	930 – 950	870	—	217		
590M17		820 – 840	—	—	—	217		
	<i>635H15</i>	—	<i>930 – 950</i>	<i>925</i>	<i>207</i>	<i>207</i>		
	<i>635M15</i>	<i>820 – 840</i>	—	—	<i>207</i>	<i>207</i>		
	<i>637H17</i>	—	<i>930 – 950</i>	<i>925</i>	<i>217</i>	<i>217</i>		
	<i>637M17</i>	<i>820 – 840</i>	—	—	<i>217</i>	<i>217</i>		
	<i>655H13</i>	—	<i>880 – 900</i>	<i>830</i>	<i>255</i>	—	<i>255</i>	<i>223</i>
	<i>655M13</i>	<i>800 – 820</i>	—	—	<i>255</i>	—	<i>255</i>	<i>223</i>
	<i>665H17</i>	—	<i>930 – 950</i>	<i>925</i>	<i>207</i>	<i>207</i>		
	<i>665H20</i>	—	<i>930 – 950</i>	<i>925</i>	<i>207</i>	<i>207</i>		
	<i>665H23</i>	—	<i>930 – 950</i>	<i>925</i>	<i>229</i>	<i>229</i>		
	<i>665M17</i>	<i>820 – 840</i>	—	—	<i>207</i>	<i>207</i>		
	<i>665M20</i>	<i>820 – 840</i>	—	—	<i>207</i>	<i>207</i>		
	<i>665M23</i>	<i>820 – 840</i>	—	—	<i>229</i>	<i>229</i>		
708H20		—	930 – 950	925				
708M20		830 – 840	—	—	—	—		217
	<i>805H17</i>	—	<i>930 – 950</i>	<i>925</i>	<i>207</i>	<i>207</i>		
805H20		—	930 – 950	925	207	207		
805H22		—	930 – 950	925	217	217		
	<i>805M17</i>	<i>820 – 840</i>	—	—	<i>207</i>	<i>207</i>		
805M20		820 – 840	—	—	207	207		
805M22		820 – 840	—	—	217	217		
808H17		—	930 – 950	925	—	—		
808M17		820 – 840	—	—	—	—		

**Table 9 — Case hardening steels: heat treatment and maximum hardness requirements**

Steel		Hardening temperature °C	Requirements for hardenability test		Maximum hardness HB (when specified on the order) in the condition of delivery			
Category 1 <sup>a</sup>	Category 2 <sup>a</sup>		Preheat treatment temperature °C	Austenitizing temperature °C	Bars and billets for forging	Forgings and bars for machining		
						Normalized	Sub-critically annealed	Normalized and tempered
815H17		—	930 – 950	925	255	—	255	241
815M17		820 – 840	—	—	255	—	255	241
820H17		—	880 – 900	830	277	—	269	248
820M17		820 – 840	—	—	277	—	269	248
822H17		—	880 – 900	830	277	—	269	255
822M17		820 – 840	—	—	277	—	269	255
	<i>832H13</i>	—	<i>880 – 900</i>	<i>830</i>	<i>255</i>	—	<i>255</i>	<i>248</i>
	<i>832M13</i>	<i>800 – 820</i>	—	—	<i>255</i>	—	<i>255</i>	<i>248</i>
835H15		—	880 – 900	830	277	—	277	269
835M15		800 – 820 <sup>b</sup>	—	—	277	—	277	269

<sup>a</sup> See note to 1.5.1.  
<sup>b</sup> Shall also be stress relieved at a temperature not exceeding 200 °C.

## Section 5. Specific requirements for stainless and heat resisting steels

Table 10 and Table 11 specify requirements for ferritic, martensitic and austenitic stainless steels in the form of forgings, and the heat resisting steel 310 S31 both as forgings and as-cast or rolled products.

Especially in the case of austenitic steels, changes have been made to take into account agreements that have been reached in international harmonization discussions and mainly concern the chemical composition ranges. The changes include the introduction of 2.0 % to 2.5 % and 2.5 % to 3.0 % molybdenum ranges in place of the single range 2.25 % to 3.0 % molybdenum, the removal of the previous minimum silicon and manganese limits and for certain unstabilized steels, the chromium range has been widened allowing chromium down to 17.0 %.

**Table 10 — Ferritic and martensitic stainless and heat resisting steels in the form of forgings: chemical composition, heat treatment and mechanical property requirements**

Steel <sup>b</sup>	Chemical composition (maximum unless range stated) %									Softened condition HB max.	Heat treatment condition	LRS mm	Heat treatment °C	R <sub>m</sub> aN/mm <sup>2</sup>	R <sub>e</sub> min. aN/mm <sup>2</sup>	A min. on 5.65√S <sub>0</sub>	Impact		R <sub>p</sub> 0.2 aN/mm <sup>2</sup>	HB
	C	Si	Mn	P	S	Cr	Mo	Ni	Se								Izod min. ft · lb	KVC min. J		
<b>Ferritic steels</b>																				
403S17	0.08	1.0	1.0	0.040	0.030	12.0–14.0	–	0.50	–	170	–	150	700–780 <sup>d</sup>	≥ 420	280	20	–	–	245	≤ 170
430S17	0.08	1.0	1.0	0.040	0.030	16.0–18.0	–	0.50	–	170	–	63	750–820 <sup>e</sup>	≥ 430	280	20	–	–	245	≤ 170
<b>Martensitic steels</b>																				
410S21	0.09–0.15	1.0	1.0	0.040	0.030	11.5–13.5	–	1.00	–	207	P	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	550–700	370	20	} ≤ 63 mm 40 > 63 mm 25	–	340	152–207
											R	63	600–700 <sup>g</sup> 950–1020 <sup>f</sup>	700–850	525	15		25	–	495
416S21	0.09–0.15	1.0	1.5	0.060	0.15–0.35	11.5–13.5	0.60	1.00	–	207	P	150	650–750 <sup>g</sup>	550–700	370	15	} ≤ 63 mm 25 > 63 mm 20	–	340	152–207
											R	63	600–700 <sup>g</sup>	700–850	525	11		20	–	495
416S29	0.14–0.20	1.0	1.5	0.060	0.15–0.35	11.5–13.5	0.60	1.00	–	217	R	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	700–850	525	11	} ≤ 63 mm 25 > 63 mm 20	–	495	201–255
											S	29	600–700 <sup>g</sup>	775–925	585	10		10	–	555
416S37	0.20–0.28	1.0	1.5	0.060	0.15–0.35	12.0–14.0	0.60	1.00	–	229	R	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	700–850	525	11	} ≤ 63 mm 25 > 63 mm 20	–	495	201–255
											S	150	600–700 <sup>g</sup>	775–925	585	10		10	–	555
416S41	0.09–0.15	1.0	1.5	0.060	0.060	11.5–13.5	0.60	1.00	0.15–0.35	179	P	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	555–700	370	15	} ≤ 63 mm 25 > 63 mm 20	–	340	152–207
											R	63	600–700 <sup>g</sup>	700–850	525	11		20	–	495
420S29	0.14–0.20	1.0	1.0	0.040	0.030	11.5–13.5	–	1.00	–	217	R	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	700–850	525	15	} ≤ 63 mm 25 > 63 mm 20	–	495	201–255
											S	29	600–700 <sup>g</sup>	775–925	585	13		20	–	555
420S37	0.20–0.28	1.0	1.0	0.040	0.030	12.0–14.0	–	1.00	–	229	R	150	950–1020 <sup>f</sup> 650–750 <sup>g</sup>	700–850	525	15	} ≤ 63 mm 25 > 63 mm 20	–	495	201–255
											S	150	600–700 <sup>g</sup>	775–925	585	13		20	–	555
431S29	0.12–0.20	1.0	1.0	0.040	0.030	15.0–18.0	–	2.0–3.0	–	277	T	150	950–1020 <sup>f</sup> 550–650 <sup>gh</sup>	850–1000	680	11	} ≤ 63 mm 25 > 63 mm 15	–	635	248–302

<sup>a</sup> 1 N/mm<sup>2</sup> = 1 MPa.

<sup>b</sup> All the steels are category 1.

<sup>c</sup> When specifically ordered.

<sup>d</sup> Air cooled or furnace cooled.

<sup>e</sup> Cooled freely in air.

<sup>f</sup> Oil or air hardened.

<sup>g</sup> Tempered.

<sup>h</sup> When 0.2 % proof stress is specified, it is recommended that a double tempering treatment be used:

a) 640 °C to 680 °C followed by

b) 590 °C to 610 °C



**Table 11 — Austenitic stainless and heat resisting steels in the form of forgings and the heat resisting steel 310S31 in all product forms: chemical composition, softening treatment and mechanical property requirements**

Steel <sup>b</sup>	Chemical composition (maximum unless range stated)									Softening temperature °C	Maximum section mm	$R_m$ min. <sup>a</sup> N/mm <sup>2</sup>	A min. on $5.65\sqrt{S_0}$	<sup>c</sup> $R_{p0.2}$ N/mm <sup>2</sup>	<sup>c</sup> $R_{p1.0}$ N/mm <sup>2</sup>	Sensitization period (see 1.16.6) min	HB max. <sup>d</sup>
	C	Si	Mn	P	S	Cr	Mo	Ni	Others								
<b>Austenitic steels</b>																	
302S31	0.12	1.0	2.0	0.045	0.030	17.0–19.0	–	8.0–10.0	–	1000–1100	160	510	40	190	225	–	183
304S11	0.030	1.0	2.0	0.045	0.030	17.0–19.0	–	9.0–12.0	–	1000–1100	160	480	40	180	215	30	183
304S15	0.06	1.0	2.0	0.045	0.030	17.5–19.0	–	8.0–11.0	–	1000–1100	160	480	40	195	230	15	183
304S31	0.07	1.0	2.0	0.045	0.030	17.0–19.0	–	8.0–11.0	–	1000–1100	160	490	40	195	230	15	183
321S31	0.08	1.0	2.0	0.045	0.030	17.0–19.0	–	9.0–12.0	Ti 5C–0.80	1000–1100	160	510	35	200	235	30	183
347S31	0.08	1.0	2.0	0.045	0.030	17.0–19.0	–	9.0–12.0	Nb 10C–1.00	1000–1100	160	510	30	205	240	30	183
316S11	0.030	1.0	2.0	0.045	0.030	16.5–18.5	2.00–2.50	11.0–14.0	–	1000–1100	160	490	40	190	225	30	183
316S13	0.030	1.0	2.0	0.045	0.030	16.5–18.5	2.50–3.00	11.5–14.5	–	1000–1100	160	490	40	190	225	30	183
316S31	0.07	1.0	2.0	0.045	0.030	16.5–18.5	2.00–2.50	10.5–13.5	–	1000–1100	160	510	40	205	240	15	183
316S33	0.07	1.0	2.0	0.045	0.030	16.5–18.5	2.50–3.00	11.0–14.0	–	1000–1100	160	510	40	205	240	15	183
320S31	0.08	1.0	2.0	0.045	0.030	16.5–18.5	2.00–2.50	11.0–14.0	Ti 5C–0.80	1000–1100	160	510	35	210	245	30	183
310S31	0.15	1.5	2.0	0.045	0.030	24.0–26.0	–	19.0–22.0	–	1000–1100	160	510	40	205	240	–	207
303S31	0.12	1.0	2.0	0.060	0.15–0.35	17.0–19.0	1.00 <sup>e</sup>	8.0–10.0	–	1000–1100	160	510	40	190	225	–	183
303S42	0.12	1.0	2.0	0.060	0.060	17.0–19.0	1.00 <sup>e</sup>	8.0–10.0	Se 0.15–0.35	1000–1100	160	510	40	190	225	–	183
325S31	0.12	1.0	2.0	0.045	0.15–0.35	17.0–19.0	–	8.0–11.0	Ti 5C–0.90	1000–1100	160	510	35	200	235	30	183

<sup>a</sup> 1 N/mm<sup>2</sup> = 1 MPa.  
<sup>b</sup> All the steels are category 1.  
<sup>c</sup> When specifically ordered.  
<sup>d</sup> Straightening by reeling or cold rectification of austenitic steels can increase the surface hardness above the specified maximum.  
<sup>e</sup> Optional addition.

## Section 6. Specific requirements for sizes and tolerances

### 6.1 Sizes

#### 6.1.1 Billets for forging

Billets for forging shall be supplied in accordance with the nominal sizes given in Table 12.

#### 6.1.2 Black bar

The sizes of bars shall be selected from BS 6722.

NOTE Sizes other than those in BS 6722 may be available.

### 6.2 Mass/unit length tolerances

Billets for forging shall be supplied in accordance with Table 12.

### 6.3 Dimensional tolerances

#### 6.3.1 Black bar

Tolerances shall be in accordance with Table 13 to Table 15.

#### 6.3.2 Drop and press forgings and upset forgings made on horizontal forging machines

Drop and press forgings and upset forgings made on horizontal forging machines shall conform to BS 4114 unless otherwise agreed between the purchaser and the supplier.

### 6.4 Straightness

#### 6.4.1 Billets and bars for machining

Billets and bars for machining shall be straightened to within 2 mm in any 1 m length.

#### 6.4.2 Billets and bars for forging

Billets and bars for forging shall be straight to within 1/250 in any unit length.

### 6.5 Length

The standard tolerance on length for random length bars shall be 600 mm.

NOTE Closer tolerances may be agreed between the purchaser and the supplier.

**Table 12 — Billets (other than stainless steel) for forging: standard mass per metre and tolerances**

Round cornered square billets <sup>a</sup>			Round billets		
Nominal size <sup>b</sup> across flats mm	Standard mass kg/m	Permissible variations on mass %	Nominal size <sup>c</sup> diameter mm	Standard mass kg/m	Permissible variations on mass %
50	19.3	±2.5 or, when a minimum mass is specified	76	35.6	±2.5 or, when a minimum mass is specified,
51	20.1		80	39.5	
55	23.3		85	44.5	
57	25.0		90	49.9	
60	27.7		95	55.6	
63	30.6		100	61.7	
65	32.7		105	68.0	
67	34.6		110	74.6	
70	37.7		115	81.5	
73	41.0		120	88.8	
75	43.2		125	96.3	
76	44.4		130	104.2	
80	49.1		135	112.4	
83	52.9		140	120.8	
85	55.5	145	129.6		
86	56.8	+5. -0, when a maximum mass is specified,	150	138.7	+5. -0, when a maximum mass is specified,
90	62.2		155	148.1	
92	65.2		160	157.8	
95	69.5	+0. -5	165	167.8	+0. -5
98	74.0		170	178.2	
100	77.0		175	188.8	
105	84.9		180	199.8	
108	89.8		185	211.0	
110	93.1		190	222.6	
115	101.7		195	234.4	
120	110.2		200	246.6	
127	124.0		205	259.1	
130	129.7		210	271.9	
135	140.3	215	285.0		
140	151.3	220	298.4		

<sup>a</sup> When round cornered square billets are supplied to the mass/unit length requirements of this table, it should be realized that, because of the differences in roll pass design, i.e. corner radius and angle between sides, which may exist from mill to mill, there may be slight differences in the actual size of billet of the same standard mass.

<sup>b</sup> These are preferred sizes for round cornered square billets.

<sup>c</sup> For other sizes of round billets, standard masses shall be calculated using the formula:

$$\text{Standard mass (in kg/m)} = \frac{\pi \times (\text{nominal size, in mm})^2 \times 0.00785}{4}$$

Table 13 — Tolerances for hot rolled round and square bar and rough turned rounds

Size		Permitted variation					
		General applications				Special applications	
		Primary-rolled round material		Re-rolled material		Re-rolled material	
		Diameter	Out of section <sup>a</sup>	Diameter or width across flats	Out of section <sup>a</sup>	Diameter or width across flats	Out of section <sup>a</sup>
mm	± mm	mm	± mm	mm	± mm	mm	
≤ 16	—	—	0.2	0.3	0.2	0.3	
> 16 ≤ 26	—	—	0.3	0.5	0.2	0.3	
> 26 ≤ 38	—	—	0.4	0.6	0.25	0.4	
> 38 ≤ 51	—	—	0.5	0.8	0.3	0.5	
> 51 ≤ 64	—	—	0.6	0.9	0.4	0.6	
> 64 ≤ 76	—	—	0.7	1.1	0.5	0.8	
> 76 ≤ 90	1.3	2.0	0.7	1.1			
> 90 ≤ 120	1.5	2.3	0.8	1.2			
> 120 ≤ 160	2.0	3.0					
> 160 ≤ 200	2.5	3.8					
> 200	3.0	4.5					

<sup>a</sup> In relation to Table 13, the definition of “out of section” is as follows:  
*Round bar.* The difference between the maximum and the minimum diameter of the bar measured at the same cross-section.  
*Square bar.* The difference between the two dimensions measured across the two pairs of opposing (parallel) sides at a common cross-section of the bar.

NOTE By agreement between purchaser and supplier, the tolerances may be all plus or all minus, e.g. the general applications tolerance for 16 mm round may be ±0.4 mm.

Table 14 — Tolerances for hot rolled hexagonal bar

Size		Permitted variation			
		General applications		Special applications	
		Re-rolled material		Re-rolled material	
		Width across flats	Out of section <sup>a</sup>	Width across flats	Out of section <sup>a</sup>
mm	± mm	mm	± mm	mm	
≤ 16	0.2	0.3	0.2	0.3	
> 16 ≤ 26	0.3	0.5	0.2	0.3	
> 26 ≤ 38	0.4	0.6	0.25	0.4	
> 38 ≤ 51	0.5	0.8	0.3	0.5	
> 51 ≤ 64	0.6	0.9	0.4	0.6	
> 64 ≤ 76	0.7	1.1	0.5	0.8	

<sup>a</sup> In relation to Table 14 the definition of “out of section” is as follows:  
*Hexagonal bar.* The difference between the least and the greatest dimensions measured across the three pairs of opposing (parallel) flats at a common cross-section of the bar.

NOTE By agreement between purchaser and supplier, the tolerances may be all plus or all minus, e.g. the general applications tolerance for 16 mm section may be ±0.4 mm.

**Table 15 — Tolerances for hot rolled flat bar**

Size  mm	Permitted variation	
	General applications ± mm	Special applications ± mm
<b>Width</b>		
≥ 10 ≤ 35	0.5	0.4
> 35 ≤ 75	0.8	0.6
> 75 ≤ 100	1.0	0.7
> 100 ≤ 125	1.3	0.9
> 125 ≤ 150	1.5	1.0
<b>Thickness</b>		
≤ 10	0.4	0.3
> 10 ≤ 20	0.5	0.3
> 20 ≤ 40	0.6	0.4
> 40 ≤ 60	0.8	0.5
> 60	1.0	0.7
NOTE By agreement between purchaser and supplier, the tolerances may be all plus or all minus, e.g. the standard tolerance on width for 35 mm wide flats may be ±1.0 mm.		

## **Annex A**

### **Hardenability curves for case-hardening steels**


This annex presents the hardenability data for the H grades specified in sections 3 and 4 in graphical form. This enables a pictorial assessment of the hardenability characteristics of a particular steel to be made and also facilitates the comparison of one H grade with another.

It is important that these graphs are not used for specification purposes. The values to be used are those specified in Table 7 (case-hardening steels). They should be selected as recommended in BS 4437.


A.1 Hardenability curves for case-hardening steels

A.1.1 Alloy steels

A.1.1.1 523H15

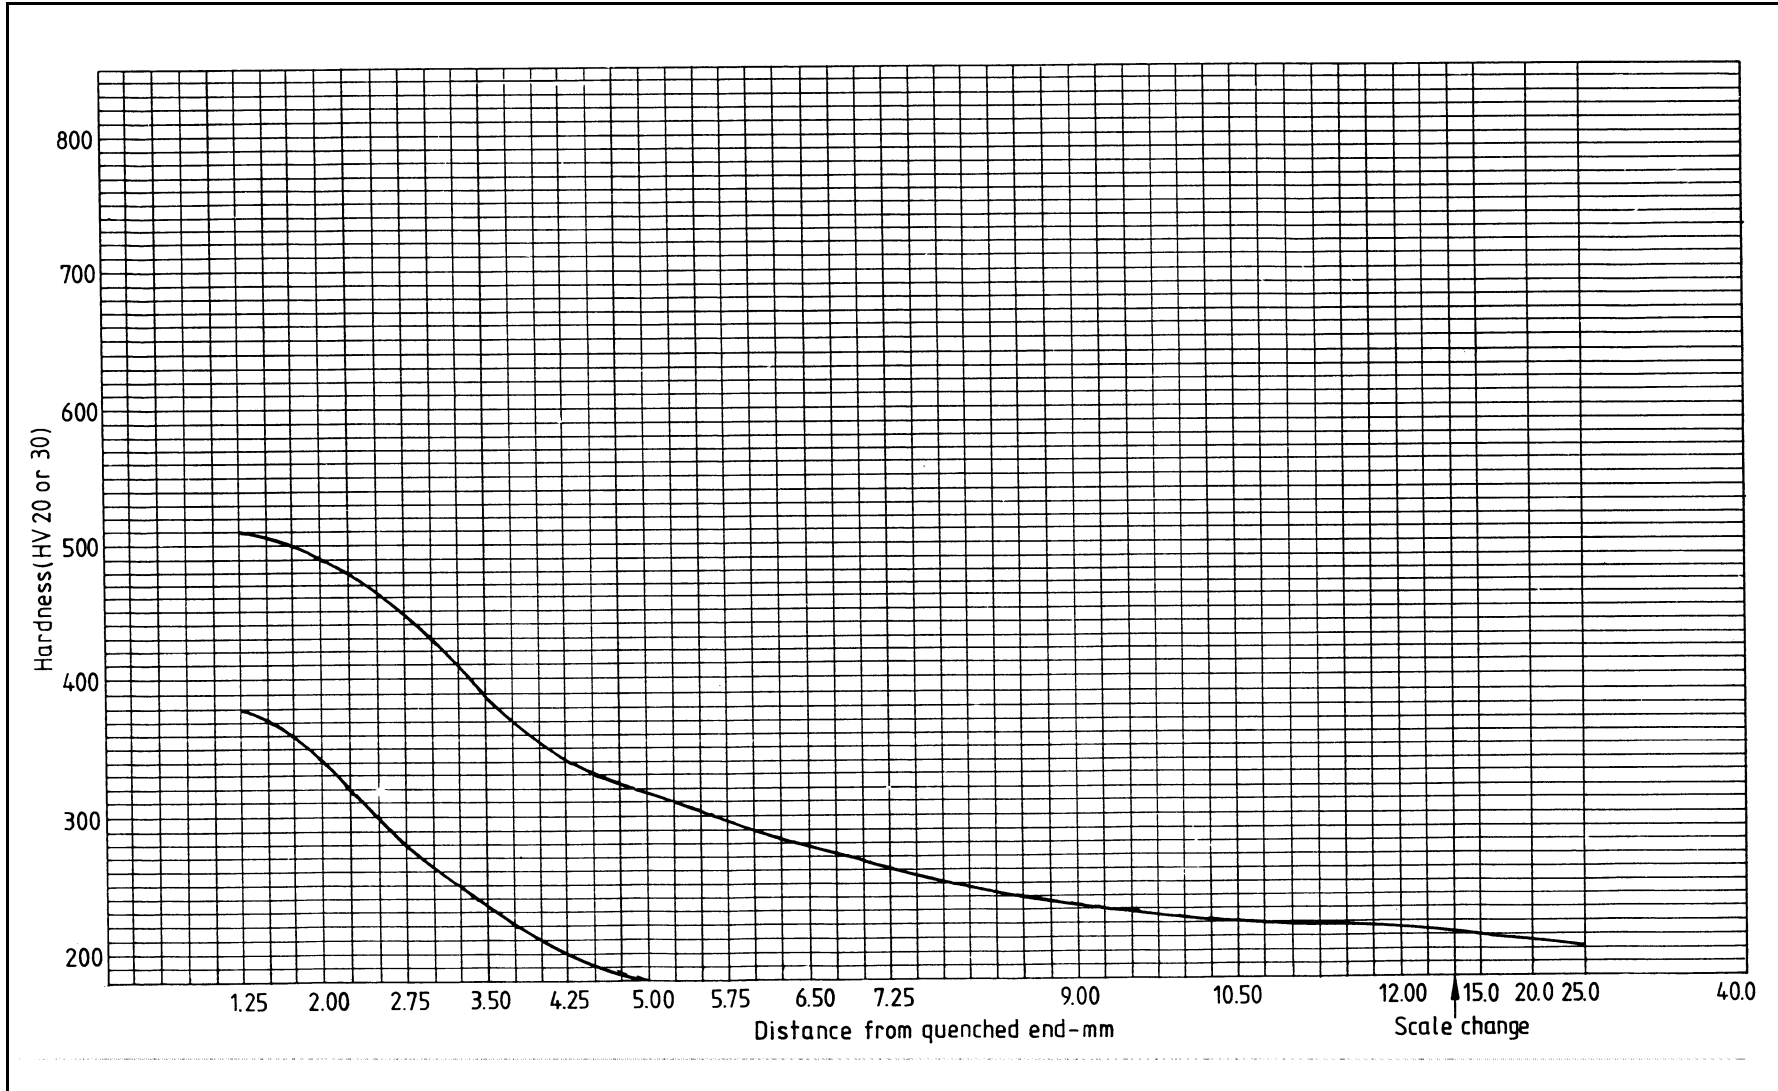


A.1.1.2 527H17

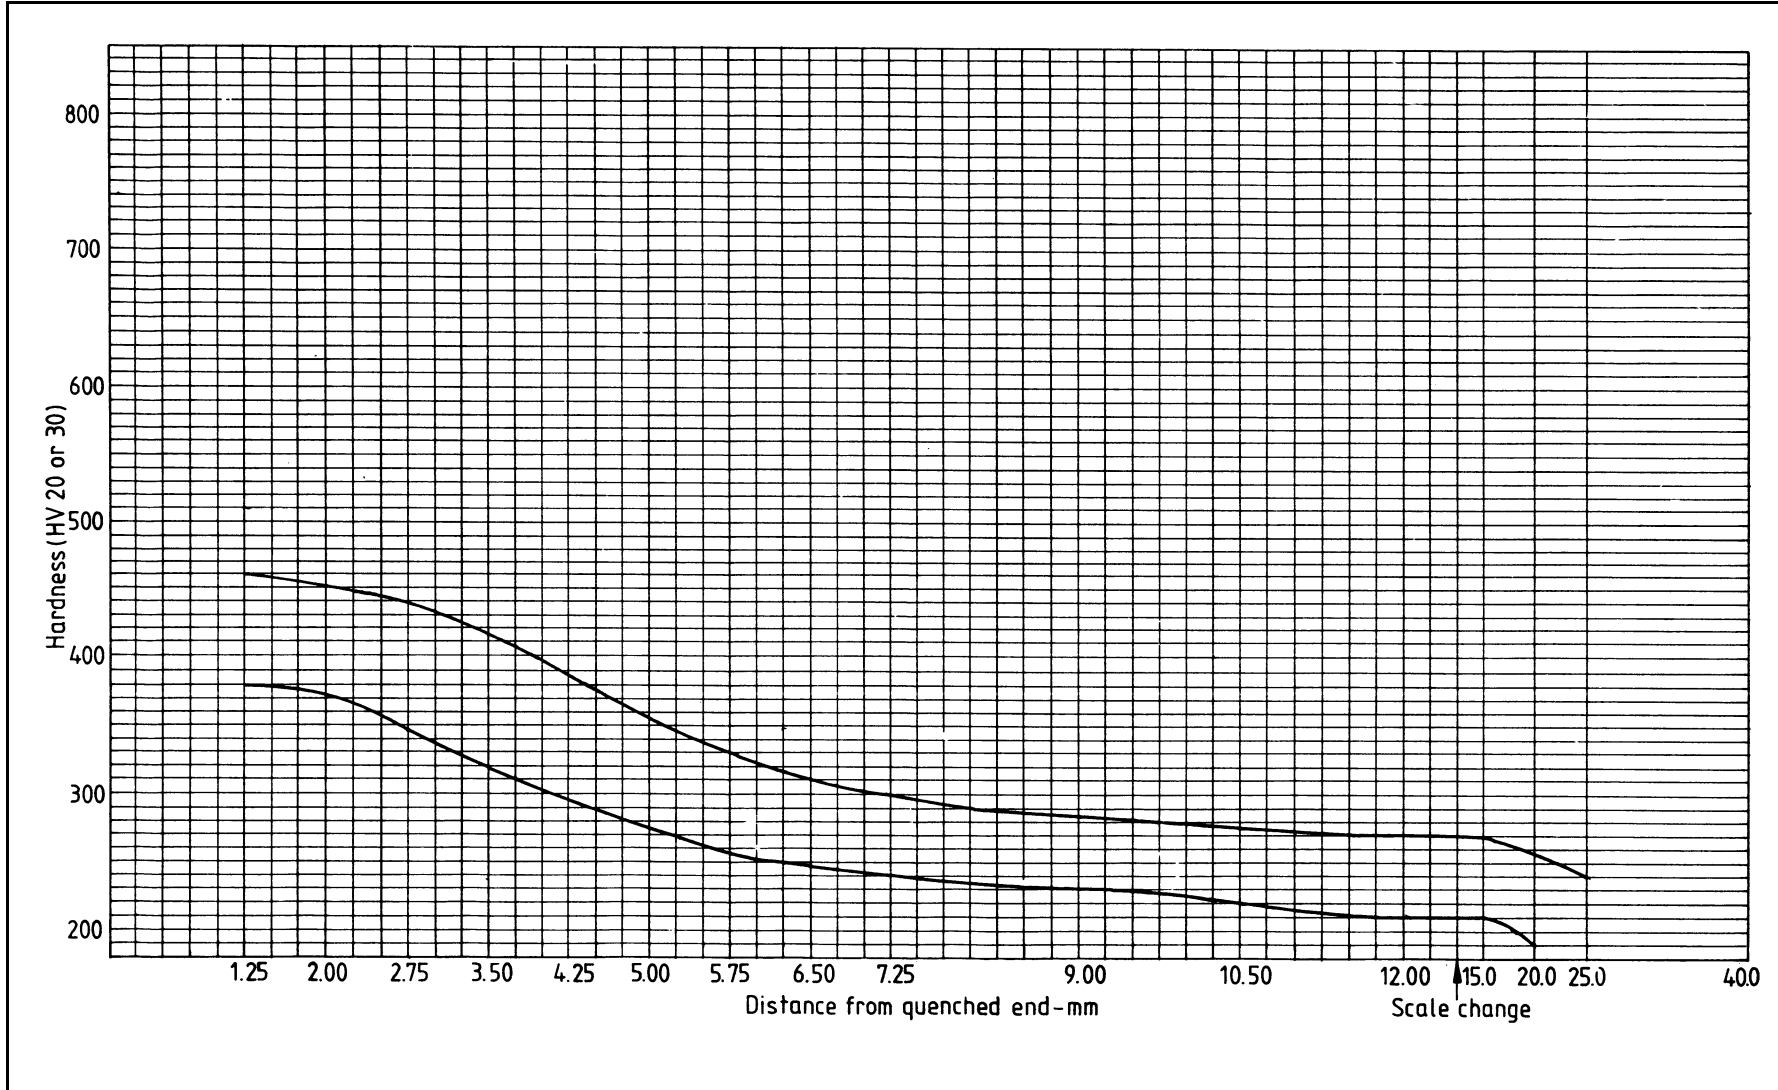





A.1.1.3 590H17

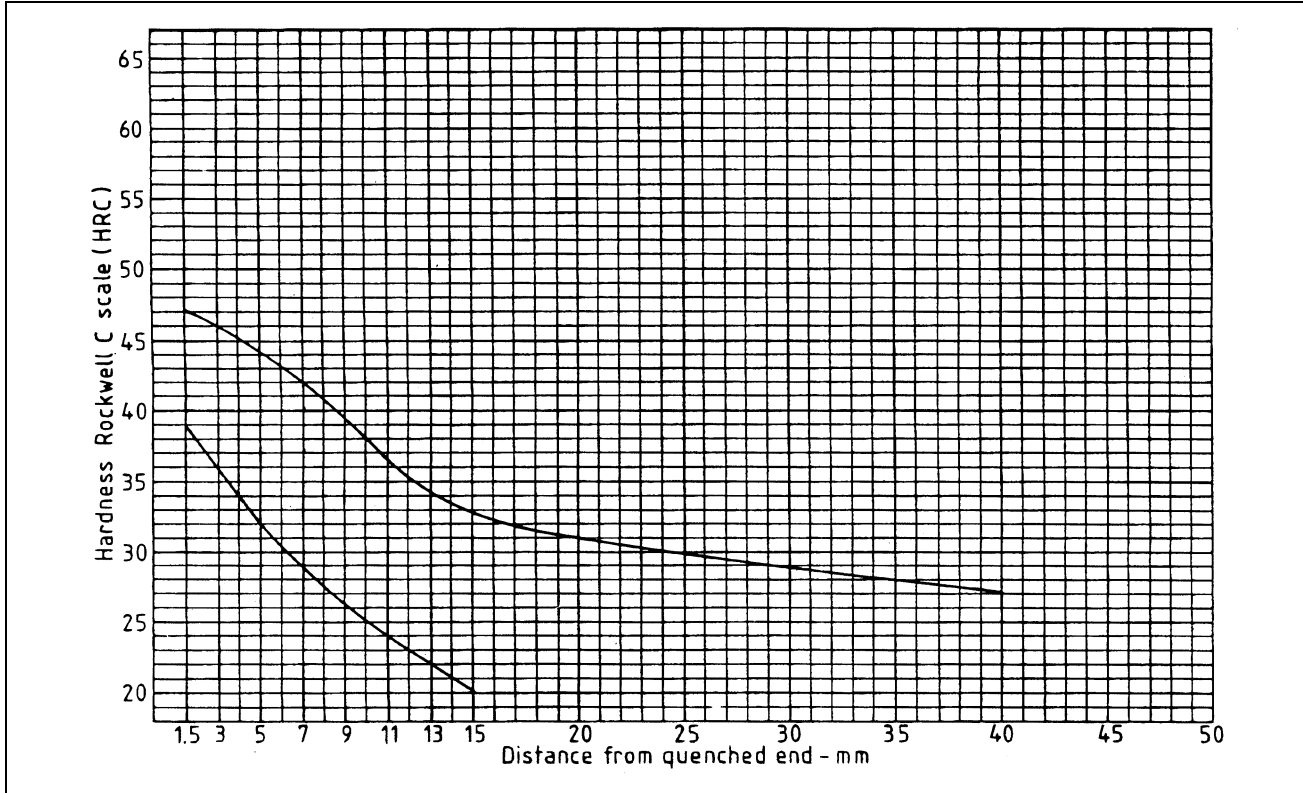


A.1.1.4 635H15

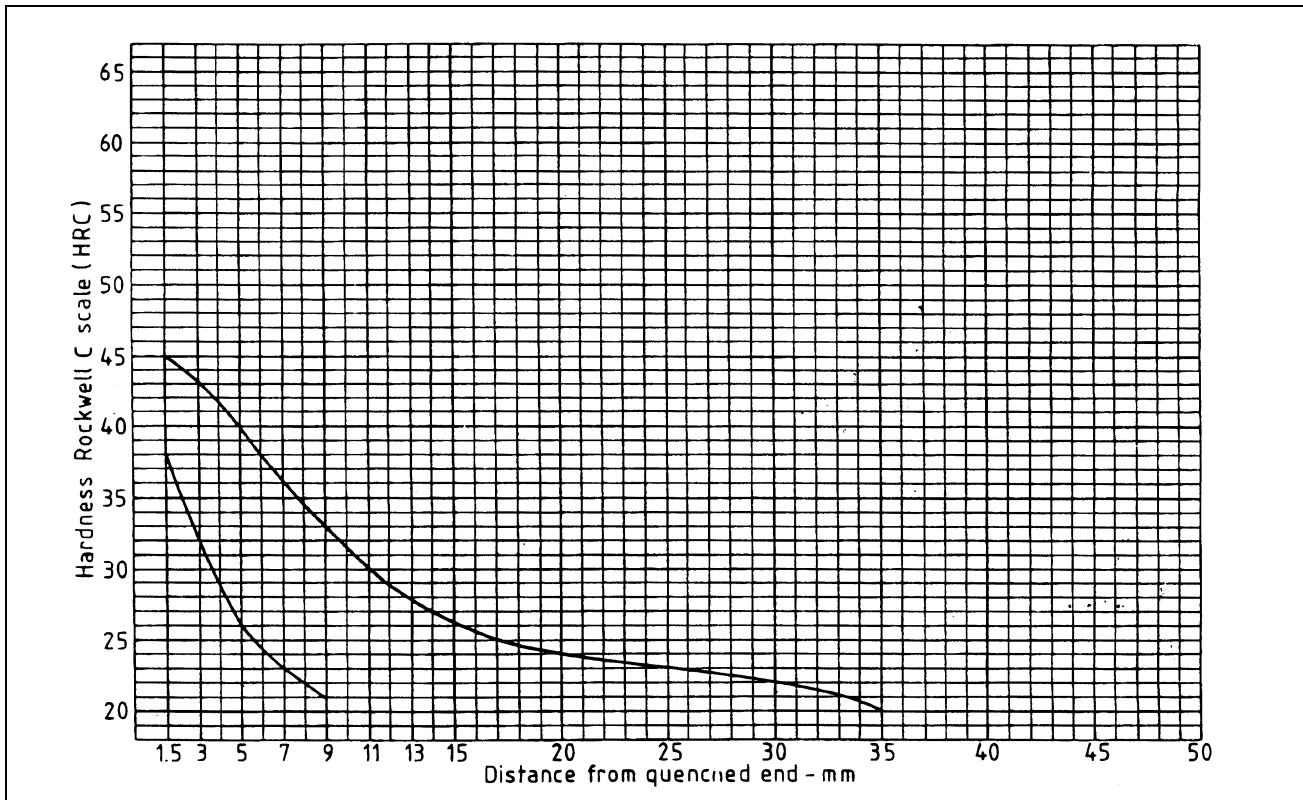


## A.1.1.5 637H17

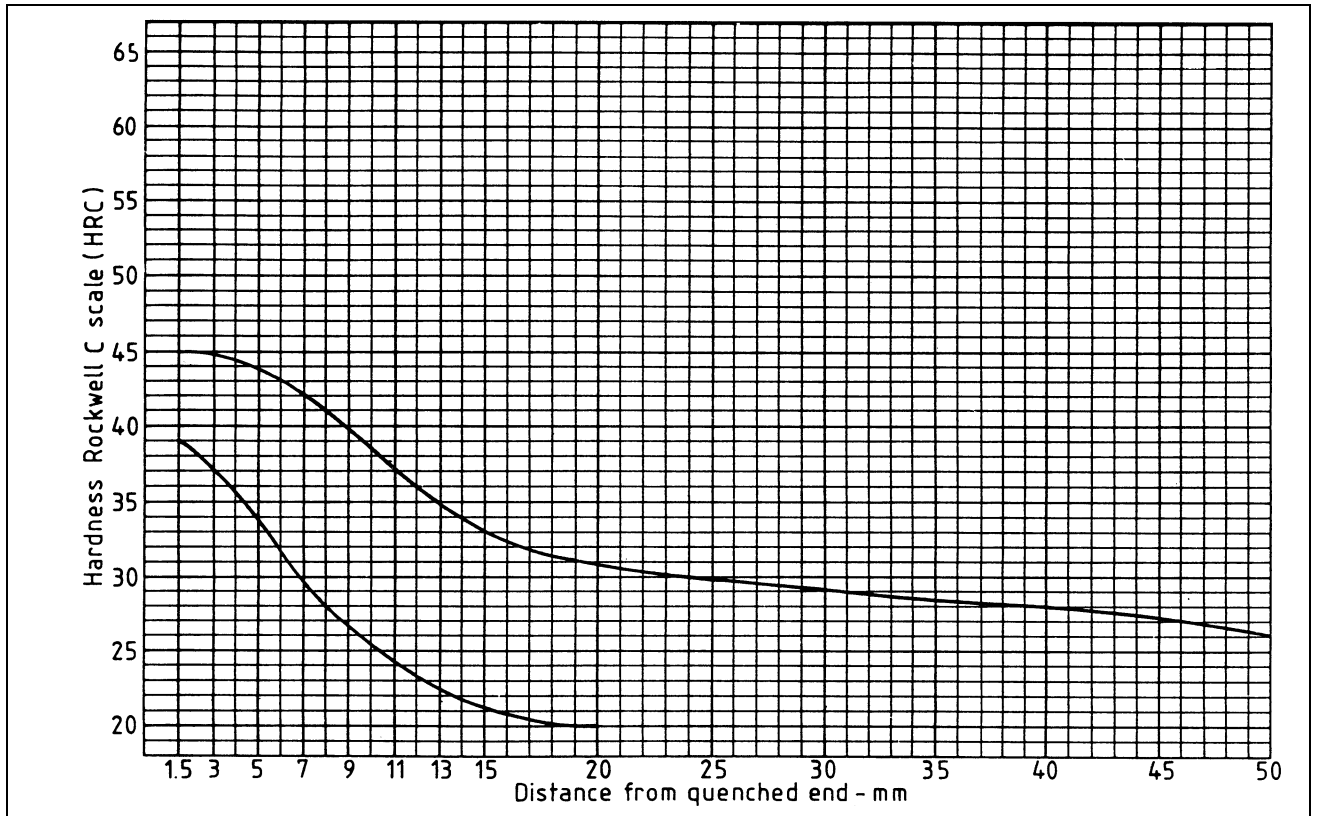


## A.1.1.6 655H13

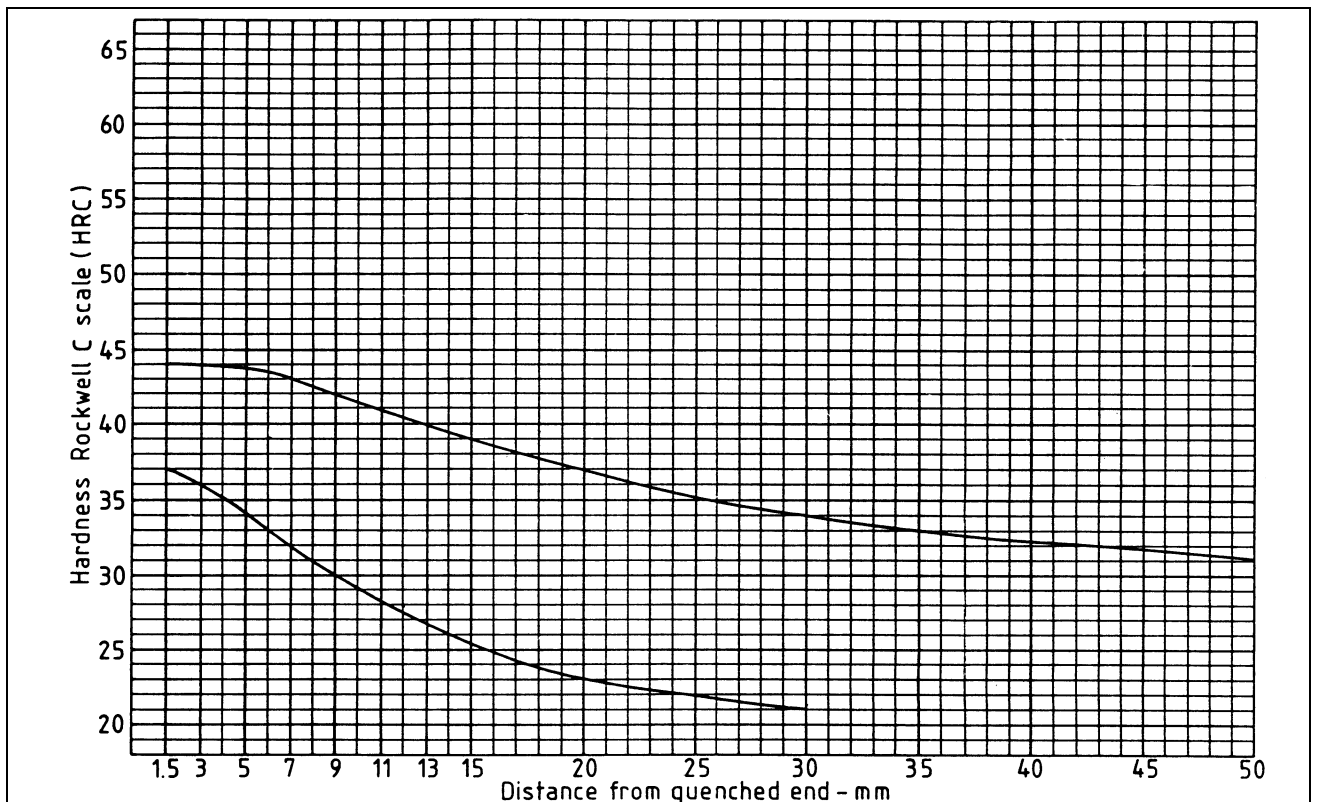


A.1.1.7 655H17

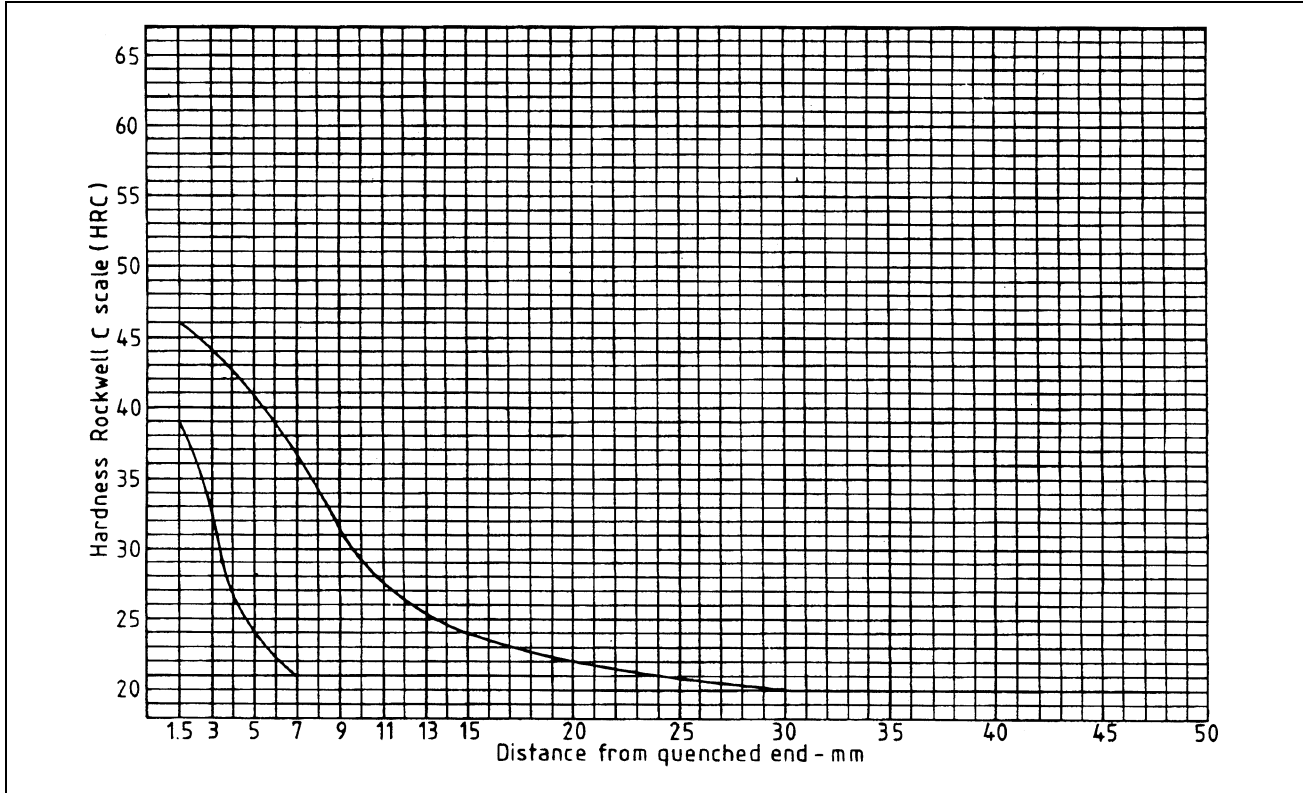


A.1.1.8 665H20

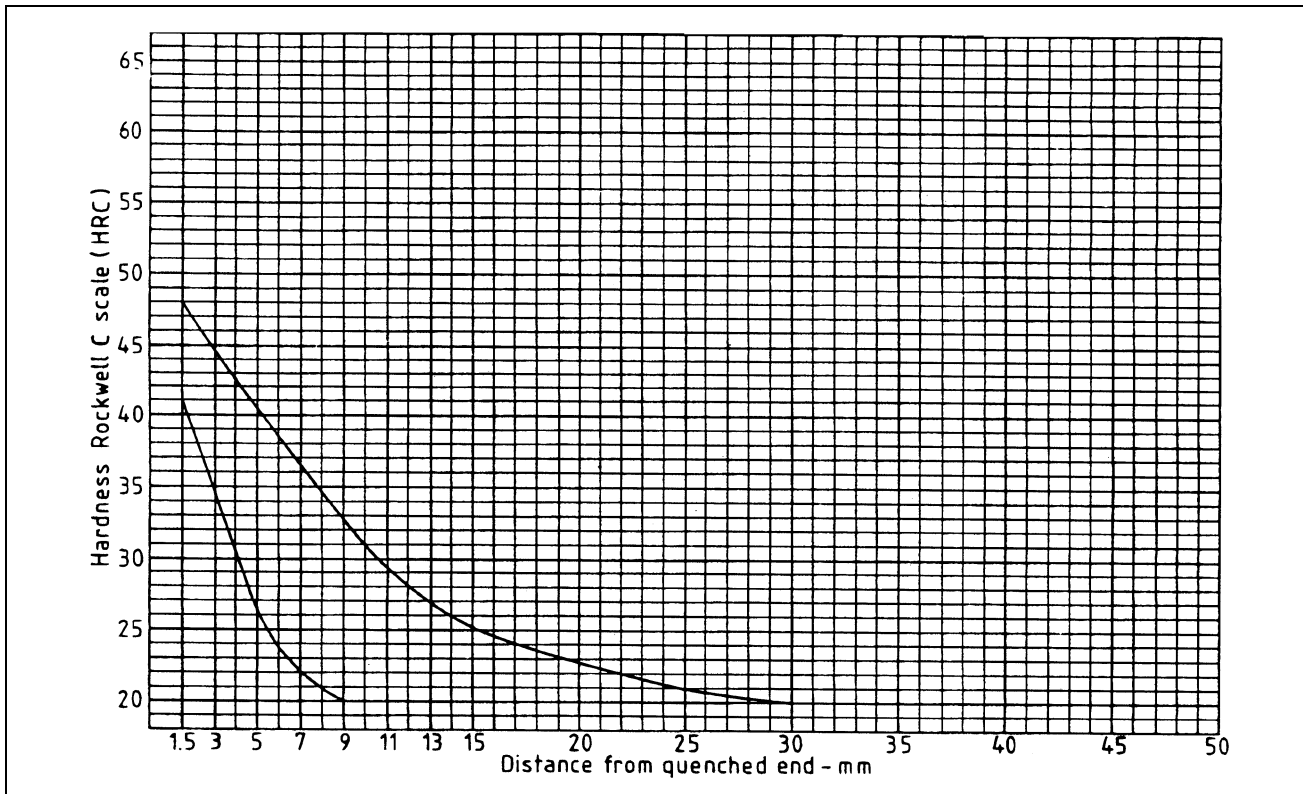


A.1.1.9 665H23

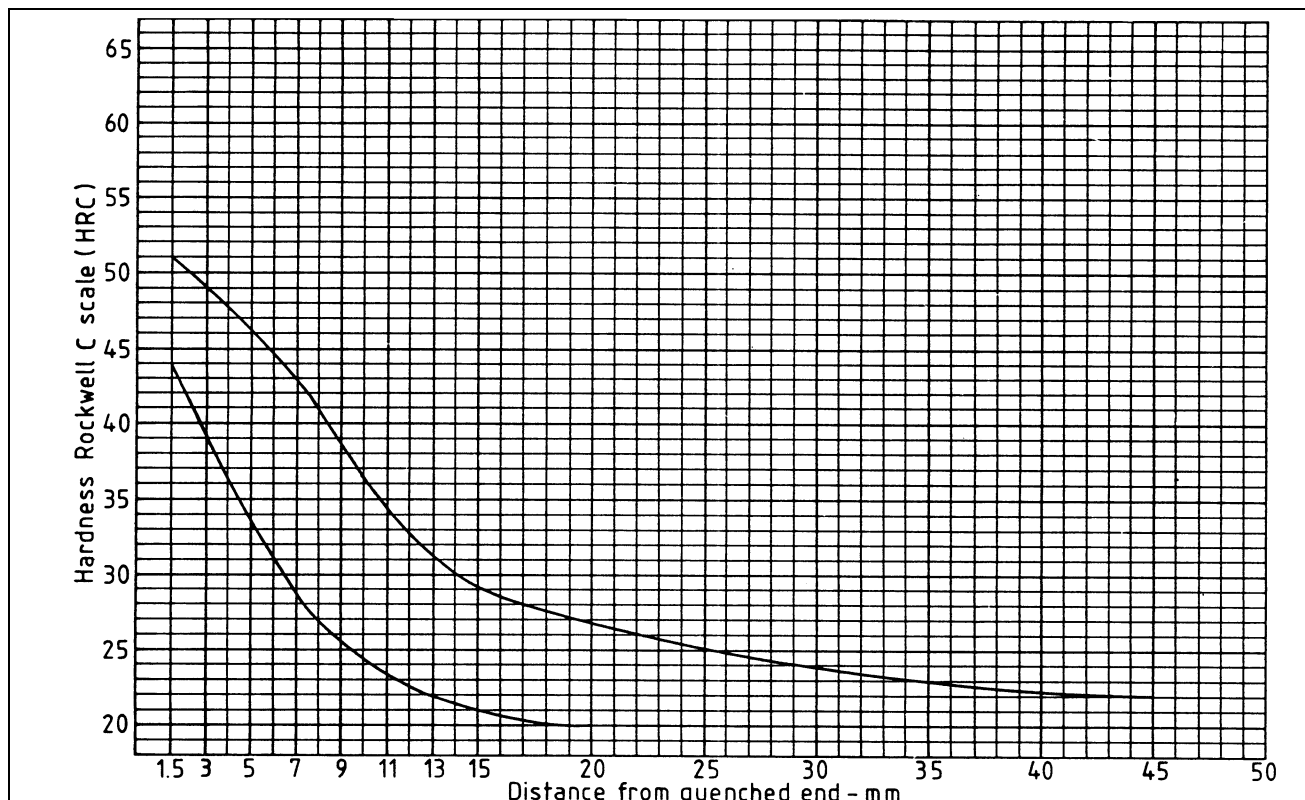


A.1.1.10 708H20

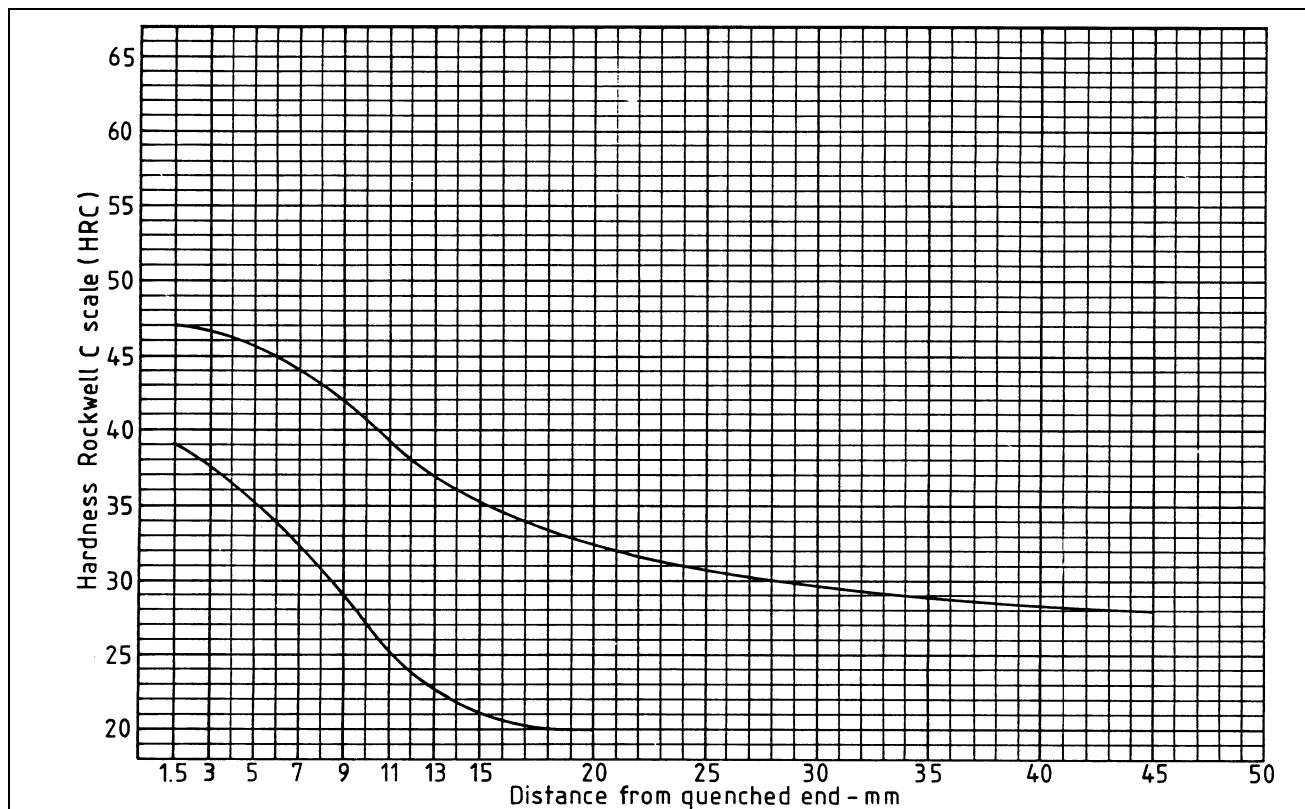


A.1.1.11 805H17

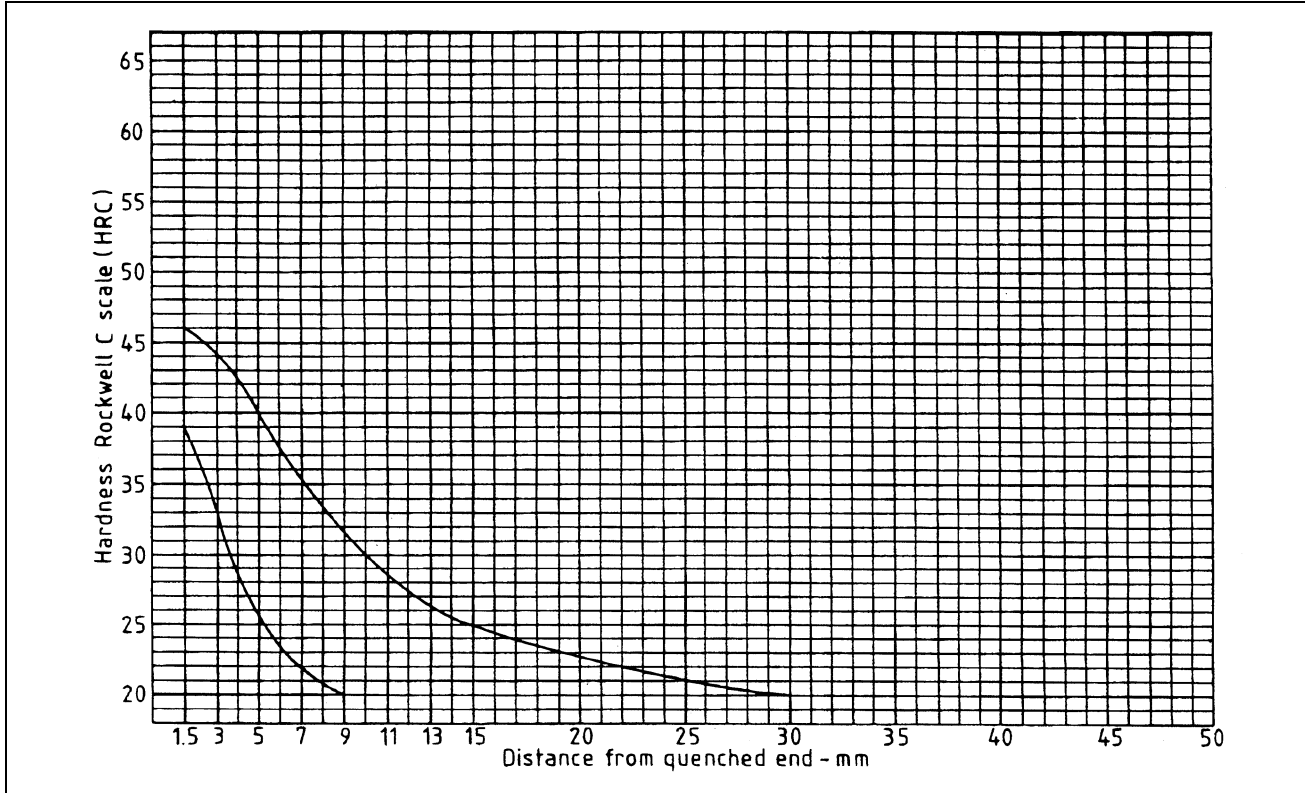


A.1.1.12 805H20

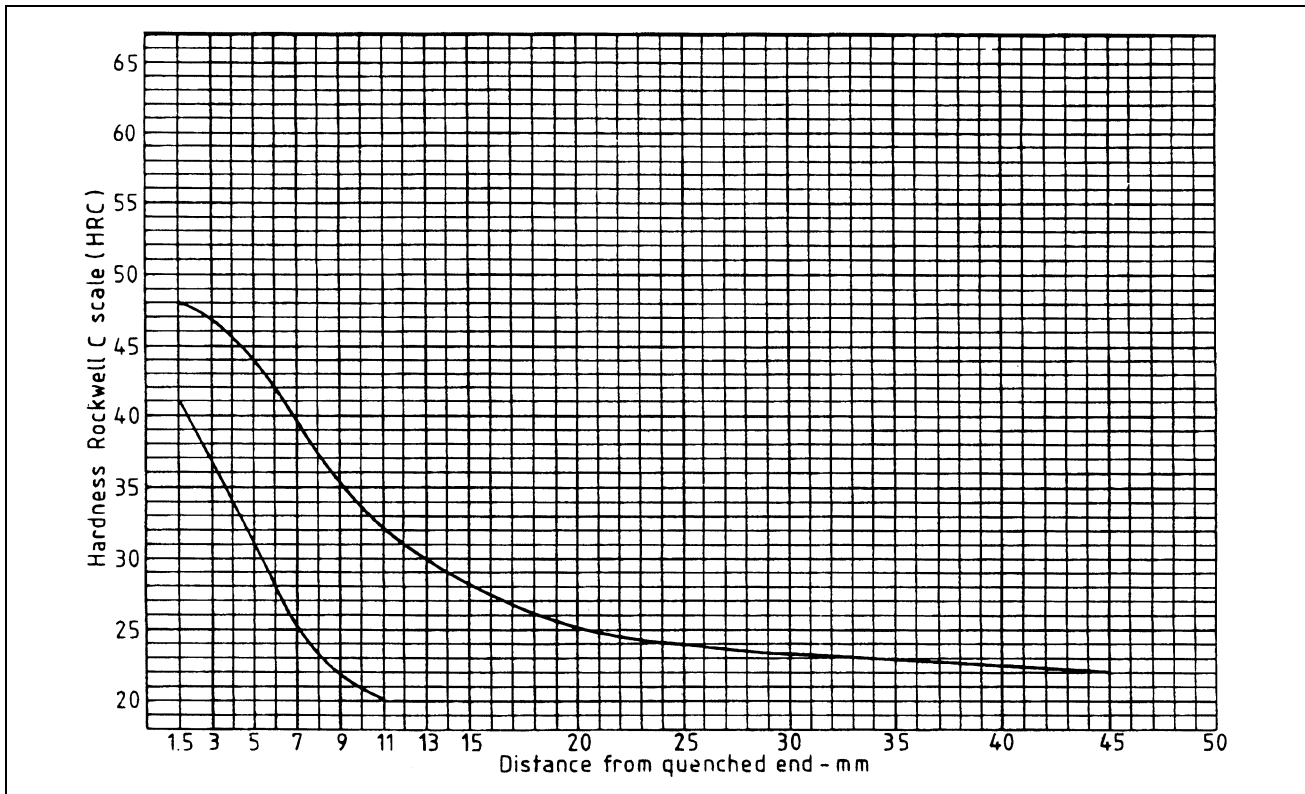


## A.1.1.13 805H22

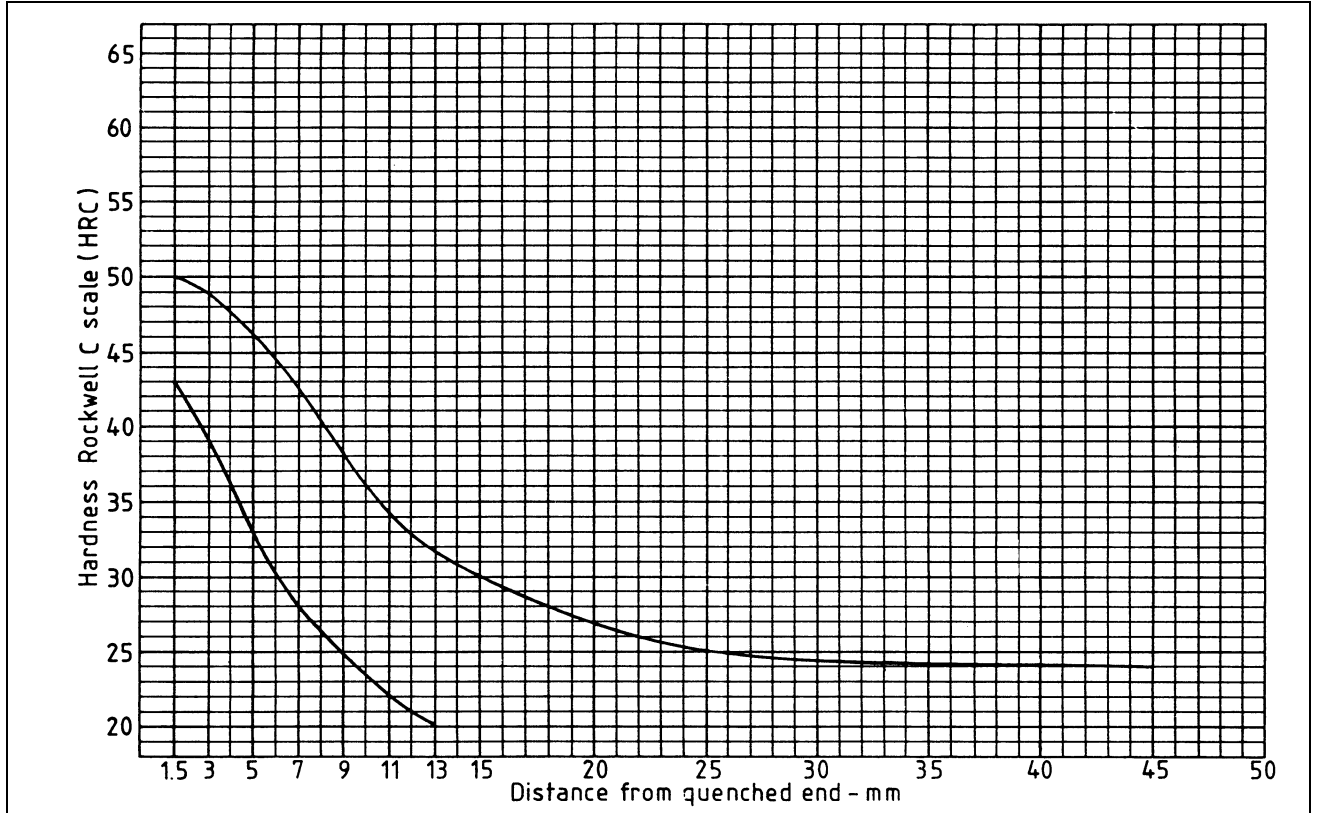


## A.1.1.14 808H17

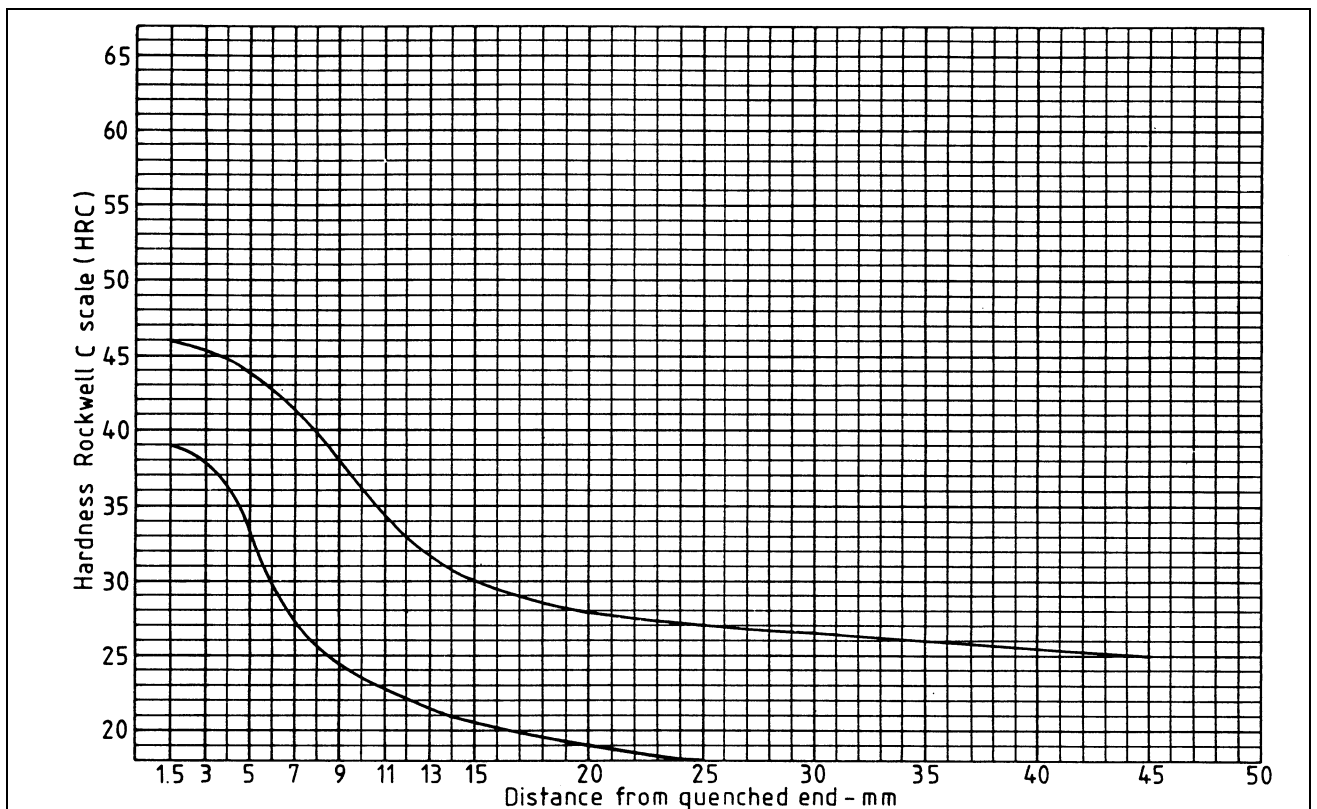


A.1.1.15 815H17

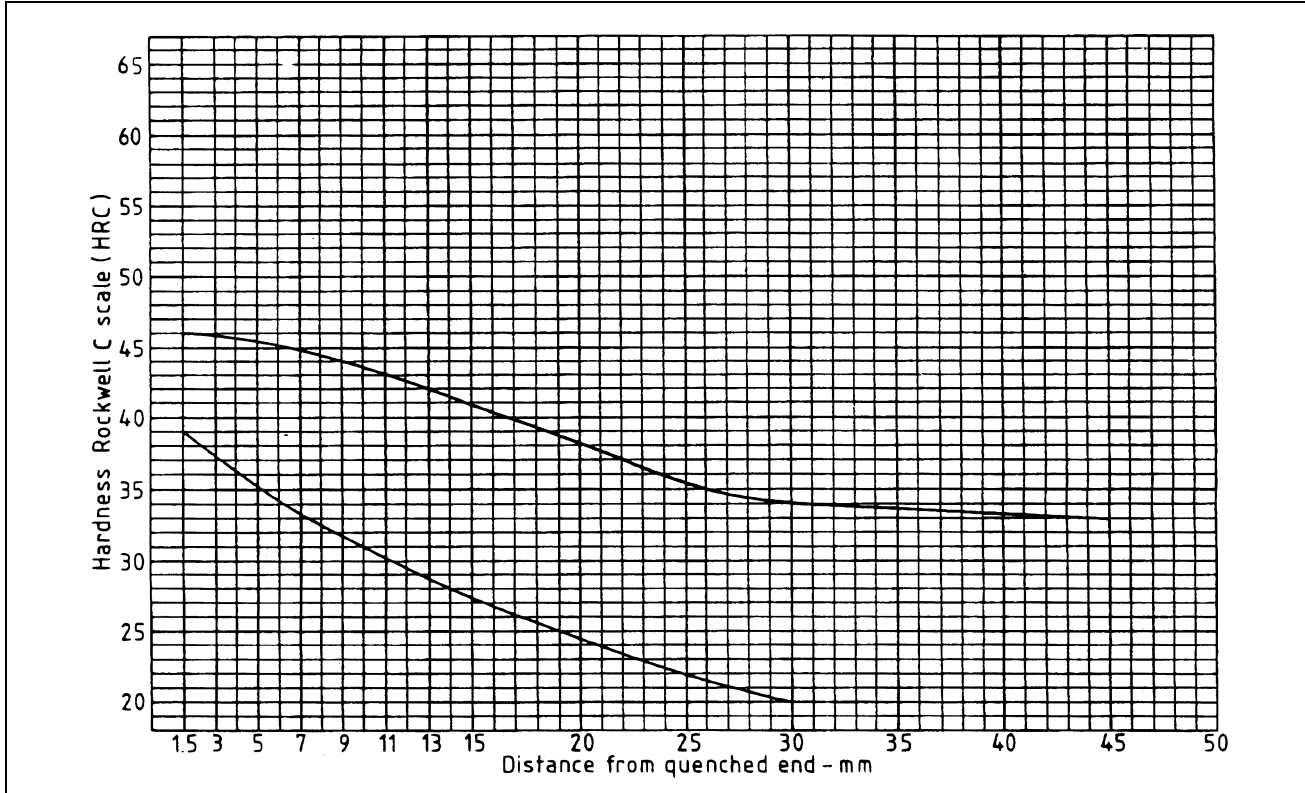


A.1.1.16 820H17

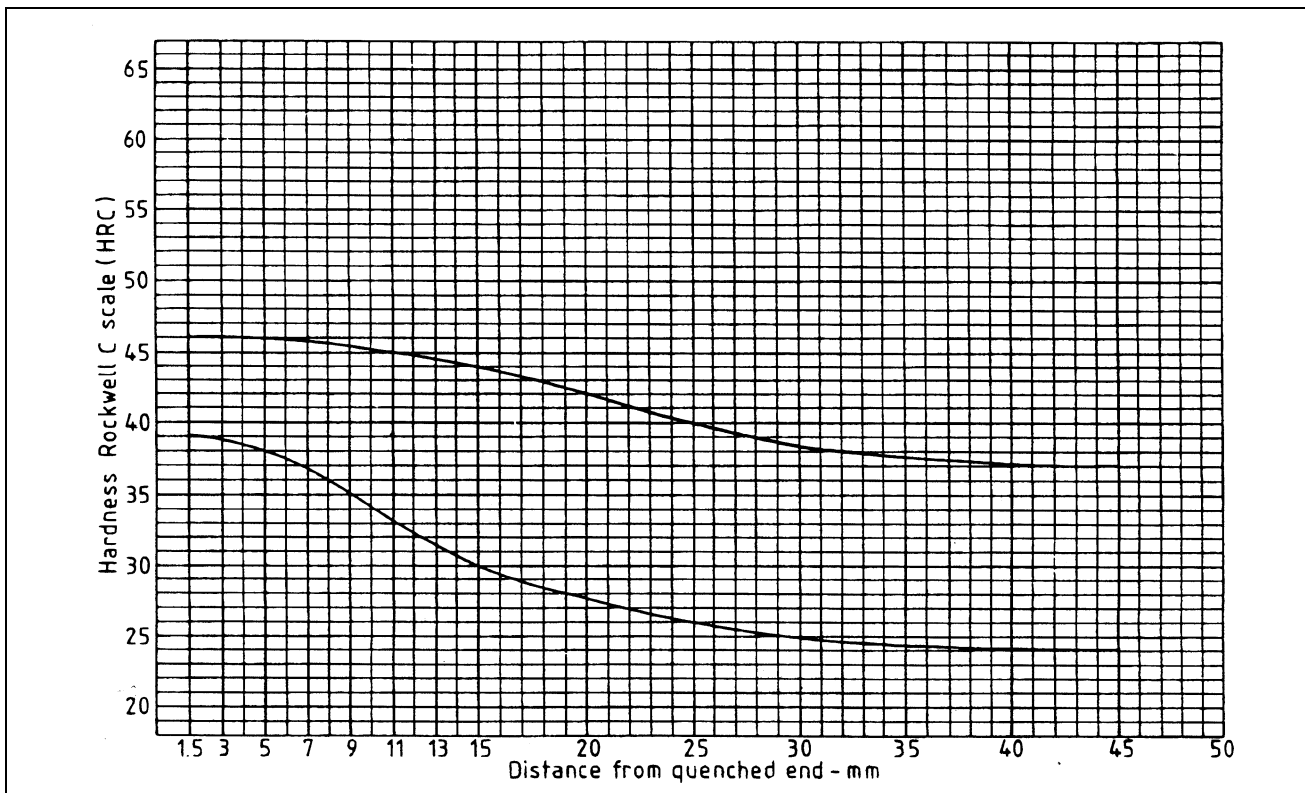

A.1.1.17 822H17

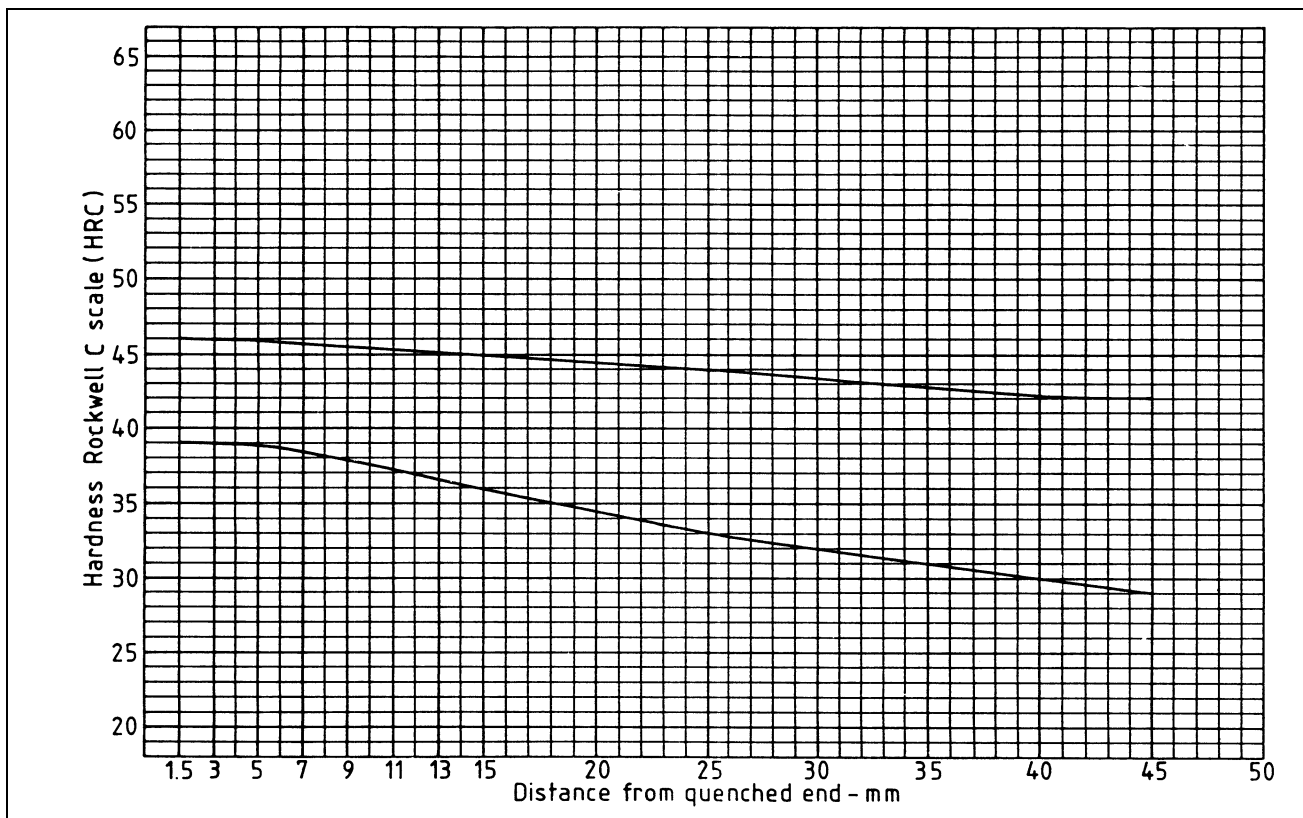


A.1.1.18 832H13

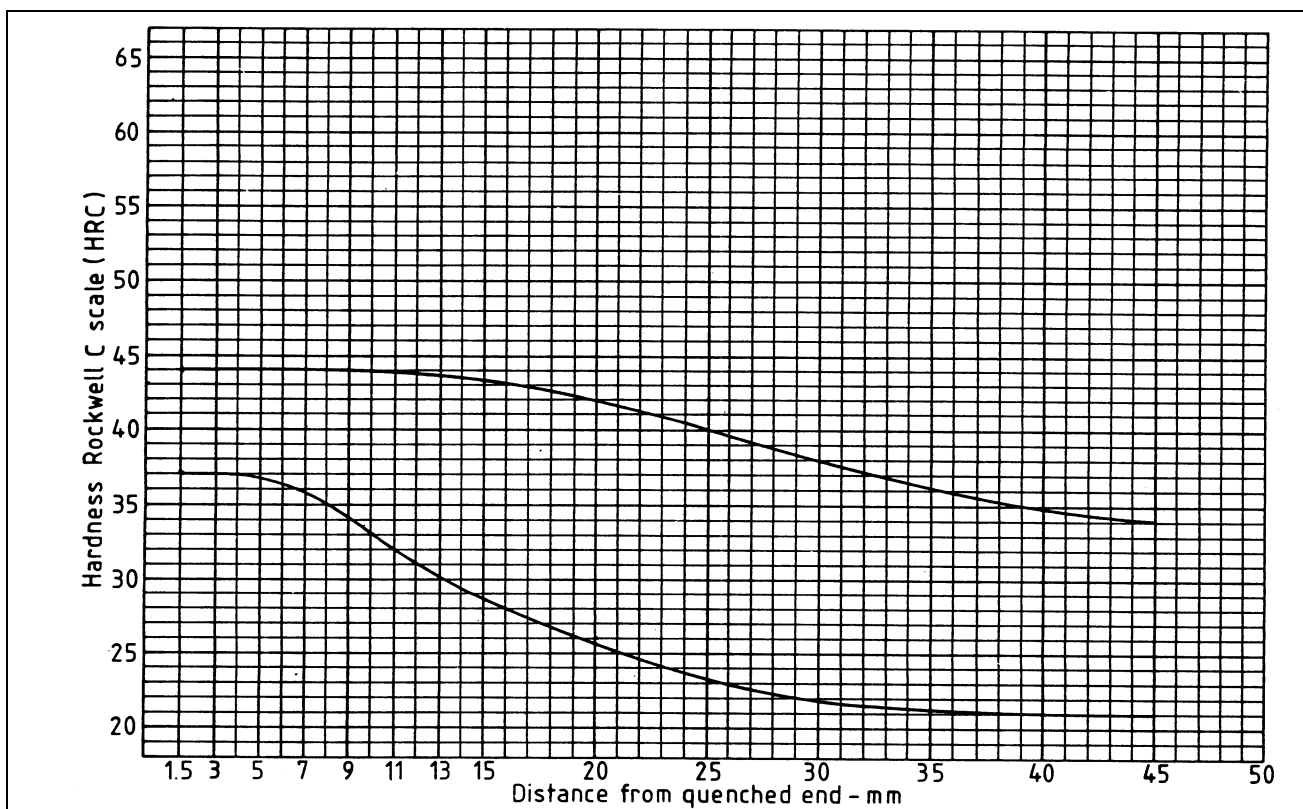



A.1.1.19 835H15

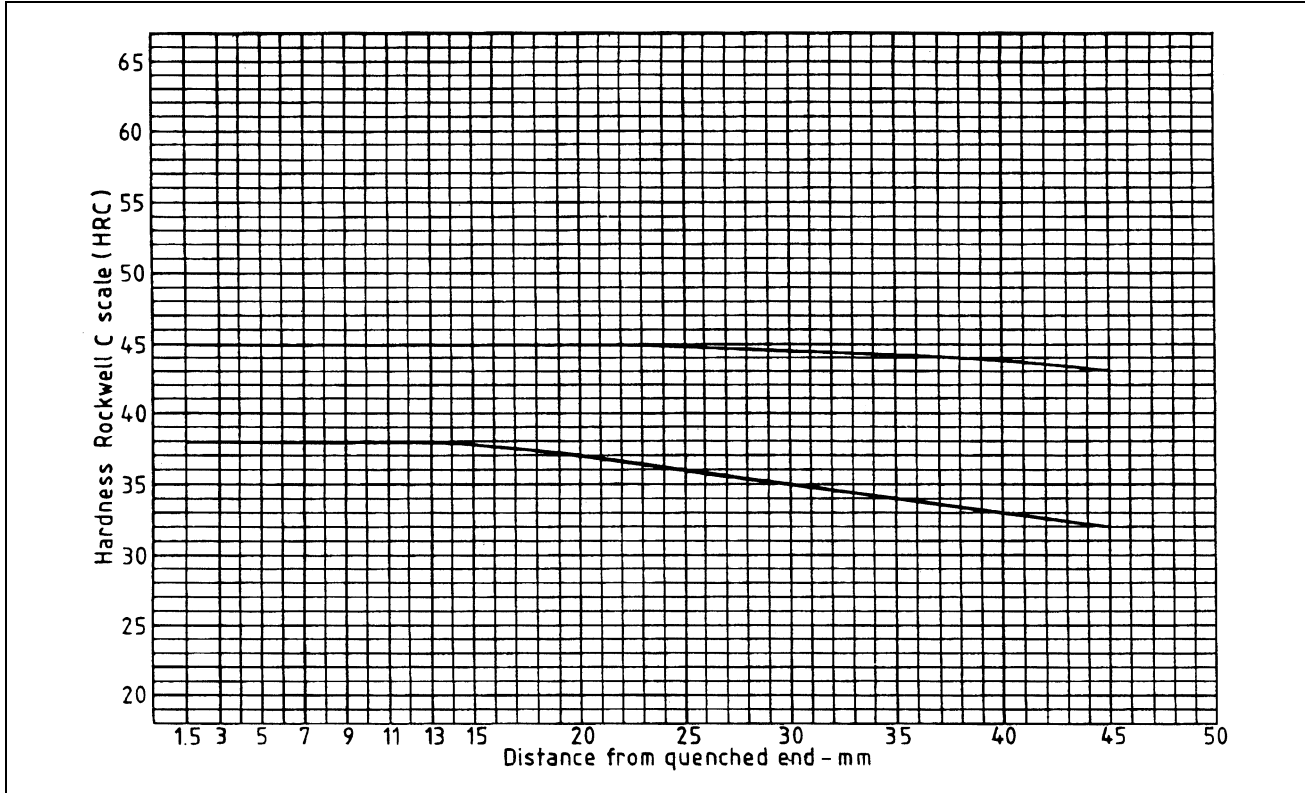

## **Annex B**

### **Deoxidation of steel (excluding stainless steels)**

#### **B.1 Carbon steel**

##### **B.1.1 General**

Carbon steel is manufactured in a variety of ways and certain features affect the ingot structure and relative uniformity of composition. The method of deoxidation is of particular importance in this respect and this should be recognized when considering the application of carbon steels.

There are three fundamental conditions of supply which are available within the following broad limits and the purchaser should state his requirements on the order.

Steel for forgings and drop forgings are required to be killed, see 1.7.3.1.

##### **B.1.2 Killed steel**

Killed steel can be provided over the whole carbon range. Generally silicon killed steel shall contain 0.10 % to 0.40 % silicon and if fine grained steel is required, combined silicon and aluminium deoxidation is generally used. Killed steels can also be supplied with lower silicon contents.

In these cases, other deoxidation practices, e.g. vacuum degassing and treatment with aluminium, can be used when the carbon content is less than 0.50 %.

A stabilized steel is usually an aluminium killed steel with sufficient aluminium to give minimal strain-ageing properties in the final product. Elements other than aluminium can be used to obtain these properties, but their use is not general.

##### **B.1.3 Semi-killed or balanced steel**

Semi-killed or balanced steels are generally only made in carbon ranges below 0.50 %, where the application may be less stringent than for killed steels. Sufficient deoxidants are added to prevent the formation of a rimmed steel structure.

##### **B.1.4 Rimmed steel**

Rimmed steels are normally restricted to a carbon content of less than 0.25 %, and to a manganese content of less than 0.70 %. Deoxidants are only added to these steels to control the rimming action.

#### **B.2 Alloy steel**

Alloy steels are required to be killed and the silicon content shall be within the range 0.10 % to 0.35 %.



# List of references

## Normative references

### BSI Publications

BRITISH STANDARDS INSTITUTION, London

BS 131, *Notched bar tests.*

BS 131-1:1961, *The Izod impact test of metals.*

BS 240:1986, *Method for Brinell hardness test and for verification of Brinell hardness testing machines.*

BS 427:1990, *Method for Vickers hardness test and for verification of Vickers hardness testing machines.*

BS 891:1989, *Methods for hardness test (Rockwell method) and for verification of hardness testing machines (Rockwell method).*

BS 4114:1967, *Specification for dimensional and quantity tolerances for steel drop and press forgings and for upset forgings made on horizontal forging machines.*

BS 4490:1989, *Methods for micrographic determination of the grain size of steel.*

BS 5903:1980, *Method for determination of resistance to intergranular corrosion of austenitic stainless steels: copper sulphate- sulphuric acid method (Money penny Strauss test).*

BS 6200, *Sampling and analysis of iron, steel and other ferrous metals.*

BS 6200-2, *Sampling and sample preparation.*

BS 6200-2.1:1993, *Methods for iron and steel.*

BS 6200-2.2:1993, *Methods for ferroalloys and other alloying additives.*

BS 6200-3, *Methods of analysis.*

BS 6722:1986, *Recommendations for dimensions of metallic materials.*

BS EN 10002, *Tensile testing of metallic materials.*

BS EN 10002-1:1990, *Method of test at ambient temperature.*

BS EN 10045, *Charpy impact test on metallic materials.*

BS EN 10045-1:1990, *Test method (V- and U-notches).*

## Informative references

BS 29:1976, *Specification for carbon steel forgings above 150 mm ruling section.*

BS 4437:1987, *Method for determining hardenability of steel by end quenching (Jominy test).*

BS 4670:1971, *Specification for alloy steel forgings.*

BS 5046:1974, *Method for the estimation of equivalent diameters in the heat treatment of steel.*

BS EN 10083, *Quenched and tempered steels<sup>2)</sup>.*

BS EN 10083-1:1991, *Technical delivery conditions for special steels<sup>2)</sup>.*

BS EN 10083-2:1991, *Technical delivery conditions for unalloyed quality steels<sup>2)</sup>.*

BS EN 10088-1:1995, *List of stainless steels.*

BS EN 10088-2:1995, *Technical delivery conditions for sheet/plate and strip for general purposes.*

BS EN 10088-3:1995, *Technical delivery conditions for semi-finished products, bars, rods and sections for general purposes.*

---

<sup>2)</sup> Referred to in the foreword only.

---

# BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

## Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

## Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

## Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

## Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.