



Steel plate, sheet and strip

Part 1. Carbon and carbon-manganese plate, sheet and strip

Section 1.12 Specification for tolerances on dimensions and shape for hot rolled narrow strip

Tôles, bandes et feuillards en acier
Partie 1. Tôles, bandes et feuillards en acier au carbone et au carbone-manganèse
Section 1.12 Tolérances de dimensions et de forme des feuillards laminés à chaud —
Spécifications

Bleche und Bänder
Teil 1. Bleche und Bänder aus unlegiertem Stahl und Manganstahl
Abschnitt 1.12 Maß- und Formtoleranzen für wärmegewalztes Schmalband

Committees responsible for this British Standard

The preparation of this British Standard was entrusted by the Iron and Steel Standards Policy Committee (ISM/-) to Technical Committee ISM/10, upon which the following bodies were represented:

British Railways Board
British Steel Industry
Cold Rolled Sections Association
Society of Motor Manufacturers and Traders Limited

The following bodies were also represented in the drafting of the standard, through subcommittees and panels:

British Welded Steel Tube Association
Institution of Mechanical Engineers
National Association of Steel Stockholders

This British Standard, having been prepared under the direction of the Iron and Steel Standards Policy Committee, was published under the authority of the Standards Board and comes into effect on 31 October 1991

© BSI 1991

Amendments issued since publication

Amd. No.	Date	Text affected

The following BSI references relate to the work on this standard:
Committee reference ISM/10
Draft announced in *BSI News*
August 1991

ISBN 0 580 19881 2

Foreword

This Section of BS 1449 has been prepared under the direction of the Iron and Steel Standards Policy Committee. It is a new edition of the element of BS 1449 : Part 1 : 1983 covering tolerances on dimensions and shape for hot rolled narrow strip. This Section of BS 1449, together with BS 1449 : Sections 1.1 to 1.11 and 1.13 to 1.15 and BS EN 10130, supersedes BS 1449 : Part 1 : 1983 which is withdrawn.

The requirements specified are technically identical to those applicable to hot rolled narrow strip in section five of BS 1449 : Part 1: 1983. This Section of BS 1449 will be withdrawn when EU 48 'Hot rolled narrow strip. Tolerances on dimensions and shape' becomes a European Standard and is published as a British Standard.

For further explanation of this change in presentation see the foreword to BS 1449 : Section 1.1 : 1991.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Specification

1 Scope

This Section of BS 1449 specifies tolerances on dimensions and shape for hot rolled narrow strip.

NOTE. The titles of the publications referred to in this standard are listed on the inside back cover.

2 Definitions

For the purposes of this Section of BS 1449, the definitions given in BS 1449 : Section 1.1 apply.

3 Tolerance on thickness

3.1 The thickness of material shall be measured at a position that complies with the appropriate requirements of table 1.

Table 1. Details of position for measurement of thickness

Nominal width of ordered material	Details of position for measurement
mm	
Up to and including 75	Not less than 10 % of the ordered width from the edge
Over 75 up to and including 600	Not less than 10 mm from the edge

3.2 The variation in thickness shall be in accordance with the tolerances given in table 2. The variation in thickness across the width shall not exceed half the total tolerance given in table 2. This thickness variation or 'crown' shall be within the overall thickness tolerances as given in table 2.

4 Tolerance on width

The variation in the width of strip shall be in accordance with the tolerances given in table 3.

5 Tolerance on length


The variation in length of flat cut lengths shall not exceed the tolerances given in table 4. Tolerances on length for resheared material shall be in accordance with those given in table 4.

6 Maximum edge camber

The edge camber (i.e. lateral departure of the edge of the material from a straight line forming a chord) (see figure 1) shall not exceed the values given in table 5.

7 Maximum out-of-squareness

The out-of-squareness (i.e. the greatest deviation of an end edge from a straight line at right angles to a side and touching one corner) of material shall not exceed the tolerances given in table 6. Tolerances for out-of-squareness for resquared material shall be in accordance with those given in table 6.

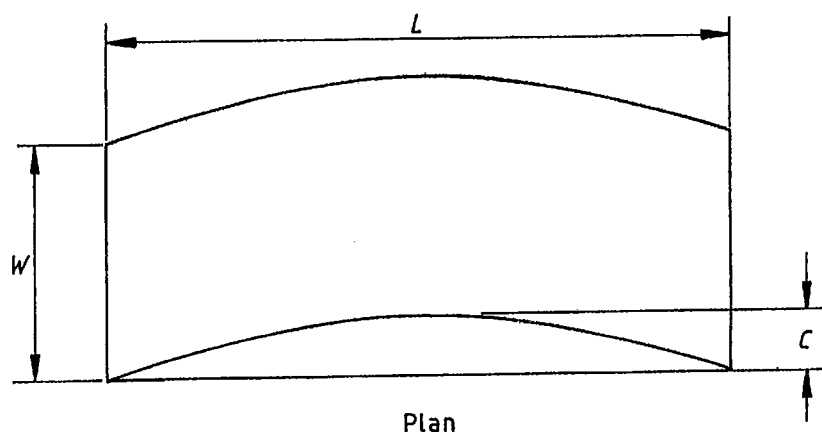

Key
W is the width
L is the length
C is the edge camber

Figure 1. Edge camber

8 Maximum deviation from flatness

8.1 General

If hot rolled narrow strip is required to be specially flat across the width, the maximum deviation from flatness and the method of measurement shall be agreed between manufacturer and purchaser at the time of ordering.

NOTE 1. Material that has been rotary sheared as a final operation tends to have a slight bow across the width.

NOTE 2. If strip is required specially flat across the width, this condition may be produced by further cold rolling after shearing.

8.2 Products, flattened and cut to length

For products of nominal length 2000 mm, the deviation from flatness shall not exceed 10 mm plus the thickness of the strip.

NOTE. These maximum deviations from flatness do not apply to material supplied in coil form.

For products of nominal lengths other than 2000 mm, the permitted maximum deviations shall be agreed between manufacturer and purchaser at the time of ordering.

Nominal thickness		Tolerance on nominal thickness
Over	Up to and including	
mm	mm	mm
—	1.2	± 0.08
1.2	2.0	± 0.10
2.0	2.5	± 0.12
2.5	3.0	± 0.13
3.0	5.0	± 0.15
5.0	8.0	± 0.18

NOTE 1. If thickness is specified as a minimum with tolerances all +, the permitted variation is equal to the total tolerance. For example, a specified minimum thickness of 2.30 mm permits -0, +0.24 mm and the nominal thickness would be 2.42 mm. However, where, as a result, the nominal thickness then falls with the next higher range for nominal thickness, the tolerances for the higher apply; i.e. if a minimum thickness of 2.40 mm is ordered, the tolerance range would be -0, +0.26 mm and the nominal thickness would be 2.53 mm.

NOTE 2. The above tolerances do not apply to the uncropped ends of material having a mill edge.

BS 1449 : Section 1.12 : 1991

Table 3. Tolerance on nominal width

Type of edge	Nominal width		Nominal thickness		Tolerance on nominal width
	Over	Up to and including	Over	Up to and including	
Mill edge	mm	mm	mm	mm	mm
	—	50	All thicknesses		±1.0
	50	150			±1.5
	150	250			±2.0
250	600	±3.0			
Sheared edge	—	250	—	1.6	±0.13
	—	250	1.6	3.0	±0.19
	—	250	3.0	—	±0.25
	250	600	—	1.6	±0.20
	250	600	1.6	5.0	±0.25

NOTE. These tolerances apply to all lengths including coil with the exception of the uncropped ends of hot rolled coils having mill edges.

Table 4. Tolerance on nominal length for cut lengths in all widths

Nominal length		Tolerance on nominal length
Over	Up to and including	
mm	mm	mm
—	1000	-0 +25
1000	3000	-0 +25
3000	—	-0 +25

NOTE. The above values apply to cold sheared material; the tolerance for hot shearing is ± 50 mm.

Table 5. Maximum edge camber for mill edge and sheared edge material¹⁾

Nominal width		Nominal thickness		Maximum edge camber in any 2000 mm length
Over	Up to and including	Over	Up to and including	
mm	mm	mm	mm	mm
—	25	—	2	—
25	50	—	2	13
—	50	2	—	10
50	250	—	2	13
50	250	2	—	10
250	600	—	2	13
250	600	2	—	6.5

¹⁾See figure 1.

NOTE 1. Where it is not practicable to measure over 2000 mm, equivalent tolerances can be calculated from the following equation and rounded to the next higher millimetre.

$$\text{New tolerance} = \frac{(\text{non standard length})^2}{(\text{standard length})^2} \times \text{tolerance in table 5}$$

NOTE 2. Special requirements on edge camber may be available by arrangement between the manufacturer and the supplier.

Table 6. Maximum out-of-squareness of width in flat cut lengths

Nominal length	Nominal width	Nominal thickness	Maximum out-of-squareness per 150 mm of nominal width or fraction thereof
All lengths	All widths	All thicknesses	mm 1.5 max. (1.0 %)

Publication(s) referred to

- BS 1449 Steel plate, sheet and strip
 Section 1.1 General specification
- EU 48¹⁾ Hot rolled narrow strip. Tolerances on dimensions and shape

¹⁾Referred to in the foreword only.

BS 1449 :
Section 1.12 :
1991

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Contract requirements

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

Any person who finds an inaccuracy or ambiguity while using this British Standard should notify BSI without delay so that the matter may be investigated swiftly.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying British Standards

Orders for all British Standard publications should be addressed to the Sales Department at Milton Keynes.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library, the Standardline Database, the BSI Information Technology Service (BITS) and its Technical Help to Exporters Service. Contact Customer Information at Milton Keynes: Tel: 0908 221166.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact the Manager, Membership Development at Milton Keynes: Tel: 0908 220022.

Copyright

Copyright subsists in all BSI publications. No part of this publication may be reproduced in any form without the prior permission in writing of BSI. This does not preclude the free use, in the course of implementing the standard, of details such as symbols and size, type or grade designations. Enquiries about copyright should be made to the Copyright Manager, Marketing at Milton Keynes.

BSI
 2 Park Street
 London
 W1A 2BS

BSI
 Linford Wood
 Milton Keynes
 MK14 6LE