

# Testing concrete —

## Part 209: Recommendations for the measurement of dynamic modulus of elasticity

UDC 666.972:691.32:620.1

# Committees responsible for this British Standard

The preparation of this British Standard was entrusted by the Cement Gypsum, Aggregates and Quarry Products Standards Policy Committee (CAB/-) to Technical Committee CAB/4, upon which the following bodies were represented:

Association of Lightweight Aggregate Manufacturers  
 Association of Metropolitan Authorities  
 Association of Quality Pulverised Fuel Ash Suppliers  
 British Aggregate Construction Materials Industries  
 British Cement Association  
 British Civil Engineering Test Equipment Manufacturers' Association  
 British Precast Concrete Federation  
 British Ready Mixed Concrete Association  
 Building Employers' Confederation  
 Cement Admixtures Association  
 Cementitious Slag Makers' Association  
 Concrete Society  
 County Surveyors' Society  
 Department of the Environment (Building Research Establishment)  
 Department of the Environment (Property Services Agency)  
 Department of Transport  
 Department of Transport (Transport and Road Research Laboratory)  
 Electricity Supply Industry in England and Wales  
 Federation of Civil Engineering Contractors  
 Institute of Concrete Technology  
 Institution of Civil Engineers  
 Institution of Highways and Transportation  
 Institution of Structural Engineers  
 Institution of Water and Environmental Management (IWEM)  
 Royal Institution of Chartered Surveyors  
 Sand and Gravel Association  
 Society of Chemical Industry

The following bodies were also represented in the drafting of the standard, through sub-committees and panels:

British Nuclear Fuels Limited  
 United Kingdom Atomic Energy Authority

This British Standard, having been prepared under the direction of the Cement, Gypsum, Aggregates and Quarry Products Standards Policy Committee, was published under the authority of the Board of BSI and comes into effect on 30 April 1990

© BSI 12-1998

The following BSI references relate to the work on this standard:  
 Committee reference CAB/4  
 Draft for comment 88/10608

ISBN 0 580 17925 7

## Amendments issued since publication

Amd. No.	Date	Comments

---

# Contents

	Page
Committee responsible	Inside front cover
Foreword	ii
<hr/>	
1 Scope	1
2 Definitions	1
3 Applications	1
4 Principle	1
5 Summary of the test method	1
6 Apparatus	1
7 Methods of testing laboratory made specimens	2
8 Calculations	3
9 Report	3
<hr/>	
Figure 1 — Test configuration for determination of dynamic modulus of elasticity	4
<hr/>	
Publications referred to	Inside back cover
<hr/>	

## Foreword

This Part of BS 1881 has been prepared under the direction of the Cement, Gypsum, Aggregates and Quarry Products Standards Policy Committee. It supersedes clause 4 of BS 1881-5:1970, which has been deleted.

All aspects of testing concrete are being included as Parts of BS 1881, from sampling fresh concrete to assessing concrete in structures. Part 201 gives general guidance on the choice of non-destructive test methods and should be consulted for advice on methods which can be used to complement this method of measuring the dynamic modulus of elasticity.

Testing of concrete by the measurement of dynamic modulus of elasticity is a laboratory technique and involves applying an alternating force of variable frequency to the end of a prismatic sample and recording the resonant frequency.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, pages 1 to 4, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

## 1 Scope

This Part of BS 1881 gives recommendations for the determination of dynamic modulus of elasticity of plain concrete in the laboratory using resonance of vibration in the longitudinal mode.

NOTE The titles of the publications referred to in this standard are listed on the inside back cover.

## 2 Definitions

For the purposes of this Part of BS 1881 the definitions given in BS 3683-4 and BS 6100-6 apply, together with the following.

### 2.1 resonance

condition in which the frequency of a vibration applied to a body is equal to one of the natural frequencies of vibration of that body

NOTE This concurrence of frequencies maximizes the amplitude of vibration in the body.

### 2.2 longitudinal mode of vibration

mode in which compression waves travel through a prismatic specimen in the direction parallel to its length

NOTE 1 The waves are partially reflected by the end faces of the specimen and thus travel to and fro within it.

NOTE 2 Other modes exist such as transverse and torsional.

### 2.3 fundamental frequency

lowest resonant frequency at which a body will vibrate in a particular mode

### 2.4 dynamic modulus of elasticity of concrete ( $E_D$ )

ratio of the stress to that part of the strain corresponding to elastic deformation only

NOTE The modulus obtained refers to the initial tangent to the non-linear stress/strain relationship for concrete, which does not obey Hooke's Law. It is normally appreciably larger than the statically measured value obtained by the method described in BS 1881-121.

## 3 Applications

Measurement of dynamic modulus is most commonly used for comparative testing of concretes in the laboratory and for assessing degradation in durability tests, e.g. in freezing and thawing tests.

## 4 Principle

An elastic or partially elastic body will vibrate if struck a blow. Each body possesses many modes of vibration and in geometrical bodies well defined modes may be identified. This method is concerned only with identifying the fundamental longitudinal mode of vibration in concrete prisms.

The frequency at which this vibration occurs depends largely on the dynamic modulus of elasticity, density, and length of the specimen.

## 5 Summary of the test method

A variable frequency oscillator imparts an alternating force to the specimen and the response is sensed by an accelerometer or vibration pick-up. The amplitude of vibrations is monitored by an indicator and when a resonant frequency is reached, the indicator shows the amplitude to be at a well defined maximum.

If this resonant frequency is the fundamental frequency it is related to the modulus of elasticity of the concrete through the equation in clause 8.

## 6 Apparatus

**6.1 Variable frequency oscillator**, providing a variable narrow-band sinusoidal output from 500 Hz to 20 kHz with power adjustable from zero to at least 2 W.

The frequency of the oscillator output should be indicated within an accuracy of  $\pm 0.5\%$ .

The output of a good quality oscillator tuned to a given frequency should not contain more than 2% of its amplitude in the second and third harmonics of the frequency and should have a stability within  $\pm 5\%$  of the operating voltage.

**6.2 Exciter**, of which the part in contact with the specimen should have a mass of not more than 0.2% of the mass of the specimen.

**6.3 Pick-up**, of which any part in contact with the specimen should have a mass of not more than 0.2% of the mass of the specimen. The vibration pick-up should have no resonances at frequencies below 20 kHz.

**6.4 Amplitude indicator**, consisting of a voltmeter or cathode ray oscilloscope incorporating appropriate amplification facilities.

**6.5 Support**, consisting of a pair of horizontal steel bars between which the specimen can be clamped. The width of the contact area of the clamping bars should not exceed one twentieth of the length of the specimen. The bars can be positioned by threaded vertical rods attached to a rigid baseboard which also carries the exciter and pick-up mounting posts as shown in Figure 1. The baseboard stands on soft elastomeric pads on a rigid workbench to reduce the effects of extraneous vibrations transmitted through the laboratory floor.

Alternatively, the specimen may lie on a block of foam rubber provided that the exciter and pick-up centrelines are normal to the specimen's end faces.

**6.6 Balance**, of appropriate capacity to weigh the specimen to the accuracy required by 7.2.

**6.7 Vernier calliper**, complying with BS 887, capable of measuring the lateral dimensions of the specimen to the accuracy required by 7.2.

## 7 Methods of testing laboratory made specimens

### 7.1 Preparation

The laboratory made specimens should be prisms of circular or square section with a length not less than three nor more than five times the maximum transverse dimension. Specimens should preferably be beams made in accordance with BS 1881-109 and then cured in accordance with BS 1881-111.

### 7.2 Preliminary measurements

Immediately before testing, the length and density of each specimen should be obtained from the following procedures.

a) *Length*. Calculate the mean length,  $L$ , (in mm) from at least four symmetrically placed measurements read to an accuracy of  $\pm 1$  mm.

b) *Density*. Weigh the specimen in air and record its mass,  $M_A$ , (in kg) to an accuracy of  $\pm 0.25$  %.

Determine the volume,  $V$ , (in  $\text{m}^3$ ) of the specimen either from its dimensions or by water displacement as follows.

1) *Dimensions*. For a beam, calculate the mean width,  $a$ , and depth,  $b$ , (in mm) from at least six measurements of each dimension spaced equally along its length read to an accuracy of  $\pm 0.25$  mm. Then

$$V = L b a \times 10^{-9}$$

For a cylindrical specimen, calculate the mean diameter,  $d$ , (in mm) from at least six measurements spaced equally along its length read to an accuracy of  $\pm 0.25$  mm. Then

$$V = \frac{L \pi d^2}{4} \times 10^{-9}$$

2) *Water displacement*. Weigh the specimen in water and record its apparent loss in mass,  $M_L$ , (in kg) to an accuracy of  $\pm 0.25$  %. Then

$$V = M_L / \rho_w$$

where

$\rho_w$  is the density of water which may be taken as  $1 \text{ kg/m}^3$  at ambient temperature.

Method 2 should not be used for unsaturated specimens.

Calculate the density,  $\rho$ , (in  $\text{kg/m}^3$ ) of the specimen from the equation

$$\rho = M_A / V.$$

### 7.3 Measurement of resonant frequency

Specimens should be tested in a condition appropriate to the purpose of the investigation.

Where specimens have been stored in water they should be tested immediately on removal from the water, whilst they are still saturated. Surface water and grit should be wiped off the specimen.

The specimen should be clamped or balanced at its centre on the fixed support.

Contact should be made between the vibrating part of the exciter and the centre of one end face of the specimen by means of a weak adhesive or by gentle spring loading. Contact should be made between a piezo-electric vibration pick-up and the opposite end of the specimen in a similar way, as indicated in Figure 1. Alternatively, an electromagnetic non-contacting pick-up can be used in accordance with the manufacturer's recommendations. Ensure that the axes of the transducers are in the centre of and normal to the end faces of the specimen.

The exciter should be driven by the variable frequency oscillator and the oscillations received from the pick-up should be fed to the amplitude indicator to show the changes in amplitude received.

The frequency of excitation should be varied until a resonance is obtained and the frequency noted. Resonance will be recognized when the amplitude indicator shows a peak response. As the frequency is further varied, the indicator may show the existence of several resonant frequencies, some of these relating to modes of vibration other than longitudinal.

The identification of the fundamental frequency in the longitudinal mode requires care. Generally the required frequency produces the greatest response on the indicator for given settings of the output and gain controls. As a check, with the specimen set up as shown in Figure 1, resonance should also be obtainable at a frequency three times that of the fundamental frequency.

If difficulties are still encountered, an approximate value for the dynamic modulus of elasticity of the concrete may be obtained from a pulse transit time measurement (see BS 1881- 203). This value may then be substituted into the equation in clause 8 to yield an approximate value for the desired resonant frequency. The search for the exact frequency may then be confined to a narrow range about the value so calculated.

Instrument manufacturer's literature sometimes provides very useful instructions for identifying the fundamental frequency. Once identified, this value should be recorded.

## 8 Calculations

The dynamic modulus of elasticity of concrete,  $E_D$ , (in  $\text{GN/m}^2$ ) for each specimen should be calculated to the nearest  $0.5 \text{ GN/m}^2$  from the formula

$$E_D = 4n^2 L^2 \rho \cdot 10^{-15}$$

where

- $L$  is the length of the specimen (in mm);
- $n$  is the fundamental frequency in the longitudinal mode of vibration of the specimen (in Hz);
- $\rho$  is the density of the specimen (in  $\text{kg/m}^3$ ).

NOTE This formula applies to all uniform specimens of constant cross section.

## 9 Report

### 9.1 General

The report should affirm that the dynamic modulus of elasticity of concrete was determined in accordance with the recommendations given in BS 1881-209:1990.


### 9.2 Information to be included in the test report

**9.2.1 Obligatory information.** The following information should be included in the test report:

- a) date of test;
- b) description and nominal size of the specimen with any identifying mark;
- c) age of the specimen when tested;
- d) conditions in which the specimen had been stored between manufacture and testing;
- e) the calculated dynamic modulus of elasticity of the concrete.

**9.2.2 Additional information.** When requested, the following information should also be included in the test report:

- a) the fundamental frequency;
- b) the measured dimensions of the specimen;
- c) the density of the specimen at the time of testing.

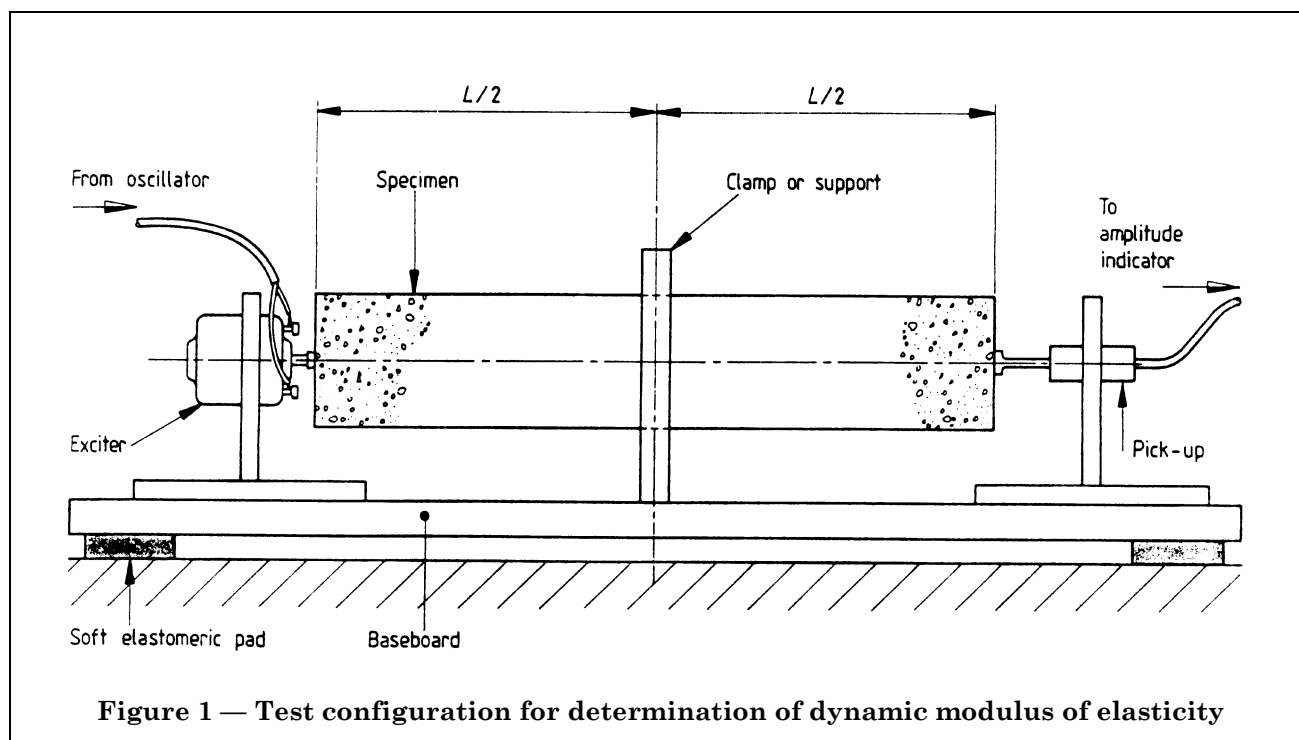



## Publications referred to

BS 887, *Specification for precision vernier callipers.*

BS 1881, *Testing concrete.*

BS 1881-109, *Method for making test beams from fresh concrete.*

BS 1881-111, *Method of normal curing of test specimens (20 °C method).*

BS 1881-121, *Method for determination of static modulus of elasticity in compression.*

BS 1881-201, *Guide to the use of non-destructive methods of test for hardened concrete<sup>1)</sup>.*

BS 1881-203, *Recommendations for measurement of velocity of ultrasonic pulses in concrete.*

BS 3683, *Glossary of terms used in non-destructive testing.*

BS 3683-4, *Ultrasonic flaw detection.*

BS 6100, *Glossary of building and civil engineering terms.*

BS 6100-6 *Concrete and plaster.*

---

<sup>1)</sup> Referred to in the foreword only.

---

---

# BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

## Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

## Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

## Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

## Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.