

OBSOLESCE
AUGUST 1988

Specification for

**Unified precision
hexagon bolts,
screws, & nuts
(UNC & UNF Threads)
Normal series**

UDC 621.882.2.082.3

Co-operating organizations

The Mechanical Engineering Industry Standards Committee, under whose supervision this British Standard was prepared, consists of representatives from the following Government departments and scientific and industrial organizations:

Admiralty*	Gas Council
Air Ministry	High Commission of India*
Associated Offices' Technical Committee	Institute of Marine Engineers
Association of Consulting Engineers (Incorporated)	Institute of Petroleum
Association of Mining Electrical and Mechanical Engineers	Institution of Civil Engineers
British Chemical Plant Manufacturers' Association	Institution of Gas Engineers
British Compressed Air Society	Institution of Heating and Ventilating Engineers
British Electrical and Allied Manufacturers' Association*	Institution of Mechanical Engineers
British Gear Manufacturers' Association	Institution of Mechanical Engineers (Automobile Division)
British Internal Combustion Engine Manufacturers' Association*	Institution of Production Engineers*
British Iron and Steel Federation*	Locomotive and Allied Manufacturers' Association of Great Britain*
British Mechanical Engineering Federation*	London Transport Board
British Railways Board*	Machine Tool Trades Association*
Crown Agents for Oversea Governments and Administrations	Ministry of Labour (H.M. Factory Inspectorate)
D.S.I.R. — National Engineering Laboratory	Ministry of Power
Electricity Council, the Generating Board and the Area Boards in England and Wales	Ministry of Public Building and Works
Engineering Equipment Users' Association*	Ministry of Transport
	National Coal Board
	National Physical Laboratory (D.S.I.R.)*
	Radio Industry Council
	War Office*

The Government departments and scientific and industrial organizations marked with an asterisk in the above list, together with the following were directly represented on the Committee entrusted with the preparation of this standard:

Agricultural Engineers' Association	Heat Treated Bolt Association
Association of Hydraulic Equipment Manufacturers	Institute of Iron & Steel Wire Manufacturers
Bright Bolt & Nut Manufacturers Association	Ministry of Aviation
Bright Steel Bar Association	Oil Companies Materials Association
British Constructional Steelwork Association	Post Office
British Cycle & Motor Cycle Industries Association Limited	Rolled Thread Screw Association
Council of British Manufacturers of Petroleum Equipment	Screw Manufacturers Association
Electronic Engineering Association	Society of Motor Manufacturers & Traders Ltd.
	Washer Manufacturers' Association
	Individual manufacturers

This British Standard, having been approved by the Mechanical Engineering Industry Standards Committee and endorsed by the Chairman of the Engineering Divisional Council, was published under the authority of the General Council on 17 September 1963

© BSI 10-1999

First published September 1951
First revision September 1963

The following BSI references relate to the work on this standard:
Committee reference MEE/60
Draft for comment
AB(MEE) 4808

ISBN 0 580 30789 1

Amendments issued since publication

Amd No.	Date	Comments
5706	December 1965	
6223	July 1967	
5373	April 1988	Indicated by a sideline in the margin

Contents

	Page
Co-operating organizations	Inside front cover
Foreword	iii
<hr/>	
1 Scope	1
2 Material and manufacture	1
3 Finish	2
4 Mechanical properties of steel bolts and screws	2
5 Tensile strength and proof stress of bolts and screws	2
6 Grading and mechanical properties of steel nuts	3
7 Proof load for nuts	4
8 Dimensions	4
9 Length of bolts and screws	4
10 Ends of bolts and screws	5
11 Screw threads	5
12 Length of thread	5
13 Nuts, squareness of thread to face	5
14 Chamfering, washer facing and countersinking	6
15 Split-pin holes and slots	6
16 Marking	6
17 Inspection and testing	7
<hr/>	
Appendix A Mechanical properties of finished steel hexagon head bolts and screws and hexagon nuts	14
Appendix B Materials	18
Appendix C Testing fixtures and recommended gauges	22
Appendix D Standard sizes of Unified precision steel hexagon head bolts and screws and shortest lengths designated as bolts	28
Appendix E Details of identification marking for Unified hexagon bolts, screws and nuts	31
Appendix F Formulae	34
<hr/>	
Figure 1 — Hexagon head bolt, washer faced	8
Figure 2 — Hexagon head screw, washer faced	8
Figure 3 — Full bearing	8
Figure 4 — Rounded end	8
Figure 5 — Rolled thread end	8
Figure 6 — Double chamfered	10
Figure 7 — Thick double chamfered	10
Figure 8 — Washer faced	10
Figure 9 — Thick washer faced	10
Figure 10 — Hexagon lock nut	10
Figure 11 — Enlarged view of nut countersink (see clause 14 b)	10
Figure 12 — Double chamfered	12
Figure 13 — Washer faced	12
Figure 14 — Double chamfered	12
Figure 15 — Washer faced	12
Figure 16	22
Figure 17	23
Figure 18	24
Figure 19	25
Figure 20	26
Figure 21	27

	Page
Figure 22	27
Figure 23 — Ordinary nut and thick nut with indented groove	31
Figure 24 — Lock nut with indented groove	31
Figure 25 — Slotted nut and thick slotted nut with indented groove	31
Figure 26 — Ordinary nut, thick nut, lock, slotted or thick slotted nut with indented circles	31
Figure 27 — Washer faced	32
Figure 28 — Enlarged part section through recess	32
Figure 29 — Bolt or screw with recess	33
Figure 30 — Bolt or screw with indented circles	33
<hr/>	
Table 1 — Unified hexagon head bolts and screws	9
Table 2 — Unified hexagon ordinary nuts, thick ordinary nuts and lock nuts	11
Table 3 — Unified hexagon slotted nuts and thick slotted nuts	13
Table 4 — Mechanical properties of steel bolts and screws	14
Table 4A — Comparison of strength grades of BS 1768 and BS 970	15
Table 5 — Proof loads for bolts and screws	16
Table 6 — Proof loads for nuts	17
Table 7 — Examples of suitable material for Materials for cold forged bolts and screws	18
Table 8 — Materials for hot forged bolts and screws	19
Table 9 — Materials for bolts and screws turned from bar	21
Table 10 — Materials for nuts	21
Table 11 — Standard sizes of Grade A bright hexagon bolts	28
Table 12 — Standard sizes of Grade A bright hexagon screws	28
Table 13 — Standard sizes of Grade S heat treated hexagon bolts	29
Table 14 — Standard sizes of Grade S heat treated hexagon screws	29
Table 15 — Shortest lengths designated as bolts	30

Foreword

This standard makes reference to the following British Standards:

BS 18, *Methods for tensile testing of metals.*

BS 131, *Methods for notched bar tests — Part 1: The Izod impact test on metals.*

BS 240, *Methods of Brinell hardness test — Part 1: Testing of metals.*

BS 860, *Table of approximate comparison of hardness scales.*

BS 919, *Screw gauge limits and tolerances — Part 1: Gauges for screw threads of Unified form.*

BS 969, *Plain limit gauges: Limits and tolerances.*

BS 970, *Specification for wrought steels for mechanical and allied engineering purposes — Part 1: General inspection and testing procedures and specific requirement for carbon, carbon manganese, alloy and stainless steels.*

BS 1574, *Split cotter pins.*

BS 1580, *Unified screw threads — Parts 1 and 2: Diameters $\frac{1}{4}$ in and larger.*

BS 3111, *Specification for steel wire for cold forged fasteners and similar components — Part 1: Carbon and low alloy steel.*

When BS 1768 was first issued in 1951, its publication marked an important stage in the development of the Unified screw thread system established in accordance with the agreement reached by the United Kingdom with the United States and Canada at the Ottawa Conference of 1945 and ratified by the Declaration of Accord signed by representatives of those three countries in November, 1948.

It was recognized at that time that effective adoption of the system depended very largely on the provision of commonly used types and sizes of fasteners, the general features of which would be unified as well as the threads. As a first step, two standards for hexagon bolts, screws and nuts were published: BS 1768 for the Unified precision normal series, and BS 1769 for the Unified black heavy series.

BS 1768 was restricted at that time to sizes up to and including 1 inch but the many requests received for an extension of the standard have long indicated that this range was inadequate for the needs of industry and this edition accordingly provides for sizes up to and including 2 inches.

It should be mentioned that this extension of the Unified range is also in accordance with agreement reached with the U.S.A. and Canada at a further ABC Conference held in Ottawa in June, 1960, and that an ISO Recommendation now in course of preparation for hexagon bolts, screws and nuts will include the range of Unified normal hexagons for nominal sizes up to $1\frac{1}{2}$ inches.

In revising the standard, the opportunity has been taken to deal more fully with material and manufacture. In addition to specifying materials for cold forged bolts, screws and nuts and offering guidance in the selection of materials for those produced by other methods, the standard now includes full details of the tests to be employed for determining the mechanical properties of the fasteners. Reference is also made to the control of decarburization and rolling laps.

Special attention is drawn to an important feature of this revision, namely the replacement of Grade R bolts which had a tensile range of 45 to 55 tonf/in² with Grade S bolts having a minimum tensile strength of 50 tonf/in² which is more nearly in line with both American and continental practice.

It is recognized that a transition period will necessarily ensue during which stocks of both grades will be held by manufacturers and either may be offered when bolts in this tensile range are ordered.

Washers have been excluded from this standard as they are now covered by BS 3410, "*Metal washers for general engineering purposes.*"

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i to iv, pages 1 to 34, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

1 Scope

This British Standard covers the Normal series of Unified precision hexagon bolts, screws and nuts having Unified screw threads in a range of nominal sizes from $\frac{1}{4}$ in to 2 in inclusive. The dimensional requirements of this standard apply both to ferrous and non-ferrous bolts, screws and nuts. Mechanical properties are given only in respect of steel bolts, screws and nuts, and the finishes in which they are normally supplied are described in Clause 3.

NOTE It is considered that the range of nominal sizes included in this standard is adequate for most of the applications for which this series is likely to be employed, but for the convenience of users requiring larger sizes, the formulae from which the proportions for bolt heads and nuts are derived are given in Appendix F.

2 Material and manufacture

a. *General.* In order to provide for the different methods of manufacture by which bolts, screws and nuts to this standard may be produced, a choice of materials is given.

Bolts, screws and nuts in sizes up to and including $\frac{3}{4}$ in nominal size are most commonly produced by cold forging from wire; larger sizes are generally produced by hot forging. Bolts, screws and nuts can also be produced by machining from hexagon bars.

Bolts and screws produced by cold forging shall, except in the case of bolts and screws bright finished to Grade A (see Table 4, Appendix A) be heat-treated after forging.

Bolts, screws and nuts produced by hot forging or by turning from bars, and cold formed nuts shall be heat-treated when this is necessary to give the requisite mechanical properties specified in Clauses 4 and 6 and Appendix A.

b. *Cold forged bolts and screws.* The choice of material used to manufacture bolts and screws by cold forging shall normally be at the discretion of the manufacturer. The finished products shall comply with the requirements for physical properties as set out in Clause 4 and in Table 4 of Appendix A.

If, however, the purchaser wishes to specify the composition of the material to be used, this shall be the subject of agreement with the manufacturer.

c. *Cold forged nuts and hot forged bolts, screws and nuts.* The material to be used for cold forged nuts or hot forged bolts, screws and nuts depends to a large extent on the size of the product. Unless otherwise stipulated by the purchaser, the choice of material shall therefore be left to the manufacturer provided that the finished products satisfy the requirements for mechanical properties set out in Clauses 4 and 6 and in Table 4 and Table 6 of Appendix A, but recommendations on suitable materials are given for guidance in Table 8 and Table 10 of Appendix B.

d. *Bolts, screws and nuts machined from bars.* Table 9 and Table 10 of Appendix B give a selection of steels from BS 970 which are among those suitable for particular grades of bolts, screws and nuts. Unless otherwise stipulated by the purchaser, the choice of material shall be left to the manufacturer provided that the finished products satisfy the requirements for mechanical properties set out in Clauses 4 and 6 and in Table 4 and Table 6 of Appendix A.

e. *Decarburization.* As normally manufactured from wire of ordinary quality, a proportion of threads produced on forged bolts and screws by rolling may have some surface decarburization (principally at crests of threads). For highly stressed bolt applications, the definition and degree of such decarburization shall be negotiated between manufacturer and user. For bolts of strength Grade T and greater, the depth of decarburization, measured from the crest, shall not exceed 33 per cent of the height of the threads. Complete freedom from any decarburization is achieved by shank grinding after heat treatment and before thread rolling; if this is required, it shall be the subject of negotiation between manufacturer and user.

f. *Rolling laps.* When threads are produced by rolling, small laps are commonly present at the crests and are generally of a magnitude which is not detrimental to the performance of the bolt.

A lap formed at the crest of the thread perpendicular to the axis of the bolt shall not be considered a cause for rejection if the depth of the lap does not exceed 33 per cent of the depth of the thread.

Bolts of Grades T, V and X shall be free from laps in the thread flank below the effective diameter. Laps in the flanks above the effective diameter shall not have a depth greater than 33 per cent of the thread depth.

3 Finish

- a. *General.* The bolts, screws and nuts shall be cleanly finished, sound and free from defects.
- b. *Types of finish.* Steel precision bolts, screws and nuts are normally supplied with the following finishes:
- i) *Heat treated bolts and screws.* The surfaces of these bolts and screws are customarily dull black from heat treatment, although the manufacturer may machine some of the surfaces of the larger size bolts and screws after heat treatment.
 - ii) *Bright finished bolts and screws.* This term is used to describe bolts and screws which are machined on all surfaces or which have a finish on the hexagons produced by bright drawing and regarded as a machined finish.
 - iii) *Nuts.* These may be bright on all surfaces or dull black where heat treated.
 - iv) *Special finishes.* If steel bolts, screws or nuts are required bright all over, the purchaser should state this in his enquiry and order.

If the purchaser requires bolts, screws or nuts of steel or other material to be coated, he should state the type of coating required in his enquiry and order.

4 Mechanical properties of steel bolts and screws

Steel bolts and screws shall meet the requirements for mechanical properties specified in Table 4 of Appendix A.

NOTE For guidance concerning the comparison of strength grades of BS 1768 and BS 970-1:1983 see Table 4A.

- a. *Tensile strength and proof stress.* The tensile strength and the proof stress shall be determined by the methods of test described in Clause 5.
- b. *Minimum elongation.* Test specimens for the measurement of elongation shall be machined from the shank of the bolt to the dimensions for standard round test specimens as given in BS 18 "*Tensile testing of metals*" and shall be concentric with the axis of the bolt. They shall be tested in accordance with the standard procedure as given in BS 18.

NOTE The minimum elongation values in Table 4 are based on a gauge length of $4\sqrt{\text{Area}}$; BS 18 now specifies a gauge length of $5.65\sqrt{\text{Area}}$, but values appropriate to this length are not yet available for the higher grades of steel. The former gauge length and its associated values have therefore been retained in this standard for the time being and a suitable amendment will be issued when the necessary information can be supplied.

- c. *Minimum Izod impact value.* Test specimens for Izod impact test shall be machined from the bolt to the dimensions specified for standard test pieces in BS 131-1, "*The Izod impact test on metals*" and shall be tested in accordance with the standard procedure as given in BS 131-1.

Where an Izod test is not practicable, a nicked fracture test may be substituted.

- d. *Hardness.*

- i) *General.* A hardness test on bolts and screws is not part of the requirements of this standard, but Brinell hardness values are given for guidance in Table 4 of Appendix A.
- ii) *Method of test.* The Brinell hardness test is carried out in accordance with the method specified in BS 240 "*Method of Brinell hardness test*" Part 1 and is made on the top of the head or on the point of the bolt or screw.

5 Tensile strength and proof stress of bolts and screws

- a. *Tensile strength.* The tensile test on a bolt or screw shall be carried out as follows:

An ordinary nut or its equivalent in the form of an adaptor shall be screwed on to the bolt or screw so as to be clear of the run-out of the thread towards the head and also clear of any imperfect threads at the point, the load shall then be applied to the head and to the nut or adaptor.

- b. *Proof stress.* The proof stress for bolts shall be determined as follows:

- i) *Method of test.* The proof stress for bolts or screws shall be determined with a straight full size threaded bolt or screw. The bolt or screw shall be placed in a suitable testing machine with the threaded end of the bolt or screw in a threaded grip or in a nut. The grips of the testing machine shall be self-aligning to avoid side thrust (see Figure 16 in Appendix C).

The bolt or screw shall be screwed into the grip or nut to the thread run-out of the bolt or screw and then unscrewed six full threads. The bolt or screw shall be subjected to the proof stress for bolts and screws specified in Column 3 of Table 4 in Appendix A by applying the appropriate load as given in Table 5, Appendix A and maintaining for ten seconds and then releasing.

ii) *Method of measurement.* Measurement of the specimens subjected to the proof stresses for bolts or screws shall be performed in the following manner:

The overall length of the bolt or screw shall be measured at its true centre line with an instrument capable of measuring changes in length of 0.0001 in.

After the bolt or screw has been stressed in accordance with the provisions of i) of this clause, its length shall again be measured. There shall be no permanent elongation of the bolts or screws, but to allow for errors of determination between consecutive measurements of bolt or screw length, this condition is considered to have been achieved if the measurement is within ± 0.0005 in of that made before loading.

NOTE The preferred method of carrying out this test is to measure the length between conical centres on the centre line of the bolt or screw which has been set up on the mating centres of the anvils of the measuring fixture; the head or shank of the bolt or screw should be marked so that it can be placed in the same position for all measurements.

6 Grading and mechanical properties of steel nuts

a. *Grading.* Nuts shall be graded as follows:

GRADE 0. Nuts suitable for use with bolts, Grades A, B and P.

The nuts shall be capable of withstanding a proof load, based on the minimum tensile strength of Grade P Bolts, as laid down in Table 4, Column 2.

GRADE 1. Nuts suitable for use with Bolts Grade S.

These nuts shall be capable of withstanding a proof load, based on the minimum tensile strength of Grade S Bolts, as laid down in Table 4, Column 2.

GRADE 3. Nuts suitable for use with Bolts Grade T.

These nuts shall be capable of withstanding a proof load, based on the minimum tensile strength of Grade T Bolts, as laid down in Table 4, Column 2.

GRADE 5. Nuts suitable for use with Bolts Grades V and X.

These nuts shall be capable of withstanding a proof load, based on the minimum tensile strength of Grade X Bolts, as laid down in Table 4, Column 2.

b. *Mechanical properties.*

i) *Proof load.*

Nuts 1 in diameter and under. These nuts shall meet the requirements for proof load specified in Table 6. They shall be tested in accordance with the method described in Clause 7.

Nuts over 1 in diameter. As equipment of sufficient capacity may not be readily available for nuts in this range, they shall meet the requirements for hardness specified in sub-clause c) below.

c. *Hardness.*

i) *Nuts over 1 in diameter.* Nuts of diameters over 1 in shall be subjected to a hardness test and their hardness shall not be less than that specified below:

Brinell Hardness

Grade 0 Nuts—120 HB 10/3 000 min.

Grade 1 Nuts—180 HB 10/3 000 min.

Grade 3 Nuts—230 HB 10/3 000 min.

Grade 5 Nuts—270 HB 10/3 000 min.

ii) *Nuts up to and including 1 in diameter.* For nuts up to and including 1 in diameter, a hardness test is not part of the requirements of this standard but for general guidance Brinell hardness values are given below:

Brinell Hardness

Grade 0 Nuts—120/235 HB 10/3 000

Grade 1 Nuts—163/240 HB 10/3 000

Grade 3 Nuts—183/300 HB 10/3 000

Grade 5 Nuts—270/335 HB 10/3 000

iii) *Preparation of specimens.* The preparation of test specimens and the method of testing shall be in accordance with BS 240 “*Method of Brinell hardness test.*” If Vickers or Rockwell methods are used, reference should be made to BS 860 “*Table of approximate comparison of hardness scales*” for appropriate values.

The test shall be made on the end faces of the nuts.

d. *Assembly testing of nuts.* When nuts up to and including $\frac{3}{4}$ in diameter are torque tested to destruction they shall not fail by splitting of the wall.

7 Proof load for nuts

a. *Method of test* (see Figure 17 in Appendix C). The proof load for nuts shall be determined by assembling the sample nut on a hardened threaded mandrel as specified in sub-clause b) below. A load axial with the mandrel and equal to the proof load for nuts specified in Table 6 shall be applied against the nut. The nut shall satisfactorily resist this load without stripping and should be removable by the fingers after the test. If the threads of the mandrel are damaged during the test the test shall be discarded.

b. *Test mandrel.* The test mandrel shall have a hardness of not less than 365 HV30. It shall be threaded to Class 3A tolerances in accordance with BS 1580, “*Unified screw threads*”, except that the major diameter shall be equal to the minimum major diameter as specified in the standard subject to a plus tolerance of 0.002 in.

8 Dimensions

The bolts, screws and nuts shall conform to the dimensions and tolerances given in Table 1 to Table 3 inclusive and Clauses 9 to 15 inclusive.

9 Length of bolts and screws

a. The nominal length of a bolt or screw shall be the distance from the underside of the head to the extreme end of the shank including any chamfer or radius.

NOTE The nominal lengths of bolts and screws normally stocked are given in Appendix D.

b. The permissible tolerance on the nominal length shall be as given below:

Nominal length in	Diameter in	Tolerance of length in
Up to and including 1	Up to and including $\frac{3}{4}$	+ 0 – $\frac{1}{32}$
	Over $\frac{3}{4}$	+ 0 – $\frac{1}{16}$
Over 1 up to and including 2	Up to and including $\frac{3}{4}$	+ 0 – $\frac{1}{16}$
	Over $\frac{3}{4}$	+ 0 – $\frac{1}{8}$
Over 2 up to and including 6	Up to and including $\frac{3}{4}$	+ 0 – $\frac{3}{32}$
	Over $\frac{3}{4}$	+ 0 – $\frac{3}{16}$
Over 6	All diameters	+ 0 – $\frac{3}{16}$

10 Ends of bolts and screws

The ends of bolts and screws may, at the option of the manufacturer, be finished with either a 45° chamfer to a depth slightly exceeding the depth of thread or a radius approximately equal to $1\frac{1}{4}$ times the nominal diameter of shank. When bolts and screws are made with rolled threads the lead formed at the end of the bolt by the thread rolling operation may be regarded as providing the necessary chamfer to the end, no other machining operation being necessary, and the end shall be reasonably square with the centre line of the shank.

11 Screw threads

- a. *General.* The screw threads on bolts, screws and nuts up to and including 1 inch nominal size shall be Unified coarse (UNC) or Unified fine (UNF) in accordance with BS 1580, “*Unified screw threads*,” as specified by the purchaser. The screw threads on bolts, screws and nuts in nominal sizes above 1 in shall be Unified coarse (UNC) in accordance with BS 1580. If a finer thread is required on bolts, screws and nuts in nominal sizes above 1 in, it is recommended that the 8-thread series be used.
- b. *Bolts and screws.* The screw threads may be either cut or rolled at the option of the manufacturer and shall conform to the limits and tolerances for Class 2A specified in BS 1580.
- c. *Nuts.* The screw threads shall conform to the limits and tolerances for Class 2B specified in BS 1580.
- d. *Gauging of screw threads.* Screw threads shall be gauged in accordance with the system recommended in BS 919-1, “*Gauges for screw threads of Unified form*.” The NOT GO effective diameter screw plug gauge used for checking nuts shall be of the low addendum form specified in that standard.

12 Length of thread

- a. *Bolts.* The length of thread on bolts shall be the distance from the end of the bolt (including any chamfer or radius) to the leading face of a screw ring gauge which has been screwed as far as possible on to the bolt by hand.

The minimum thread length shall be twice the diameter plus $\frac{1}{4}$ in for lengths up to and including 6 in, and twice the diameter plus $\frac{1}{2}$ in for lengths over 6 in.

Bolts that are too short for minimum thread lengths shall be threaded as screws and shall be designated screws.

NOTE The shortest designated lengths for bolts are tabulated for guidance in Appendix D.

- b. *Screws.* Screws shall be threaded to permit of a screw ring gauge being screwed by hand to within a distance from the underside of the head not exceeding two and a half times the pitch for diameters up to and including 1 in and three and a half times the pitch for diameters over 1 in.
- c. *Tolerances.*

- i) *Tolerance on bolt thread length.* The tolerance on thread length shall be plus $\frac{3}{16}$ in or $2\frac{1}{2}$ threads, whichever is the greater, for all lengths.
- ii) *Tolerance on eccentricity.* Tolerance on eccentricity (including out of parallelism) of thread in relation to body for sizes up to and including $\frac{3}{4}$ in shall be 0.010 in for each inch of length when measured in a sleeve gauge. For sizes over $\frac{3}{4}$ in, total eccentricity shall be the subject of agreement between manufacturer and purchaser.

NOTE Details of the sleeve gauge referred to above are given in Appendix C.

13 Nuts, squareness of thread to face

The axis of the thread of the nut shall be square to the face of the nut subject to the “squareness tolerance” specified in Table 2, Column 13.

The nut shall be screwed by hand on to a gauge having a truncated taper thread until the thread of the nut is tight on the thread of the gauge. A sleeve sliding on a parallel extension of the gauge, and which has a face of diameter equal to the minimum distance across flats of the nut and exactly at 90° to the axis of the gauge shall be brought into contact with the leading face of the nut. With the sleeve in this position it shall not be possible for a feeler gauge of thickness equal to the “squareness tolerance” to enter anywhere between the leading face of the nut and the face of the sleeve (see Figure 20 in Appendix C).

14 Chamfering, washer facing and countersinking

a. *Bolts and screws.* Bolts and screw heads shall have a chamfer of approximately 30° on their upper faces and, at the option of the manufacturer, a washer face or full bearing face on the underside.

b. *Nuts* i) Ordinary nuts, thick ordinary nuts, slotted nuts and thick slotted nuts shall have a chamfer of 30° on their upper faces and at the option of the manufacturer, a similar chamfer or a washerface on their lower faces.

ii) Lock nuts shall have a chamfer of approximately 30° on both faces.

iii) All nuts shall be countersunk on the bearing face at an included angle of $120 \pm 10^\circ$; the diameter of the countersink shall not exceed the nominal major diameter of the thread (see Figure 11).

With the exception of slotted nuts, all hexagon nuts chamfered at both ends shall also have a countersink as above at both ends of the thread.

NOTE The option referred to in sub-clauses a) and b) above shall apply unless the purchaser in his enquiry and order specifically states that he requires one of the alternatives available.

Attention is drawn to the fact that these alternative methods of finishing the underside of bolt and screw heads and the lower face of nuts are associated both with the nominal size and the particular method of manufacture. A request by the purchaser for a specific type of finish limits the manufacturing processes available and it is therefore recommended that the purchaser avoids making such a request unless circumstances fully justify it.

15 Split-pin holes and slots

Bolts with split-pin holes will be supplied only when specially ordered. The purchaser should state, in his enquiry and order, Dimension J (see Figure 1).

A tolerance of $+ \frac{1}{32}$ in $- 0$ shall be permissible on the specified Dimension J.

The maximum “off-centre” distance between the centreline of the split-pin hole in bolts and the axis of the thread is given in Table 1, Column 18. This shall be checked by means of a screwed ring gauge with appropriate slot and a plain plug gauge which shall be a Go gauge in the minimum split-pin hole (see Figure 21 in Appendix C).

The maximum “off-centre” distance between the centreline of the slots in slotted nuts and the axis of the tapped hole is given in Table 3, Column 13. This shall be checked by means of a screwed plug gauge with appropriate slot and a plain plug gauge which shall be a Go gauge in the minimum slot (see Figure 22 in Appendix C).

NOTE For full dimensional and other requirements of split cotter pins, reference should be made to BS 1574, “*Split cotter pins.*”

16 Marking

a. *Bolts and screws.* i) Bolts and screws shall have the appropriate grade letter (see Table 4, Appendix A) marked on the head. The letter shall be either indented or embossed, but if embossed the letter shall not project more than $\frac{1}{64}$ in.

ii) All bolts and screws shall be identified as “Unified” by means of the application of either of the following features, full details of which are given in Appendix E.

A circular recess in the upper surface of the head or,

A line of contiguous circles indented on one or more of the flats of the hexagon and parallel to the axis of the bolt or screw.

b. i) Nuts (see Clause 6) shall have the appropriate grade number indented on one of the flats of the hexagon or on the non-bearing face.

ii) All nuts shall be identified as “Unified” by means of the application of one of the following features, full details of which are given in Appendix E:

A circular groove of semi-circular section indented in the non-bearing face, or

A line of contiguous circles indented on one or more of the flats of the hexagon and parallel to the axis of the nut, or

A recess in the non-bearing face of the nut.

The last named method of identification is for use on washer-faced nuts only.

c. *Manufacturer's trade mark.* Bolts, screws and nuts shall be marked with the manufacturer's identification (trade) mark.

17 Inspection and testing

The manufacturer shall take the necessary steps to ensure that the requirements specified in this standard are fulfilled, but if, in addition, the purchaser desires the manufacturer to certify or demonstrate that the bolts, screws, and nuts comply with this standard, the details and cost of any further inspection entailed shall be the subject of agreement between the purchaser and the manufacturer.

Table 1 — Unified hexagon head bolts and screws — Normal series
(Third Angle Projection)

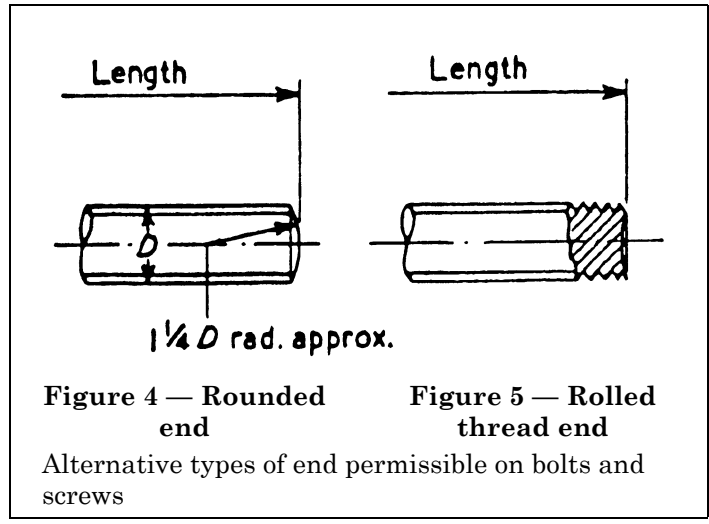
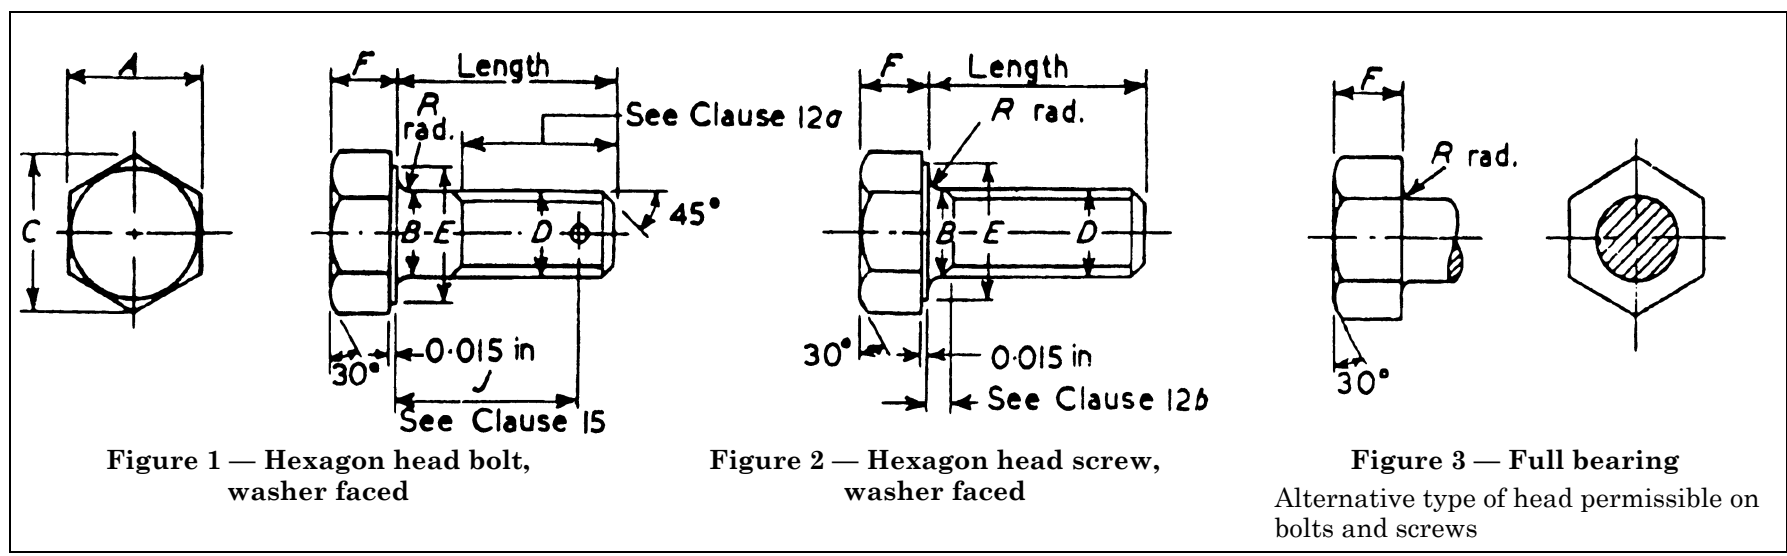


Table 1 — Unified hexagon head bolts and screws — Normal series

1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18
Nominal size <i>D</i>	Number of threads per inch	Diameter of unthreaded portion of shank <i>B</i>	Width across flats <i>A</i>		Width across corners <i>C</i>	Diameter of washer face <i>E</i>		Thickness of head <i>F</i>		Radius under head <i>R</i>		Split cotter pin holes. See clause 15					
												Diameter of hole		Drill sizes	Maximum off-centre distance between centre line of hole and thread		
	UNC	UNF	Max.	Min.	Max.	Min. ^b	Max.	Max.	Min.	Max.	Min.	Max.	Min.	Max.	Min.		
in			in	in	in	in	in	in	in	in	in	in	in	in	in	mm	in
$1/4$	20	28	0.250 0	0.246 5	0.437 5	0.430 5	0.505	0.421	0.411	0.163	0.153	0.025	0.015	0.084	0.079	2.00	0.006
$5/16$	18	24	0.312 5	0.309 0	0.500 0	0.493 0	0.577	0.483	0.473	0.211	0.201	0.025	0.015	0.100	0.095	2.40	0.006
$3/8$	16	24	0.375 0	0.371 5	0.562 5	0.554 5	0.650	0.545	0.535	0.243	0.233	0.025	0.015	0.117	0.112	2.85	0.006
$7/16$	14	20	0.437 5	0.433 5	0.625 0	0.617 0	0.722	0.605	0.595	0.291	0.281	0.025	0.015	0.117	0.112	2.85	0.007
$1/2$	13	20	0.500 0	0.496 0	0.750 0	0.742 0	0.866	0.730	0.720	0.323	0.313	0.025	0.015	0.152	0.146	3.70	0.007
^a $9/16$	12	18	0.562 5	0.558 5	0.812 5	0.804 5	0.938	0.792	0.782	0.371	0.361	0.045	0.020	0.152	0.146	3.70	0.008
$5/8$	11	18	0.625 0	0.619 0	0.937 5	0.929 5	1.083	0.918	0.908	0.403	0.393	0.045	0.020	0.184	0.177	4.50	0.008
$3/4$	10	16	0.750 0	0.744 0	1.125 0	1.115 0	1.300	1.100	1.090	0.483	0.463	0.045	0.020	0.184	0.177	4.50	0.009
$7/8$	9	14	0.875 0	0.867 0	1.312 5	1.300 5	1.515	1.285	1.275	0.563	0.543	0.065	0.040	0.184	0.177	4.50	0.009
1	8	See clause 11	1.000 0	0.992 0	1.500 0	1.488 0	1.732	1.473	1.463	0.627	0.597	0.095	0.060	0.222	0.213	5.40	0.010
$1 1/8$	7		1.125 0	1.117 0	1.687 5	1.657 5	1.948	1.641	1.625	0.718	0.678	0.095	0.060	0.222	0.213	5.40	0.010
$1 1/4$	7		1.250 0	1.242 0	1.875 0	1.830 0	2.165	1.813	1.797	0.813	0.773	0.095	0.060	0.254	0.244	6.20	0.011
^a $1 3/8$	6		1.375 0	1.365 0	2.062 5	2.017 5	2.382	2.001	1.985	0.878	0.838	0.095	0.060	0.254	0.244	6.20	0.011
$1 1/2$	6		1.500 0	1.490 0	2.250 0	2.205 0	2.598	2.188	2.172	0.974	0.934	0.095	0.060	0.290	0.280	7.10	0.011
$1 3/4$	5		1.750 0	1.740 0	2.625 0	2.565 0	3.031	2.543	2.527	1.134	1.074	0.095	0.060	0.353	0.343	8.70	0.012
2	$4 1/2$		2.000 0	1.990 0	3.000 0	2.940 0	3.464	2.918	2.902	1.263	1.203	0.095	0.060	0.353	0.343	8.70	0.015

NOTE In the case of the $7/16$ in and $9/16$ in bolt heads, the width across flats is $1/16$ in smaller than that of the corresponding nuts. This is in accordance with the American Standard from which these sizes are derived.

^a To be dispensed with wherever possible.

^b When bolts from $1/4$ in to 1 in nominal size are hot forged, the tolerance on the width across flats shall be two and a half times the tolerance shown in the table.

Table 2 — Unified hexagon ordinary nuts, thick ordinary nuts and lock nuts — Normal series
(Third Angle Projection)

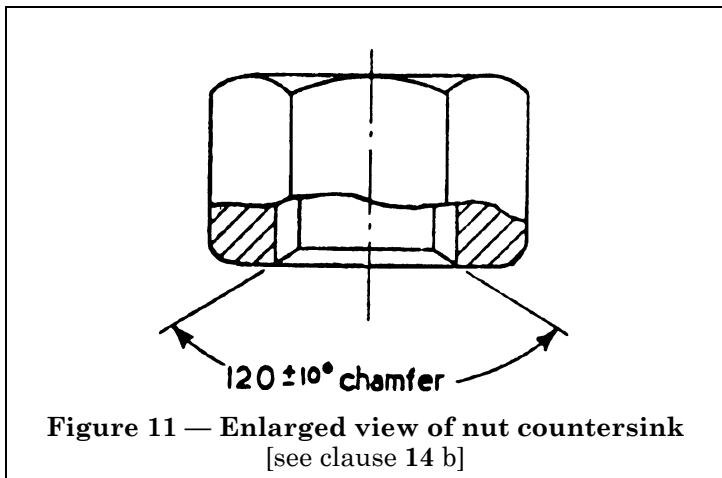
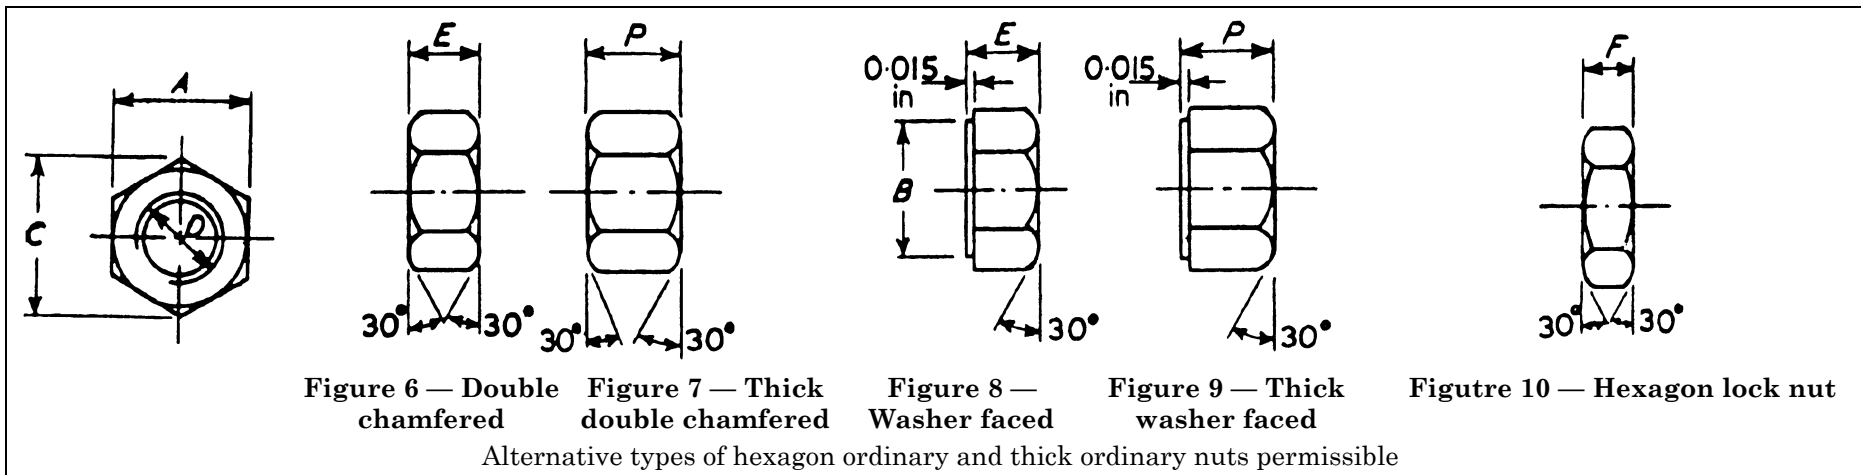


Table 2 — Unified hexagon ordinary nuts, thick ordinary nuts and lock nuts — Normal series

1	2	3	4	5	6	7	8	9	10	11	12	13
Nominal size <i>D</i>	Width across flats <i>A</i>		Width across corners <i>C</i>	Diameter of washer face <i>B</i>		Thickness						Tolerance on squareness of thread to face of nut
						Ordinary nuts <i>E</i>		Thick ordinary nuts <i>P</i>		Lock nuts <i>F</i>		
	Max.	Min.	Max.	Max.	Min.	Max.	Min.	Max.	Min.	Max.	Min.	Max.
in	in	in	in	in	in	in	in	in	in	in	in	in
1/4	0.437 5	0.430 5	0.505	0.421	0.411	0.224	0.214	0.286	0.276	0.161	0.151	0.007
5/16	0.500 0	0.493 0	0.577	0.483	0.473	0.271	0.261	0.333	0.323	0.192	0.182	0.009
3/8	0.562 5	0.554 5	0.650	0.545	0.535	0.333	0.323	0.411	0.401	0.224	0.214	0.010
7/16	0.687 5	0.679 5	0.794	0.668	0.658	0.380	0.370	0.458	0.448	0.255	0.245	0.011
1/2	0.750 0	0.742 0	0.866	0.730	0.720	0.442	0.432	0.567	0.557	0.317	0.307	0.013
^a 9/16	0.875 0	0.867 0	1.010	0.855	0.845	0.489	0.479	0.614	0.604	0.349	0.339	0.013
5/8	0.937 5	0.929 5	1.083	0.918	0.908	0.552	0.542	0.724	0.714	0.380	0.370	0.014
3/4	1.125 0	1.115 0	1.300	1.100	1.090	0.651	0.631	0.822	0.802	0.432	0.412	0.017
7/8	1.312 5	1.300 5	1.515	1.285	1.275	0.760	0.740	0.916	0.896	0.494	0.474	0.020
1	1.500 0	1.488 0	1.732	1.473	1.463	0.874	0.844	1.015	0.985	0.562	0.532	0.020
1 1/8	1.687 5	1.657 5	1.948	1.641	1.625	0.989	0.949	1.176	1.136	0.629	0.589	0.024
1 1/4	1.875 0	1.830 0	2.165	1.813	1.797	1.087	1.037	1.275	1.225	0.744	0.694	0.024
^a 1 3/8	2.062 5	2.017 5	2.382	2.001	1.985	1.197	1.147	1.400	1.350	0.806	0.756	0.026
1 1/2	2.250 0	2.205 0	2.598	2.188	2.172	1.311	1.251	1.530	1.470	0.874	0.814	0.026
1 3/4	2.625 0	2.565 0	3.031	2.543	2.527	1.530	1.470	—	—	0.999	0.939	0.030
2	3.000 0	2.940 0	3.464	2.918	2.902	1.754	1.684	—	—	1.129	1.059	0.030

NOTE In the case of the 7/16 in and 9/16 in nuts, the width across flats is 1/16 in larger than that of the corresponding bolt heads. This is in accordance with the American Standards from which these sizes are derived.

^a To be dispensed with wherever possible.

^b When nuts from 1/4 in to 1 in nominal size are hot forged, the tolerance on width across flats shall be two and a half times the tolerance shown in the table.

Table 3 — Unified hexagon slotted nuts and thick slotted nuts — Normal series
(Third Angle Projection)

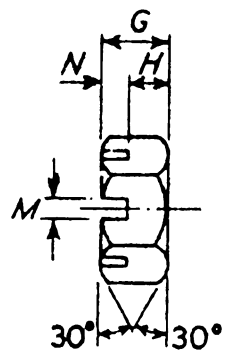


Figure 12 — Double chamfered

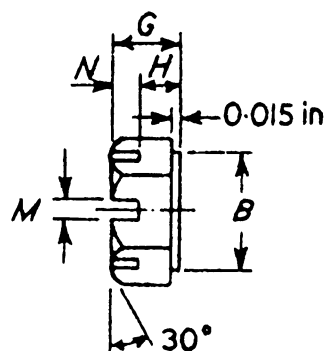


Figure 13 — Washer faced

Alternative types of hexagon slotted nuts

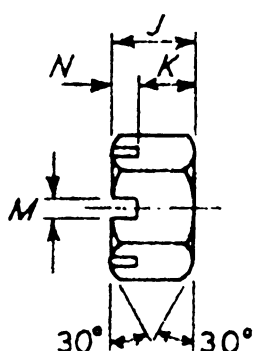


Figure 14 — Double chamfered

Alternative types of hexagon thick slotted nuts

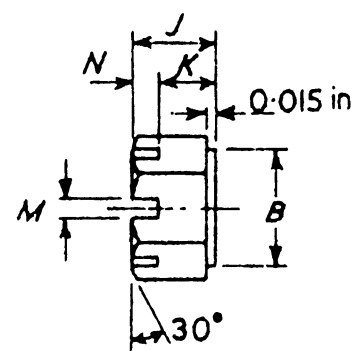


Figure 15 — Washer faced

Table 3 — Unified hexagon slotted nuts and thick slotted nuts — Normal series

1	2	3	4	5	6	7	8	9	10	11	12	13	14
Nominal size <i>D</i>	Slotted nuts				Thick slotted nuts				Slotted nuts and thick slotted nuts			Maximum off-centre distance between centre line of slot and tapped hole	Tolerance on squareness of thread to face of nut
	Thickness		Lower face of nut to bottom of slot		Thickness		Lower face of nut to bottom of slot		Width of slot		Depth of slot		
	<i>G</i>		<i>H</i>		<i>J</i>		<i>K</i>		<i>M</i>		<i>N</i>		Max.
in	in	in	in	in	in	in	in	in	in	in	in	in	in
1/4	0.224	0.214	0.161	0.151	0.286	0.276	0.224	0.214	0.088	0.078	0.062	0.012	0.007
5/16	0.271	0.261	0.177	0.167	0.333	0.323	0.239	0.229	0.104	0.094	0.094	0.012	0.009
3/8	0.333	0.323	0.224	0.214	0.411	0.401	0.302	0.292	0.135	0.125	0.109	0.012	0.010
7/16	0.380	0.370	0.255	0.245	0.458	0.448	0.333	0.323	0.135	0.125	0.125	0.014	0.011
1/2	0.442	0.432	0.302	0.292	0.567	0.557	0.427	0.417	0.166	0.156	0.141	0.014	0.013
a9/16	0.489	0.479	0.333	0.323	0.614	0.604	0.458	0.448	0.166	0.156	0.156	0.017	0.013
5/8	0.552	0.542	0.364	0.354	0.724	0.714	0.536	0.526	0.198	0.188	0.187	0.017	0.014
3/4	0.651	0.631	0.432	0.412	0.822	0.802	0.604	0.584	0.198	0.188	0.219	0.022	0.017
7/8	0.760	0.740	0.510	0.490	0.916	0.896	0.666	0.646	0.198	0.188	0.250	0.022	0.020
1	0.874	0.844	0.593	0.563	1.015	0.985	0.734	0.704	0.260	0.250	0.281	0.027	0.020
1 1/8	0.989	0.949	0.661	0.621	1.176	1.136	0.848	0.808	0.260	0.250	0.328	0.027	0.024
1 1/4	1.087	1.037	0.728	0.678	1.275	1.225	0.916	0.866	0.322	0.312	0.359	0.032	0.024
a1 3/8	1.197	1.147	0.806	0.756	1.400	1.350	1.009	0.959	0.322	0.312	0.391	0.032	0.026
1 1/2	1.311	1.251	0.889	0.829	1.530	1.470	1.108	1.048	0.385	0.375	0.422	0.037	0.026
1 3/4	1.530	1.470	1.030	0.970	—	—	—	—	0.448	0.438	0.500	0.037	0.030
2	1.754	1.684	1.176	1.106	—	—	—	—	0.448	0.438	0.578	0.042	0.030

NOTE In the case of the 7/16 in and 9/16 in nuts, the width across flats is 1/16 in larger than that of the corresponding bolt heads. This is in accordance with the American Standard from which these sizes are derived.

^a To be dispensed with wherever possible. For widths across flats, widths across corners, and diameter of washer face, see Table 2.

Appendix A Mechanical properties of finished steel hexagon head bolts and screws and hexagon nuts

Table 4 — Bolts and screws
(See clauses 4 and 5)

1	2	3	4	5	6	7	8
Grade	Properties of finished bolts						
	Minimum tensile strength (see NOTE 1)	Stress for proof load (see Table 5)	Minimum elongation on a gauge length 4√area (see NOTE 2)	Minimum Izod impact value			Brinell hardness numbers [see Clause 4 d)]
				Diameter or width across flats			
				Up to 3/4 in ft lbf	Over 3/4 in up to and including 1 1/8 in ft lbf	Over 1 1/8 in ft lbf	
A	28	—	10/14 (see NOTE 3)	—	—	—	—
B	28	—	17	—	—	—	—
P	35	20	15	20	15	10	152/240
S	50	38	18	35	30	20	223/310
T	55	41	16	35	30	20	248/335
V	65	49.5	14	35	30	20	293/370
X	75	60	12	15	15	10	341/410

NOTE 1 The cross sectional area of the thread used in calculation is obtained by the following formula.

$$\text{Area} = \pi \left(\frac{\text{Basic effective diameter}^a + \text{basic minor diameter}^a}{4} \right)^2$$

NOTE 2 BS 18 now specifies a gauge length of 5.65√Area, but elongation values appropriate to this length are not yet available for the higher grades of steel. The values in Column 4 have therefore been retained pending further information on this subject.

NOTE 3 For Grade A bolts or screws the minimum elongation shall be 10 per cent for 1/4 in and 5/16 in nominal sizes and 14 per cent for all other sizes up to and including 2 in.

^a As specified for the thread in question in BS 1580 "Unified screw threads."

**Table 4A — Comparison of strength grades of BS 1768
and BS 970 (for guidance only)**

Grade	Tensile strength		
	BS 1768		BS 970-1:1983
	min.	min.	
	tonf/m ²	N/mm ²	N/mm ²
P	35	541	550 – 700
S	50	772	775 – 925
T	55	849	850 – 1 000
V	65	1 004	1 000 – 1 150
X	75	1 158	1 150 – 1 300

Table 5 — Proof loads for bolts and screws
(see Column 2 of Table 4)

Nominal size of bolt or screw	Stress area		Grade P		Grade S		Grade T		Grade V		Grade X	
			Proof stress 20 tonf/in ²		Proof stress 38 tonf/in ²		Proof stress 41 tonf/in ²		Proof stress 49.5 tonf/in ²		Proof stress 60 tonf/in ²	
	UNC	UNF	Proof load									
	UNC	UNF	UNC	UNF	UNC	UNF	UNC	UNF	UNC	UNF	UNC	UNF
in	in ²	in ²	ton	ton	ton	ton	ton	ton	ton	ton	ton	ton
1/4	0.0324	0.0368	0.648	0.736	1.231	1.398	1.328	1.509	1.603	1.822	1.944	2.208
5/16	0.0532	0.0587	1.064	1.174	2.021	2.230	2.181	2.406	2.633	2.905	3.192	3.522
3/8	0.0786	0.0886	1.572	1.772	2.986	3.367	3.222	3.633	3.890	4.385	4.716	5.316
7/16	0.1078	0.1198	2.156	2.396	4.097	4.552	4.420	4.911	5.335	5.929	6.468	7.188
1/2	0.1438	0.1612	2.876	3.224	5.466	6.127	5.896	6.610	7.119	7.980	8.628	9.672
9/16	0.184	0.205	3.68	4.10	6.992	7.791	7.544	8.407	9.107	10.15	11.04	12.30
5/8	0.229	0.258	4.58	5.16	8.702	9.804	9.389	10.58	11.33	12.77	13.74	15.48
3/4	0.338	0.375	6.76	7.50	12.84	14.25	13.86	15.38	16.73	18.57	20.28	22.50
7/8	0.467	0.513	9.34	10.26	17.74	19.49	19.14	21.03	23.12	25.39	28.02	30.78
1	0.612	0.667	12.24	13.34	23.26	25.34	25.09	27.35	30.30	33.01	36.72	40.02
1 1/8	0.771	—	15.42	—	29.30	—	31.61	—	38.17	—	46.26	—
1 1/4	0.978	—	19.56	—	37.16	—	40.10	—	48.41	—	58.68	—
1 3/8	1.166	—	23.32	—	44.31	—	47.80	—	57.72	—	69.96	—
1 1/2	1.418	—	28.36	—	53.89	—	58.15	—	70.20	—	85.08	—
1 3/4	1.92	—	38.4	—	72.97	—	78.72	—	95.04	—	115.2	—
2	2.52	—	50.4	—	95.76	—	103.3	—	124.7	—	151.2	—

Stress area × proof stress = proof load

Table 6 — Proof loads for nuts¹⁾
(See clause 6)

Nominal size of nut	Stress area of bolts		Grade 0 nuts		Grade 1 nuts		Grade 3 nuts		Grade 5 nuts	
			For use with bolts of grades A, B, P		For use with bolts of grade S		For use with bolts of grade T		For use of bolts of grades V, X	
			Min. tensile of grade P bolts 35 tonf/in ²		Min. tensile of grade S bolts 50 tonf/in ²		Min. tensile of grade T bolts 55 tonf/in ²		Min. tensile of grade X bolts 75 tonf/in ²	
	Proof load									
	UNC	UNF	UNC	UNF	UNC	UNF	UNC	UNF	UNC	UNF
in	in ²	in ²	ton	ton	ton	ton	ton	ton	ton	ton
1/4	0.0324	0.0368	1.134	1.288	1.620	1.840	1.782	2.024	2.430	2.760
5/16	0.0532	0.0587	1.862	2.054	2.660	2.935	2.926	3.228	3.990	4.402
3/8	0.0786	0.0886	2.751	3.101	3.930	4.430	4.323	4.873	5.895	6.645
7/16	0.1078	0.1198	3.773	4.193	5.390	5.990	5.929	6.589	8.085	8.985
1/2	0.1438	0.1612	5.034	5.643	7.190	8.060	7.911	8.869	10.78	12.09
9/16	0.184	0.205	6.440	7.176	9.200	10.25	10.12	11.28	13.80	15.37
5/8	0.229	0.258	8.015	9.031	11.45	12.90	12.60	14.19	17.17	19.35
3/4	0.338	0.375	11.83	13.12	16.90	18.75	18.59	20.63	25.35	28.12
7/8	0.467	0.513	15.97	17.96	23.35	25.65	25.68	28.21	35.02	38.47
1	0.612	0.667	21.42	23.34	30.60	33.35	33.67	36.68	45.90	50.02

Stress area × min. tensile strength of bolt = proof load of nuts

¹⁾ The proof load values in this table apply only to ordinary nuts and thick ordinary nuts and not to lock-nuts or slotted nuts.

Appendix B Materials

In Table 7, Table 8, Table 9 and Table 10, for comparisons between EN No. steels and the 6-digit designations see Appendix D of BS 970-1:1983.

Table 7 — Examples of suitable material for cold forged bolts and screws

The following table is for guidance only; grades of steel shown and ruling sections are not mandatory. The finished products shall satisfy the requirements for physical properties set out in Clause 4 and Table 4 of Appendix A.

Grade	Nominal size of bolt or screw ^a	Material ^b
A and B	All sizes	Good commercial quality low carbon steel
P	Up to and including 1 in	BS 970 — EN 2, A to D BS 970 — EN 5 BS 3111 — Type 0 BS 3111 — Type 1 BS 3111 — Type 9
S	Up to and including $\frac{7}{8}$ in Up to and including 1 in	BS 3111 — Type 1 BS 3111 — Type 2 BS 3111 — Type 3 BS 3111 — Type 9 BS 3111 — Type 10
T	Up to and including $\frac{1}{2}$ in Up to and including 1 in	BS 3111 — Type 1 BS 3111 — Type 2 BS 3111 — Type 3 BS 3111 — Type 9 BS 3111 — Type 10
V	Up to and including $\frac{3}{8}$ in Up to and including $\frac{3}{4}$ in Up to and including 1 in	BS 3111 — Type 1 BS 3111 — Type 2 BS 3111 — Type 3 BS 3111 — Type 9 BS 3111 — Type 5 BS 3111 — Type 7 BS 3111 — Type 10
X	Up to and including $\frac{3}{8}$ in Up to and including $\frac{5}{8}$ in Up to and including $\frac{3}{4}$ in	BS 3111 — Type 2 BS 3111 — Type 3 BS 3111 — Type 5 BS 3111 — Type 7 BS 3111 — Type 10
^a Limiting ruling section. ^b BS 970-1:1983. BS 3111-1:1977.		

Table 8 — Materials for hot forged bolts and screws

The following table is given for guidance only and the grades of steel and the limiting ruling sections listed here are not mandatory. Unless otherwise stipulated, the final choice of the materials used to provide the physical properties given in Appendix A will be left to the manufacturer. (See Clause 2).

When materials selected from this table are used, the mechanical properties referred to above are obtained by oil quenching and tempering at a suitable temperature.

Grade	Nominal size of bolt or screw ^a	Material to BS 970 ^b
A and B	All sizes	Good commercial quality low carbon steel
P	Up to and including 2 in	EN 5 EN 7 EN 8
S	Up to and including 1/2 in	EN 5C
	Up to and including 3/4 in	EN 8
S	Up to and including 7/8 in	EN 15
	Up to and including 1 in	EN 12
		EN 18
		EN 111
	Up to and including 2 in	EN 16
		EN 17
		EN 19
		EN 24
		EN 25
		EN 26
EN 100		
EN 110		
T	Up to and including 1/2 in	EN 8 EN 15
	Up to and including 7/8 in	EN 12
	Up to and including 1 in	EN 18
		EN 111
	T	Up to and including 2 in
EN 17		
EN 19		
EN 24		
EN 25		
EN 26		
EN 100		
EN 110		

^a Limiting ruling section.

^b BS 970-1:1983. Mechanical properties relating to steels specified in BS 970-1 are for steels subjected to bulk heat treatment; significantly higher properties will be obtained by heat treatment in the finished component form.

Table 8 — Materials for hot forged bolts and screws

Grade	Nominal size of bolt or screw ^a	Material to BS 970 ^b		
V	Up to and including $\frac{3}{8}$ in	EN 8		
	Up to and including $\frac{1}{2}$ in	EN 15		
	Up to and including $\frac{5}{8}$ in	EN 12		
	Up to and including $\frac{3}{4}$ in	{ EN 18 EN 111		
	Up to and including $\frac{7}{8}$ in	EN 16		
	Up to and including $1\frac{1}{8}$ in	{ EN 17 EN 19 EN 100 EN 110		
		Up to and including 2 in	{ EN 24 EN 25 EN 26	
			X	Up to and including $\frac{1}{2}$ in
	Up to and including $\frac{5}{8}$ in			{ EN 16 EN 17 EN 18 EN 111
		Up to and including $\frac{3}{4}$ in		EN 100
Up to and including 1 in		{ EN 19 EN 110		
		Up to and including $1\frac{1}{8}$ in		EN 24
Up to and including 2 in	{ EN 25 EN 26			
	^a Limiting ruling section. ^b BS 970-1:1983. Mechanical properties relating to steels specified in BS 970-1 are for steels subjected to bulk heat treatment; significantly higher properties will be obtained by heat treatment in the finished component form.			

Table 9 — Materials for bolts and screws turned from bar

The following table is given for guidance only and the grades of steel and limiting ruling sections listed here are not mandatory. Unless otherwise stipulated, the final choice of the materials used to provide the physical properties given in Appendix A will be left to the manufacturer (see Clause 2).

Grade	Width across flats ^a	Material to BS 970 ^b
A	Up to and including 1½ in	EN 1A
	Up to and including 3 in	EN 7A
B	Up to and including 3 in	EN 3B
P	Up to and including 1¾ in	EN 7
	Up to and including 3 in	EN 8
S	Up to and including 2½ in	EN 18S
	Up to and including 3 in	EN 16S
T	Up to and including 2½ in	EN 16T
	Up to and including 3 in	EN 17T
V	Up to and including 2½ in	EN 24V
	Up to and including 3 in	EN 25V EN 26V
X	Up to and including 1⅛ in	EN 24X
	Up to and including 2½ in	EN 25X
	Up to and including 3 in	EN 26X

^a Limiting ruling section.
^b Appendix C of BS 970-1:1983.

Table 10 — Materials for nuts


The following table is given for guidance only and the grades of steel listed here are not mandatory. Unless otherwise stipulated, the final choice of the materials used to give the physical properties specified for the finished nuts in Clause 6 and Table 6 will be left to the manufacturer.

Grade	Cold formed	Hot forged	Turned from the bar
0	Good commercial quality steel	Good commercial quality steel	Good commercial quality steel
1	EN 2A to D EN 5	EN 3, EN 5 EN 8	EN 1A, EN 7 EN 8M
3	EN 5 BS 3111, Type 1 BS 3111, Type 9	EN 5, EN 8	EN 7, EN 8M EN 15M
5	EN 5 BS 3111, Type 1 BS 3111, Type 9	EN 8, EN 12 EN 15, EN 16	EN 8M, EN 15M EN 16M

Appendix C Testing fixtures and recommended gauges


Testing Fixtures

C.1 Proof load test for bolts and screws. *Clause 5.*

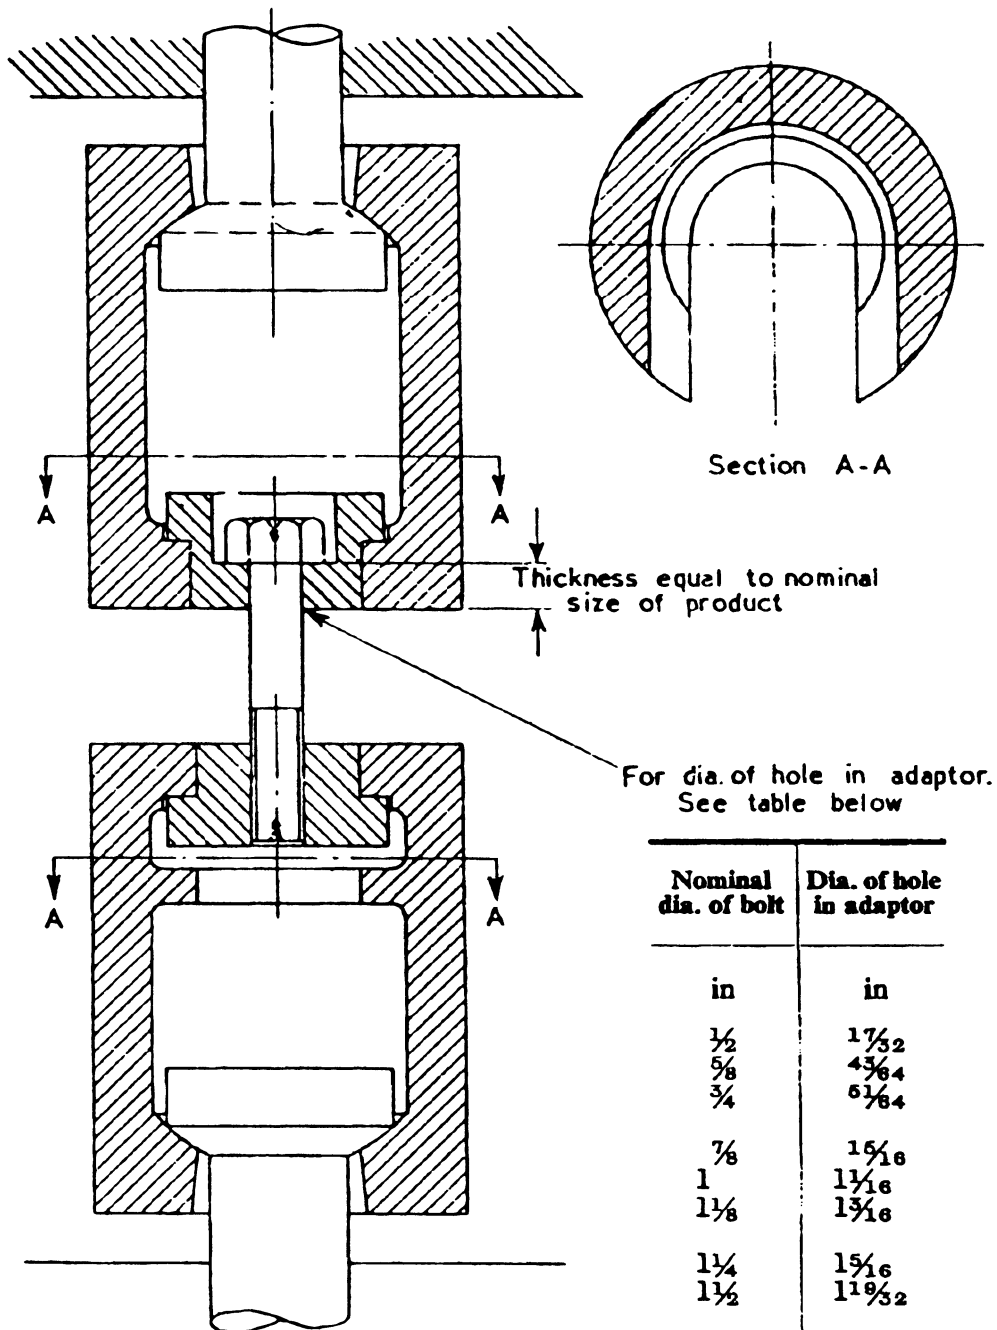


Adaptors to have a hardness of 270/320 HV30

Figure 16

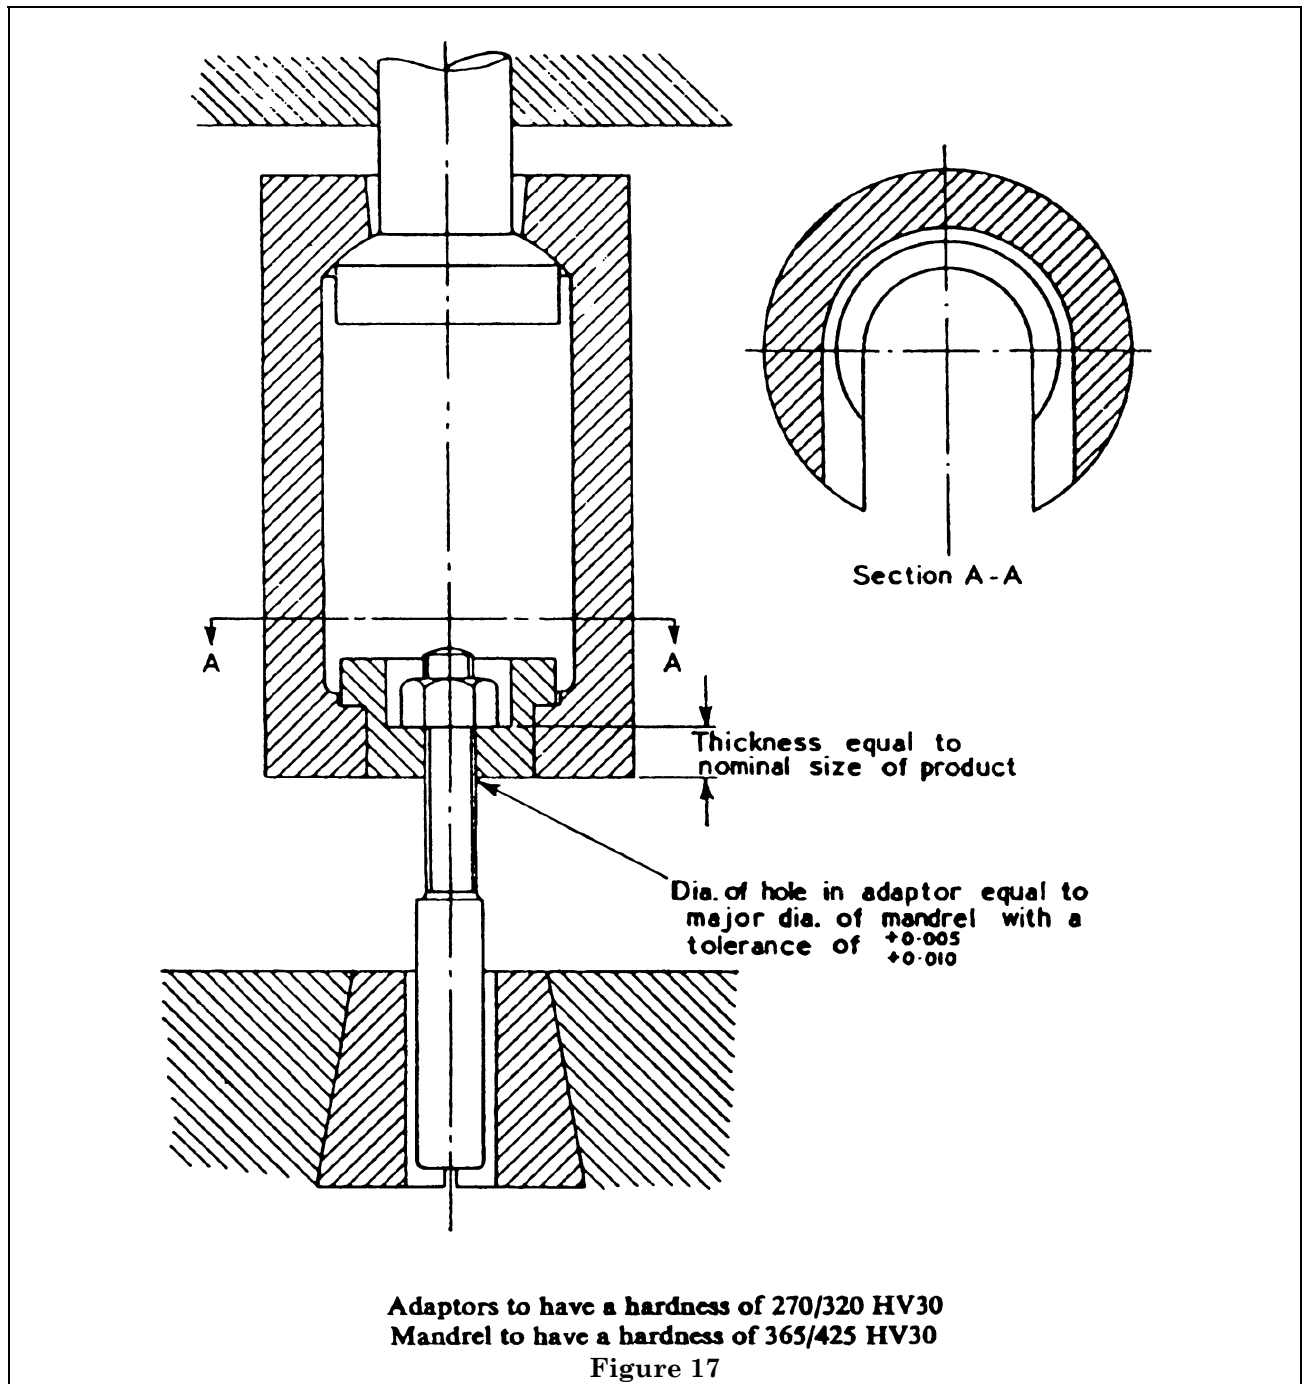
C.2 Proof load test for nuts. *Clause 6.*

Recommended Gauges

Details of gauges suitable for checking various features of the bolts, screws and nuts specified in this standard are given below. They are offered for guidance and do not form part of the requirements of this standard.

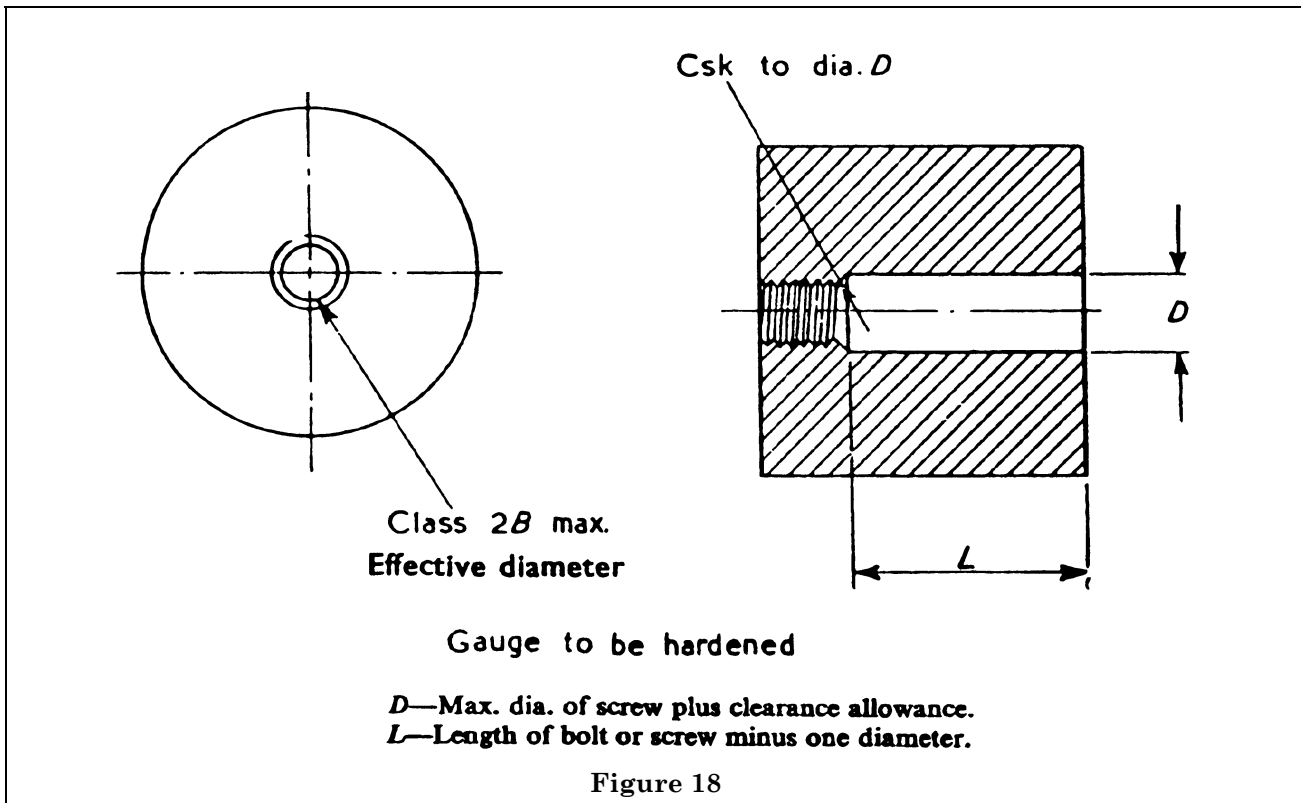C.3 Eccentricity. *Clause 12 c ii).*

Optional construction

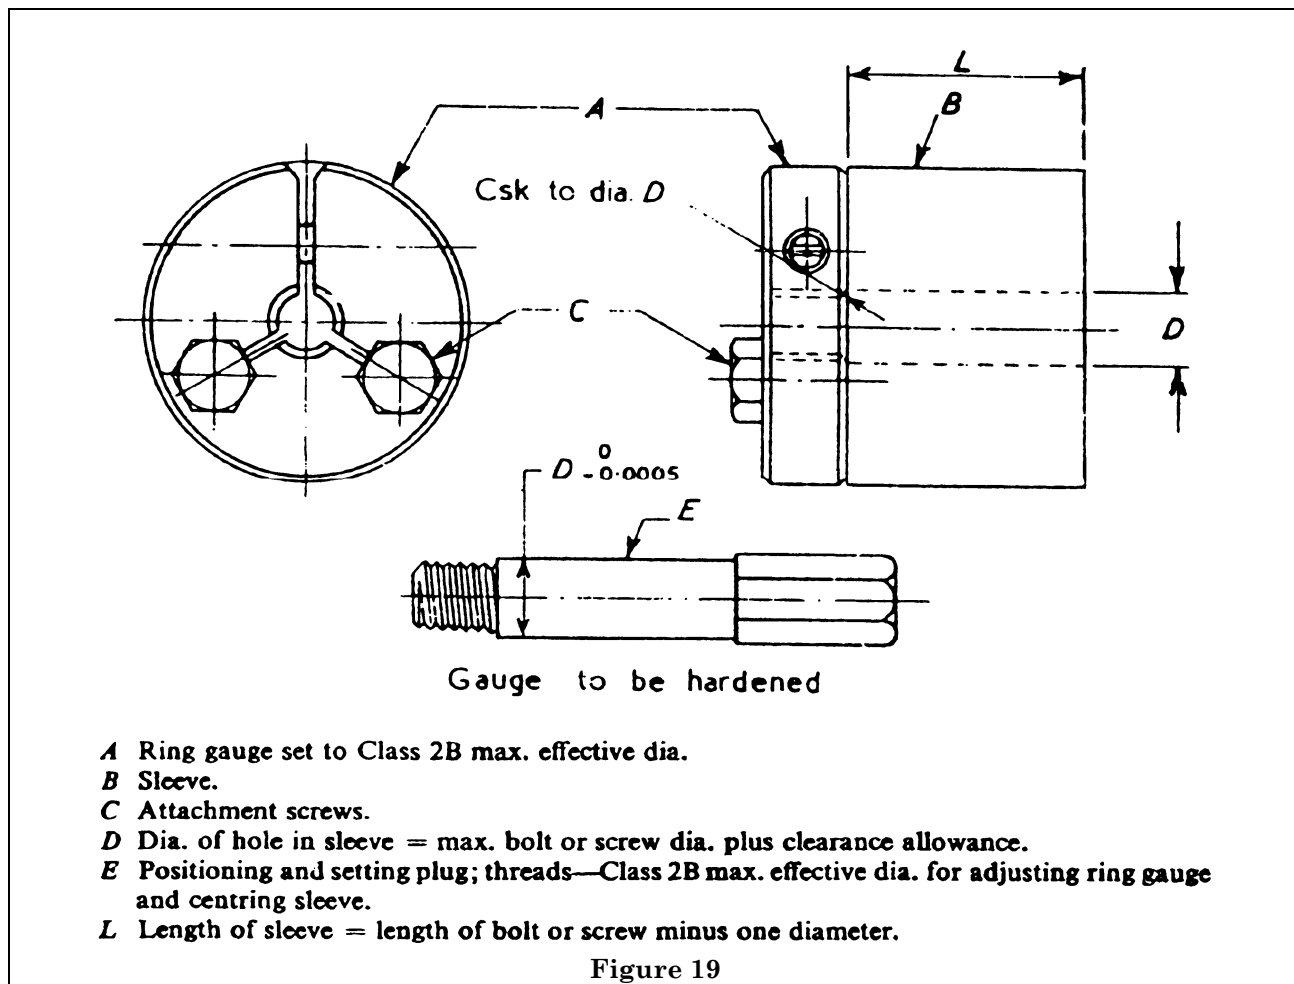


Two types of sleeve gauges for checking eccentricity of thread in relation to body are illustrated above.


The optional type shown in Figure 19 permits the use of different length sleeves to accommodate different bolt lengths.

The ring Gauge *A* in this type is centred in position on sleeve *B* by means of positioning plug *E* and secured by means of attachment screws *C*. This plug also sets the ring gauge to the maximum effective diameter. The internal diameter *D* of the sleeve equals the nominal diameter of the bolt or screw plus the concentricity tolerance. The sleeve should extend beyond the last thread of the bolt or screw to be inspected but should not exceed 3 inches in length. Failure of the bolt or screw to enter the ring gauge or interference between the sleeve and bolt while engaging the ring gauge indicates excessive eccentricity between the thread and the body.

C.4 Squareness of thread to face of nut. *Clause 13.*

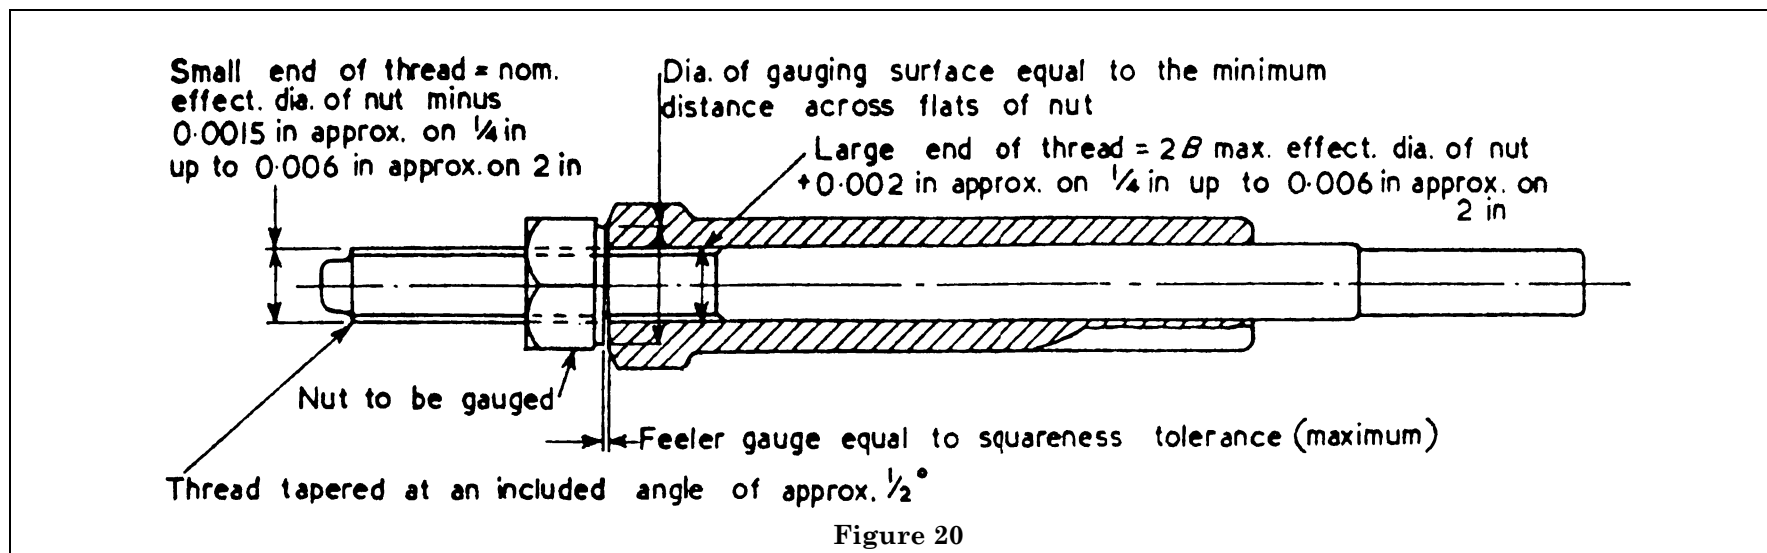

C.5 Off-centre distance between centre line of split pin hole in bolt and axis of thread (Figure 21) and off centre distance between centre line of slots in slotted nuts and axis of tapped hole (Figure 22) *Clause 15.*

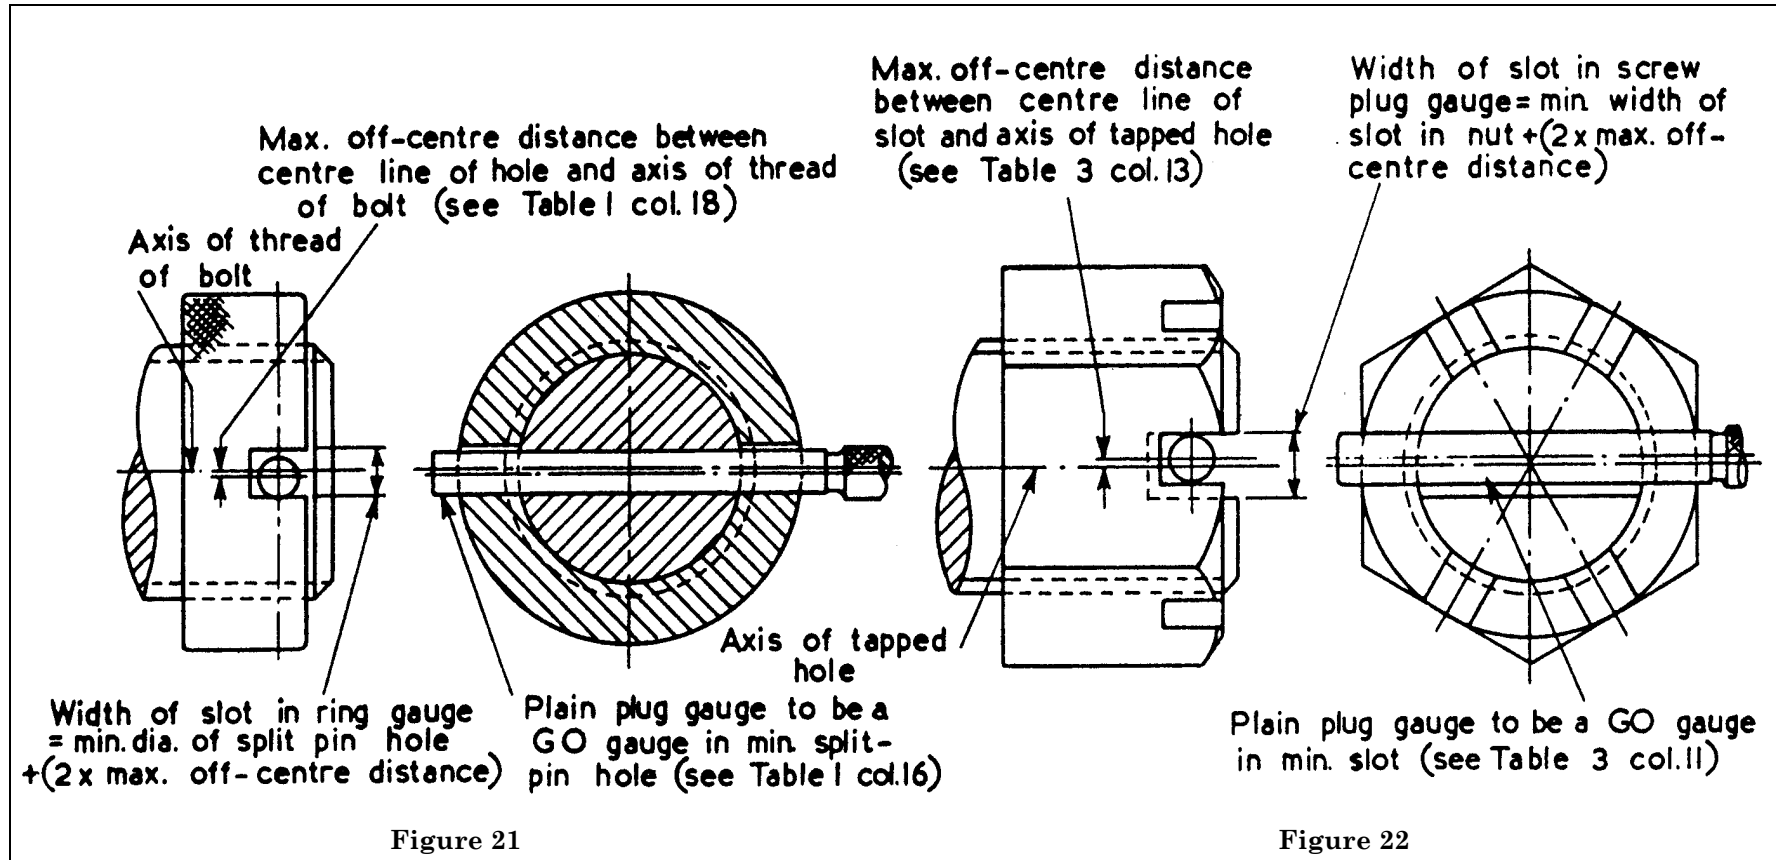

It is recommended that the screw ring gauge and the screw plug gauge illustrated above be made to the tolerances specified for screw gauges in BS 919-1, "Gauges for screw threads of Unified form", and the plain plug gauges to the tolerances for plug gauges specified in BS 969, "Tolerances for plain limit gauges."

It is also recommended that the width of the slots in both the screw ring gauge and the screw plug gauge be made to the tolerances for gap gauges specified in BS 969. These tolerances should cover both the width of slot and the off-centre distance.

Appendix D Standard sizes of unified precision steel hexagon head bolts and screws and shortest lengths designated as bolts — Normal series

NOTE The sizes listed in Table 11 to Table 14 inclusive represent those which are expected to be in greatest demand and which are most likely to be stocked by bolt and nut manufacturers.

Table 11 — Grade A bright hexagon bolts

Nominal size <i>D</i>	Nominal length in inches													
	1 ¹ / ₄	1 ¹ / ₂	1 ³ / ₄	2	2 ¹ / ₄	2 ¹ / ₂	2 ³ / ₄	3	3 ¹ / ₂	4	4 ¹ / ₂	5	5 ¹ / ₂	6
1/4	X	X	X	X	X	X	X	X	X	—	—	—	—	—
5/16	X	X	X	X	X	X	X	X	X	X	—	—	—	—
3/8	—	X	X	X	X	X	X	X	X	X	X	X	—	—
7/16	—	X	X	X	X	X	X	X	X	X	X	X	—	—
1/2	—	—	X	X	X	X	X	X	X	X	X	X	X	X
5/8	—	—	—	X	X	X	X	X	X	X	X	X	X	X
3/4	—	—	—	—	X	X	X	X	X	X	X	X	X	X
7/8	—	—	—	—	—	X	X	X	X	X	X	X	X	X
1	—	—	—	—	—	—	—	X	X	X	X	X	X	X

For shorter lengths see Table 12 for Screws. See also Table 15 for shortest lengths designated as bolts.

Table 12 — Grade A Bright Hexagon Screws

Nominal size <i>D</i>	Nominal length in inches													
	1/2	5/8	3/4	1	1 ¹ / ₄	1 ¹ / ₂	1 ³ / ₄	2	2 ¹ / ₄	2 ¹ / ₂	3	3 ¹ / ₂	4	
1/4	X	X	X	X	X	X	—	—	—	—	—	—	—	
5/16	X	X	X	X	X	X	X	X	—	—	—	—	—	
3/8	—	—	X	X	X	X	X	X	—	—	—	—	—	
7/16	—	—	—	X	X	X	X	X	—	—	—	—	—	
1/2	—	—	—	X	X	X	X	X	—	—	—	—	—	
5/8	—	—	—	—	X	X	X	X	X	X	X	—	—	
3/4	—	—	—	—	—	X	X	X	X	X	X	—	—	
7/8	—	—	—	—	—	—	—	—	X	X	X	X	X	
1	—	—	—	—	—	—	—	—	—	X	X	X	X	

Table 13 — Grade S heat treated hexagon bolts

Nominal size <i>D</i>	Nominal length in inches																
	1 ¹ / ₈	1 ¹ / ₄	1 ³ / ₈	1 ¹ / ₂	1 ³ / ₄	2	2 ¹ / ₄	2 ¹ / ₂	2 ³ / ₄	3	3 ¹ / ₄	3 ¹ / ₂	4	4 ¹ / ₂	5	5 ¹ / ₂	6
1/4	X	X	X	X	X	X	X	X	X	X	X	X	X	—	—	—	—
5/16	—	X	X	X	X	X	X	X	X	X	X	X	X	X	X	—	X
3/8	—	—	X	X	X	X	X	X	X	X	X	X	X	X	X	—	X
7/16	—	—	—	X	X	X	X	X	X	X	X	X	X	X	X	—	X
1/2	—	—	—	—	X	X	X	X	X	X	X	X	X	X	X	X	X
5/8	—	—	—	—	—	X	X	X	X	X	X	X	X	X	X	X	X
3/4	—	—	—	—	—	—	X	X	X	X	X	X	X	X	X	X	X
7/8	—	—	—	—	—	—	—	X	X	X	X	X	X	X	X	X	X
1	—	—	—	—	—	—	—	—	X	X	X	X	X	X	X	X	X

For shorter lengths see Table 14 for Screws. See also Table 15 for shortest lengths designated as bolts.

Table 14 — Grade S heat treated hexagon screws

Nominal size <i>D</i>	Nominal length in inches															
	1/2	5/8	3/4	7/8	1	1 ¹ / ₄	1 ¹ / ₂	1 ³ / ₄	2	2 ¹ / ₄	2 ¹ / ₂	2 ³ / ₄	3	3 ¹ / ₂	4	
1/4	X	X	X	X	X	X	X	—	X	X	X	X	X	—	—	
5/16	—	X	X	X	X	X	X	—	X	X	X	X	X	X	X	
3/8	—	—	X	X	X	X	X	—	—	—	—	—	—	—	—	
7/16	—	—	X	X	X	X	X	X	X	X	X	X	X	X	X	
1/2	—	—	—	X	X	X	X	X	X	X	X	X	X	X	X	
5/8	—	—	—	—	—	X	X	X	X	X	X	X	X	X	X	
3/4	—	—	—	—	—	—	X	X	X	X	X	X	X	X	X	
7/8	—	—	—	—	—	—	X	X	X	X	X	X	X	X	X	
1	—	—	—	—	—	—	—	—	X	X	X	X	X	X	X	



Table 15 — Shortest lengths designated as bolts
(See Clause 12 a)


Nominal size <i>D</i>	Shortest length of bolt
in	in
$\frac{1}{4}$	$1\frac{1}{8}$
$\frac{5}{16}$	$1\frac{1}{4}$
$\frac{3}{8}$	$1\frac{3}{8}$
$\frac{7}{16}$	$1\frac{1}{2}$
$\frac{1}{2}$	$1\frac{5}{8}$
$\frac{9}{16}$	$1\frac{7}{8}$
$\frac{5}{8}$	2
$\frac{3}{4}$	$2\frac{1}{4}$
$\frac{7}{8}$	$2\frac{1}{2}$
1	$2\frac{3}{4}$
$1\frac{1}{8}$	$3\frac{1}{4}$
$1\frac{1}{4}$	$3\frac{1}{2}$
$1\frac{3}{8}$	4
$1\frac{1}{2}$	$4\frac{1}{4}$
$1\frac{3}{4}$	$4\frac{3}{4}$
2	$5\frac{1}{2}$

Appendix E Details of identification marking for unified hexagon bolts, screws & nuts (see Clause 16)

NOTE All dimensions given are for the guidance of the manufacturer and are not part of the requirements of the standard.

NOTE The groove is approximately midway between the major diameter of the thread and the flats of the hexagon. The groove shall not exceed 0.020 in wide and 0.010 in deep.

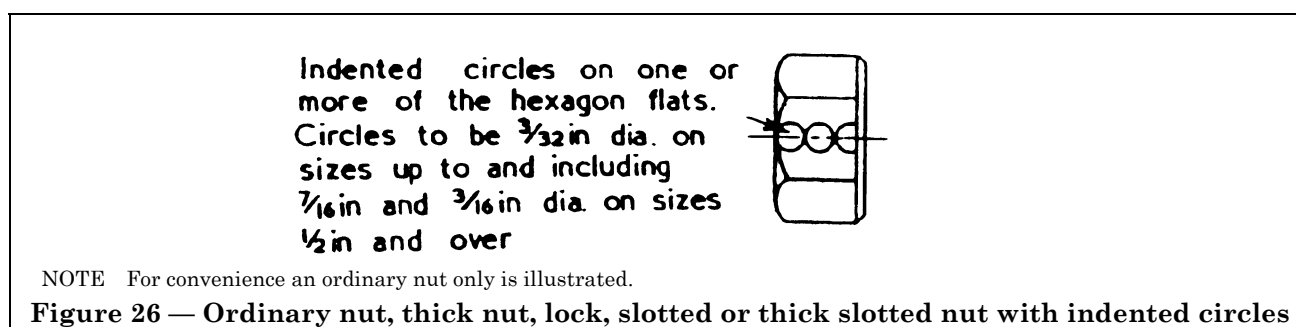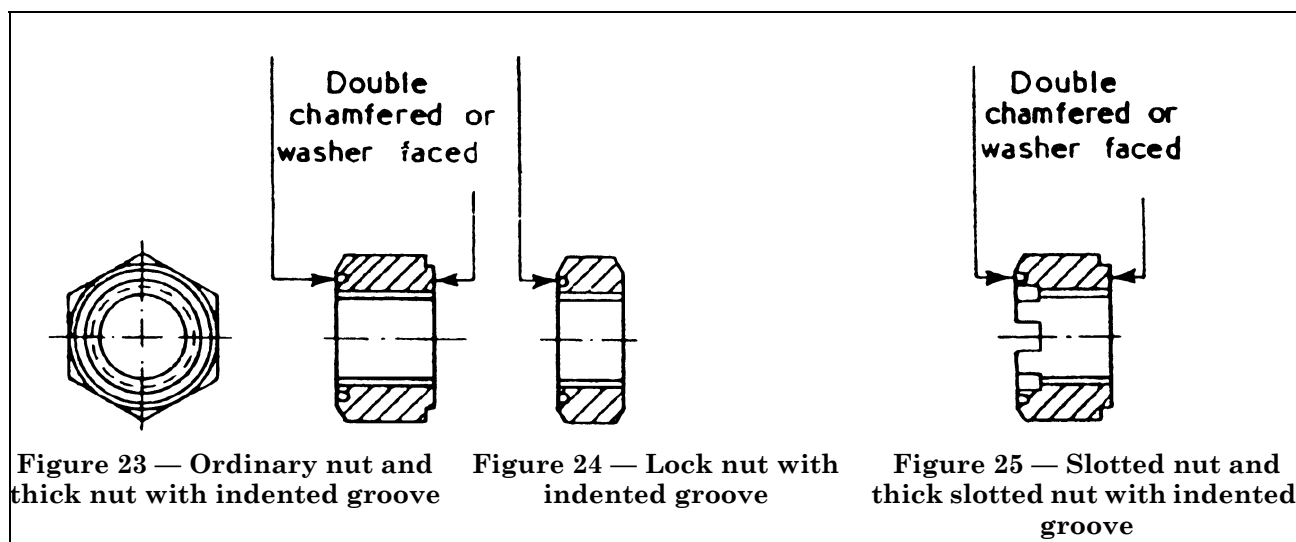

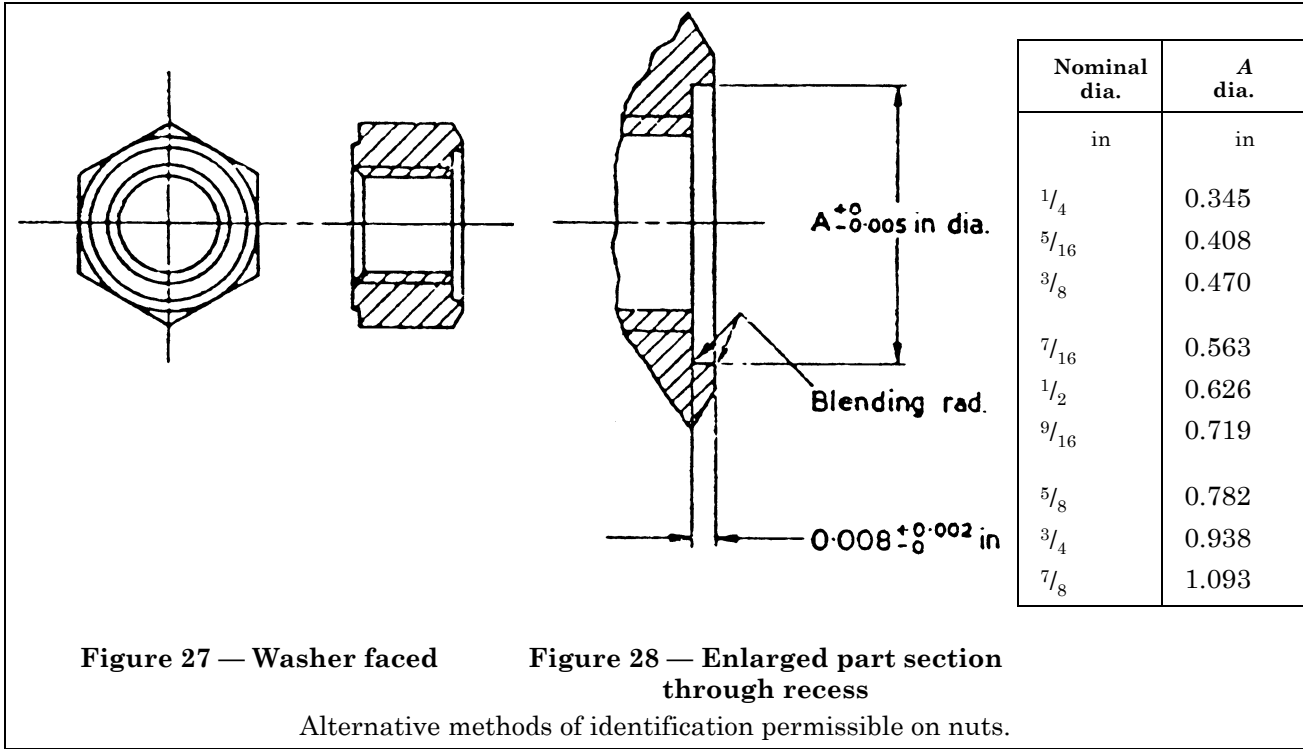

Licensed Copy: :FULLNAME, : DATE, Uncontrolled Copy, (c) BSI

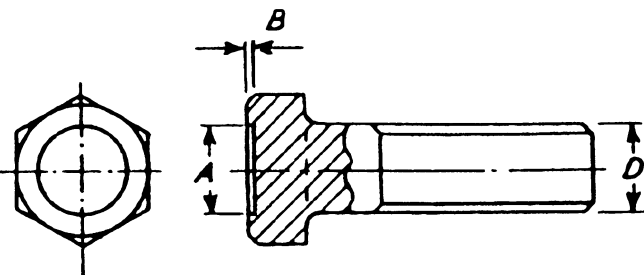


Figure 29 — Bolt or screw with recess

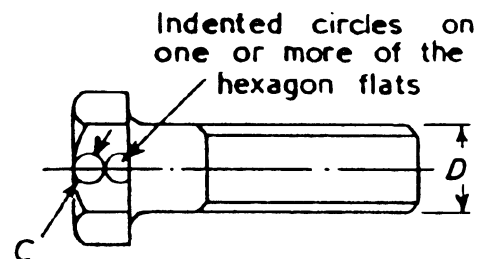


Figure 30 — Bolt or screw with indented circles

Alternative methods of identification permissible on bolts and screws

1	2	3	4	5	6
Nominal size <i>D</i>	Recess				Indented circles
	Diameter <i>A</i>		Depth <i>B</i>		Diameter <i>C</i>
	max.	min.	max.	min.	nom.
in	in	in	in	in	in
$1/4$	$1/4$	$3/16$	0.008	0.005	$3/32$
$5/16$	$5/16$	$1/4$	0.008	0.005	$3/32$
$3/8$	$3/8$	$5/16$	0.008	0.005	$3/32$
$7/16$	$7/16$	$3/8$	0.013	0.010	$3/32$
$1/2$	$1/2$	$7/16$	0.013	0.010	$3/16$
$9/16^a$	$9/16$	$1/2$	0.013	0.010	$3/16$
$5/8$	$5/8$	$9/16$	0.018	0.015	$3/16$
$3/4$	$3/4$	$11/16$	0.018	0.015	$3/16$
$7/8$	$7/8$	$13/16$	0.018	0.015	$3/16$
1	1	$15/16$	0.018	0.015	$3/16$
$1^1/8$	$1^1/8$	$1^1/16$	0.030	0.020	$1/4$
$1^1/4$	$1^1/4$	$1^3/16$	0.030	0.020	$1/4$
$1^3/8^a$	$1^3/8$	$1^5/16$	0.030	0.020	$1/4$
$1^1/2$	$1^1/2$	$1^7/16$	0.030	0.020	$1/4$
$1^3/4$	$1^3/4$	$1^11/16$	0.030	0.020	$1/4$
2	2	$1^15/16$	0.030	0.020	$1/4$

^a To be dispensed with wherever possible.

Appendix F Formulae

For dimensions of hexagons for standard bolts, screws and nuts reference should always be made to Table 1, Table 2 and Table 3. The proportions of hexagons for bolts, screws and nuts in intermediate sizes and sizes larger than 2 in should be derived from the formulae extracted from the American Standard and given below. Tolerances may be extrapolated from Table 1, Table 2 or Table 3 as appropriate.

Bolts and screws heads			
Width across flats		Height of head	
Nominal size D	Width	Nominal size D	Height
in	in	in	in
$\frac{1}{4}$	$1\frac{1}{2} D + \frac{1}{16}$	$\frac{1}{4}$ to $\frac{7}{8}$	$\frac{5}{8} D$
$\frac{5}{16}$ to 4	$1\frac{1}{2} D$	1 to $1\frac{7}{8}$	$\frac{5}{8} D - \frac{1}{84}$
—	—	2 to $2\frac{3}{4}$	$\frac{5}{8} D - \frac{1}{32}$
—	—	3	$\frac{5}{8} D$
—	—	$3\frac{1}{4}$ to $3\frac{3}{4}$	$\frac{5}{8} D - \frac{1}{16}$
—	—	4	$\frac{5}{8} D$

Nuts				
	Width across flats		Thickness of nut	
	Nominal size D	Width	Nominal size D	Thickness
	in	in	in	in
Ordinary and slotted	$\frac{1}{4}$	$1\frac{1}{2} D + \frac{1}{16}$	$\frac{1}{4}$ to $\frac{5}{8}$	$\frac{7}{8} D$
	$\frac{5}{16}$ to 3	$1\frac{1}{2} D$	$\frac{3}{4}$ to $1\frac{1}{8}$	$\frac{7}{8} D - \frac{1}{64}$
			$1\frac{1}{4}$ to 2	$\frac{7}{8} D - \frac{1}{32}$
			$2\frac{1}{4}$ to 3	$\frac{7}{8} D - \frac{1}{64}$
Lock	$\frac{1}{4}$	$1\frac{1}{2} D + \frac{1}{16}$	$\frac{1}{4}$ to $\frac{5}{8}$	(See Table)
	$\frac{5}{16}$ to 3	$1\frac{1}{2} D$	$\frac{3}{4}$ to $1\frac{1}{8}$	$\frac{1}{2} D + \frac{3}{64}$
			$1\frac{1}{4}$ to 2	$\frac{1}{2} D + \frac{3}{32}$
			$2\frac{1}{4}$	$\frac{1}{2} D + \frac{5}{64}$
			$2\frac{1}{2}$ to 3	$\frac{1}{2} D + \frac{13}{64}$
Thick and thick slotted	$\frac{1}{4}$	$1\frac{1}{2} D + \frac{1}{16}$	(See Table)	
	$\frac{5}{16}$ to $1\frac{1}{2}$	$1\frac{1}{2} D$		

British Standards

The following are available on application:

YEARBOOK

Including subject index and numerical list of British Standards

SECTIONAL LISTS. Gratis

Acoustics

Aerospace materials and components

Automobile

Building materials and components

Chemical engineering

Chemicals, fats, oils, scientific apparatus, etc.

Cinematography and photography

Coal, coke and colliery requisites

Codes of Practice

Consumer goods

Documentation, including Universal Decimal Classification

Drawing practice

Electrical engineering

Farming, dairying and allied interests

Furniture, bedding and furnishings

Gardening, horticulture and landscape work

Gas and solid fuel and refractories

Glassware including scientific apparatus

Hospital equipment

Illumination and lighting fittings

Industrial instruments, etc.

Iron and steel

Leather, Plastics, Rubber

Machine tools

Mechanical engineering

Nomenclature, symbols and abbreviations

Non-ferrous metals

Nuclear energy

Packaging and containers

Paints, varnishes, paint materials and colours for paints

Personal safety equipment

Petroleum industry

Printing, paper and stationery

Road engineering

Shipbuilding

Textiles and clothing

Welding

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.

BSI
389 Chiswick High Road
London
W4 4AL